

# **Caustic-Side Solvent Extraction: Chemical and Physical Properties of the Optimized Solvent**

**October 2002**

**Prepared by**

**Lætitia H. Delmau**

**Joseph F. Birdwell, Jr.**

**Peter V. Bonnesen**

**Linda J. Foote**

**Tamara J. Haverlock**

**Leon N. Klatt**

**Douglas D. Lee**

**Ralph A. Leonard**

**Tatiana G. Levitskaia**

**Michael P. Maskarinec**

**Bruce A. Moyer**

**Frederick V. Sloop, Jr.**

**Bruce A. Tomkins**

#### DOCUMENT AVAILABILITY

Reports produced after January 1, 1996, are generally available free via the U.S. Department of Energy (DOE) Information Bridge:

**Web site:** <http://www.osti.gov/bridge>

Reports produced before January 1, 1996, may be purchased by members of the public from the following source:

National Technical Information Service  
5285 Port Royal Road  
Springfield, VA 22161  
**Telephone:** 703-605-6000 (1-800-553-6847)  
**TDD:** 703-487-4639  
**Fax:** 703-605-6900  
**E-mail:** [info@ntis.fedworld.gov](mailto:info@ntis.fedworld.gov)  
**Web site:** <http://www.ntis.gov/support/ordernowabout.htm>

Reports are available to DOE employees, DOE contractors, Energy Technology Data Exchange (ETDE) representatives, and International Nuclear Information System (INIS) representatives from the following source:

Office of Scientific and Technical Information  
P.O. Box 62  
Oak Ridge, TN 37831  
**Telephone:** 865-576-8401  
**Fax:** 865-576-5728  
**E-mail:** [reports@adonis.osti.gov](mailto:reports@adonis.osti.gov)  
**Web site:** <http://www.osti.gov/contact.html>

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

**CAUSTIC-SIDE SOLVENT EXTRACTION :  
CHEMICAL AND PHYSICAL PROPERTIES OF THE OPTIMIZED SOLVENT**

Lætitia H. Delmau, Joseph F. Birdwell, Jr., Peter V. Bonnesen, Linda J. Foote,  
Tamara J. Haverlock, Leon N. Klatt, Douglas D. Lee, Ralph A. Leonard, Tatiana G. Levitskaia,  
Michael P. Maskarinec, Bruce A. Moyer, Frederick V. Sloop, Jr., and Bruce A. Tomkins

Date Published: October 2002

Prepared by  
OAK RIDGE NATIONAL LABORATORY  
P.O. Box 2008  
Oak Ridge, Tennessee 37831-6285  
managed by  
UT-Battelle, LLC  
for the  
U.S. DEPARTMENT OF ENERGY  
under contract DE-AC05-00OR22725



## CONTENTS

	<b>Page</b>
LIST OF FIGURES .....	vii
LIST OF TABLES .....	ix
EXECUTIVE SUMMARY .....	1
ABSTRACT .....	3
1. INTRODUCTION .....	3
2. CAUSTIC-SIDE SOLVENT EXTRACTION SOLVENT COMPOSITION RECOMMENDATION .....	5
2.1 BASIS FOR TASK AND SUMMARY RECOMMENDATION .....	5
2.2 EXPERIMENTAL APPROACHES .....	7
2.2.1 Solvent Test Samples .....	7
2.2.2 Experimental Procedures .....	8
2.2.2.1 BOBCalixC6 solubility studies .....	8
2.2.2.2 Extraction, scrub, and strip protocol .....	8
2.2.2.3 Third-phase determination .....	9
2.2.2.4 Dispersion-number measurement .....	9
2.2.2.5 Density .....	10
2.2.2.6 Viscosity .....	10
2.2.2.7 Surface tension and interfacial tension .....	11
2.3 EXPERIMENTAL RESULTS .....	12
2.3.1 BOBCalixC6 Solubility .....	12
2.3.2 Cesium Distribution Results .....	17
2.3.3 Flowsheet Robustness .....	19
2.3.4 Third-Phase Formation .....	21
2.3.5 Solvent Dispersion Numbers .....	22
2.3.6 Solvent Density .....	24
2.3.7 Solvent Viscosity .....	26
2.3.8 Solvent Interfacial Tension .....	29
2.4 SOLVENT-COMPOSITION RECOMMENDATION PROCESS .....	32
3. CESIUM DISTRIBUTION BEHAVIOR .....	35
3.1 INTRODUCTION .....	35
3.2 EXPERIMENTAL SECTION .....	35
3.3 RESULTS AND DISCUSSION .....	35
3.3.1 Extraction, Scrub, and Strip Performance .....	35
3.3.2 Temperature Variation .....	36
3.3.3 Multicycle Behavior .....	39
3.4 CONCLUSIONS .....	39
4. PARTITIONING OF SOLVENT COMPONENTS .....	41
4.1 INTRODUCTION .....	41
4.2 EXPERIMENTAL SECTION .....	41

4.2.1	Material and Contacting Method.....	41
4.2.2	Calixarene and Modifier Analyses .....	42
4.2.3	Tri- <i>n</i> -octylamine Analyses .....	43
4.3	RESULTS AND DISCUSSION .....	44
4.3.1	Calixarene Partitioning .....	44
4.3.2	Modifier Partitioning .....	44
4.3.3	Tri- <i>n</i> -octylamine Partitioning.....	45
4.4	CONCLUSIONS .....	46
5.	DISTRIBUTION OF MINOR ORGANIC AND INORGANIC COMPONENTS.....	49
5.1	INTRODUCTION .....	49
5.2	EXPERIMENTAL SECTION .....	49
5.3	RESULTS AND DISCUSSION .....	51
5.3.1	Distribution of Dibutylphosphate.....	51
5.3.2	Distribution of Other Metals and Selected Radionuclides .....	51
5.3.3	Effect of Organic Surfactants .....	54
5.4	CONCLUSIONS .....	55
6.	THERMAL STABILITY.....	57
6.1	INTRODUCTION .....	57
6.2	EXPERIMENTAL SECTION .....	57
6.2.1	Materials, Equipment, and Contacting Method .....	57
6.2.2	ESS Analyses of Phase-Stability Samples .....	58
6.2.3	HPLC Analyses of Phase-Stability Samples.....	59
6.3	RESULTS AND DISCUSSION .....	59
6.3.1	Phase Stability at Low Temperature.....	59
6.3.2	Chemical Stability at High Temperature.....	64
6.4	CONCLUSIONS .....	64
7.	PHYSICAL-PROPERTIES MEASUREMENTS.....	67
7.1	INTRODUCTION .....	67
7.2	EXPERIMENTAL PROCEDURES .....	67
7.2.1	Chemicals.....	67
7.2.2	Determination of Dispersion Number.....	68
7.2.3	Laboratory Dispersion-Number Procedures .....	69
7.3	DISPERSION-NUMBER DETERMINATIONS .....	70
7.3.1	Extraction Dispersion-Number Determinations .....	70
7.3.2	Scrubbing-Condition Dispersion-Number Determinations .....	71
7.3.3	Stripping-Condition Dispersion-Number Determinations .....	74
7.4	MEASUREMENT OF SOLVENT DENSITIES .....	78
7.5	MEASUREMENT OF SOLVENT VISCOSITIES .....	81
7.6	DISCUSSION AND CONCLUSIONS .....	84
7.6.1	Dispersion Numbers.....	84
7.6.2	Solvent Density.....	85
7.6.3	Solvent Viscosity.....	86
8.	CONCLUSIONS.....	87
8.1	OVERALL ASSESSMENT.....	87
8.2	EVALUATION OF RESULTS .....	87
8.3	RECOMMENDATIONS FOR FUTURE WORK .....	88
8.3.1	Summary Remarks.....	88

8.3.2	Solvent Composition.....	88
8.3.3	Actinide and Strontium Extraction.....	89
8.3.4	Radiation Stability.....	89
8.3.5	Thermal Stability.....	90
8.3.6	Solvent Cleanup.....	90
8.3.7	Minor Species.....	90
8.3.8	Fate of Trimethylamine.....	91
8.3.9	Role of Nitrite.....	91
8.3.10	Modeling.....	91
9.	REFERENCES.....	93
APPENDIX A. PREDICTED $D_{Cs}$ VALUES USING THE log VERSUS log RELATIONSHIPS BETWEEN $D_{Cs}$ VALUES AND BOBCALIXC6 AND Cs-7SB MODIFIER CONCENTRATIONS....		99



## LIST OF FIGURES

Figure	Page
1 BOBCalixC6 solubility tests at 15 °C.....	13
2 BOBCalixC6 solubility tests at 25 °C.....	13
3 BOBCalixC6 solubility tests at 35 °C.....	14
4 Comparison of BOBCalixC6 solubility data .....	15
5 CSSX solvent dispersion numbers for extraction, scrub, and strip conditions at baseline O:A ratios	23
6 CSSX solvent dispersion numbers for solvent wash with dilute NaOH.....	23
7 CSSX solvent dispersion numbers for solvent washing as a function of NaOH concentration .....	24
8 CSSX solvent density as a function of Cs-7SB modifier concentration for 25.6 °C.....	25
9 Solvent viscosity as a function of temperature.....	26
10 Solvent shear stress as a function of temperature.....	27
11 Solvent and process solution surface tension .....	31
12 Solvent interfacial tension in extraction, scrub, and strip contacts.....	32
13 ESS tests at three different temperatures .....	38
14 ESS protocol for optimized solvent phase-stability test.....	58
15 Phase separation in the optimized solvent at 0 °C.....	60
16 Phase separation in the optimized solvent at -24 °C.....	61
17 Gel-like material formed during dispersion-number determinations.....	72
18 Graph of CSSX solvent extraction equilibration dispersion numbers.....	74
19 Graph of CSSX solvent scrub equilibration dispersion numbers .....	76
20 Graph of CSSX solvent strip equilibration dispersion numbers .....	77
21 Solvent density versus temperature.....	81
22 Solvent viscosity versus temperature.....	83
23 Solvent shear stress versus temperature.....	83



## LIST OF TABLES

<b>Table</b>	<b>Page</b>
1 Summary of selection criteria and associated property .....	6
2 Test sample compositions.....	7
3 Validation data for the modified ESS protocol.....	9
4 BOBCalixC6 solubility data from FY 2001 study .....	15
5 BOBCalixC6 solubility data from FY 2000 study .....	16
6 ESS results obtained with constant TOA concentration .....	18
7 ESS results obtained with two selected solvents with variable TOA concentrations .....	19
8 Calculated robustness for various CSSX solvent compositions .....	20
9 Temperature range for third-phase appearance .....	21
10 Dispersion numbers for extraction, scrub, and stripping of CSSX solvents .....	22
11 Dispersion numbers for washing of CSSX solvents B001107-3-4 and B001107-3-5.....	24
12 Solvent-density determinations .....	25
13 Solvent-viscosity determinations .....	27
14 Surface-tension determinations .....	29
15 Interfacial tension versus simulant.....	30
16 Interfacial tension versus scrub solution.....	30
17 Interfacial tension versus strip solution .....	31
18 Cesium batch ESS performance for previous-baseline and optimized solvents .....	36
19 ESS results for three different temperatures .....	37
20 Apparent enthalpy changes for each ESS stage.....	38
21 Two-cycle ESS tests .....	39
22 Partition ratios for BOBCalixC6.....	45
23 Partition ratios for modifier Cs-7SB .....	46
24 Partitioning of dibutylphosphate .....	51
25 Detection limits of non-extractable metals .....	52

26	Concentrations of metals present in the solvent after extraction .....	52
27	Concentrations of anions present in the solvent at each stage .....	53
28	Concentrations of strontium in the aqueous phase at each stage .....	53
29	Distribution ratios of technetium obtained in ESS tests.....	54
30	Effect of dodecanoate on cesium extraction in ESS tests .....	55
31	Phase separation at 0 °C for the previous-baseline and the optimized solvents.....	60
32	Phase compositions at 0 °C for the previous-baseline and the optimized solvents.....	61
33	Phase separation at -24 °C for the previous-baseline and the optimized solvents.....	62
34	Phase compositions at -24 °C for the previous-baseline and the optimized solvents.....	62
35	Solvent compositions at 0 °C for the previous-baseline and the optimized solvents.....	62
36	Solvent compositions at -24 °C for the previous-baseline and the optimized solvents.....	63
37	ESS tests at 25 °C using the low temperature-conditioned previous baseline solvent.....	63
38	ESS tests at 25 °C using the low temperature-conditioned optimized solvent.....	64
39	ESS tests at 25 °C using the high temperature-stressed optimized solvent.....	65
40	Simulant composition (major components).....	68
41	Materials for full simulant (added trace metals and organic species).....	69
42	Dispersion numbers for extraction with optimized CSSX solvent .....	73
43	Dispersion numbers for scrub with optimized CSSX solvent.....	75
44	Dispersion numbers for strip with optimized CSSX solvent .....	78
45	Water-density determinations .....	79
46	Optimized-solvent density determinations .....	80
47	Solvent-viscosity determinations .....	82
48	Dispersion numbers for CSSX solvent extraction, scrub, and stripping .....	84
49	Comparison of CSSX solvent densities .....	85
50	Comparison of solvent viscosities.....	86
A-1	Predicted $D_{Cs}$ values.....	97

## EXECUTIVE SUMMARY

The present work was undertaken to optimize the solvent used in the Caustic Side Solvent Extraction (CSSX) process and to measure key chemical and physical properties related to its performance. The CSSX process was selected by the USDOE in FY 2001 as the preferred technology for removal of cesium from the alkaline high-level salt waste stored in tanks at the Savannah River Site. This decision had been made with the understanding that the component concentrations of the baseline solvent employed till then would have to be adjusted to avoid supersaturation with respect to the extractant. Taking into consideration bounding requirements, an optimization of the solvent composition was performed, resulting in the following recommended component concentrations in Isopar<sup>®</sup> L diluent: 0.007 M calix[4]arene-bis(*tert*-octylbenzo-crown-6) (BOBCalixC6) extractant, 0.75 M 1-(2,2,3,3-tetrafluoropropoxy)-3-(4-*sec*-butylphenoxy)-2-propanol (Cs-7SB) phase modifier, and 0.003 M tri-*n*-octylamine (TOA) stripping aid. Criteria for this selection included BOBCalixC6 solubility, batch cesium distribution ratios ( $D_{Cs}$ ), calculated flowsheet robustness, third-phase formation, dispersion numbers, and density. Although some minor compromises within acceptable limits were made in flowsheet robustness and solvent density, significant benefits from solvent optimization were gained in lower risk of third-phase formation (operation to as low as 11 °C at high cesium and potassium loading versus 20 °C using the previous solvent) and lower solvent cost. The solubility of BOBCalixC6 in Isopar<sup>®</sup> L containing 0.5–1.0 M Cs-7SB at 15–35 °C was examined by monitoring the concentration of BOBCalixC6 as it precipitated from supersaturated solutions over a period of approximately 9 months. Its solubility at 0.75 M Cs-7SB was found to be 7.7 mM at 25 °C. Extract/scrub/strip (ESS) tests showed that the optimized solvent performs acceptably; the extraction strength from baseline waste simulant is lower by 20%, but this is compensated partially by 5–14% improved stripping. When the optimized solvent was washed with an aqueous solution of 10 mM sodium hydroxide following an ESS test, identical  $D_{Cs}$  values were obtained on a second ESS test with fresh aqueous phases. The temperature dependence of  $D_{Cs}$  values in ESS testing was found to be similar to that of the former baseline solvent, and parameters are reported for the estimation of  $D_{Cs}$  values for ESS contacts in the range 15–35 °C. Measurements of the partition ratios of BOBCalixC6, Cs-7SB, and TOA between the optimized solvent and aqueous process solutions indicate that the losses of these solvent components by partitioning to the aqueous process solutions will be negligible to minor. Respective fractional replacements of the three components due solely to partitioning losses over the course of one year are estimated to be 4%, 27%, and 9% respectively. The partitioning behavior of selected organic anions examined in studies of the previous baseline solvent were repeated with the optimized solvent with no change in behavior found. For example, dibutylphosphate, present in the waste in trace amounts, will partition weakly into the solvent on extraction, and the fraction that is extracted will remain in the solvent to be washed out efficiently by the NaOH wash stage. Similarly, trace metal distribution was not significantly changed. Trace Ag, Cr, Cu, Hg, Mn, Mo, Pb, Pd, Rh, Ru, Sn, and Zn were not extracted; traces of Al, Ca, Sr, and Fe were detected in the optimized solvent after extraction but are scrubbed out. The bulk metals Na and K are also extracted as expected, and these are also scrubbed out. Technetium in the form of pertechnetate anion is extracted very weakly from the simulant ( $D_{Tc} = 0.038$  or 1% extracted) and, like dibutylphosphate, remains in the solvent in the acidic scrub and strip stages, subsequently to be washed out in the NaOH wash stage. On storage at or below 0 °C, both the previous and optimized solvents exhibit phase splitting in which the more dense of two phases is concentrated in BOBCalixC6 and Cs-7SB. On warming to room temperature and remixing, the solvents are restored to their original composition and ESS performance. A 43-day test of the solvent stability to elevated temperatures, 35 and 60 °C, showed no evidence of degraded ESS performance. The physical properties density, viscosity, and dispersion number for the solvent against full simulant, scrub, and strip solutions at 15–35 °C were measured and found to be adequate for contactor operation. Dispersion numbers ( $N_{Di}$ ) under all conditions met the criterion  $N_{Di} > 4 \times 10^{-4}$ ; the solvent density and viscosity at 25 °C were respectively  $0.8516 \pm 0.0001$  and  $3.51 \pm 0.1$  cP. Overall, optimization and testing of the CSSX solvent has reduced the technical risk of the CSSX process by resolving previously identified issues and raising no new issues.

## ABSTRACT

This work was undertaken to optimize the solvent used in the Caustic Side Solvent Extraction (CSSX) process and to measure key chemical and physical properties related to its performance in the removal of cesium from the alkaline high-level salt waste stored in tanks at the Savannah River Site. The need to adjust the solvent composition arose from the prior discovery that the previous baseline solvent was supersaturated with respect to the calixarene extractant. The following solvent-component concentrations in Isopar<sup>®</sup> L diluent are recommended: 0.007 M calix[4]arene-bis(*tert*-octylbenzo-crown-6) (BOBCalixC6) extractant, 0.75 M 1-(2,2,3,3-tetrafluoropropoxy)-3-(4-*sec*-butylphenoxy)-2-propanol (Cs-7SB) phase modifier, and 0.003 M tri-*n*-octylamine (TOA) stripping aid. Criteria for this selection included BOBCalixC6 solubility, batch cesium distribution ratios ( $D_{Cs}$ ), calculated flowsheet robustness, third-phase formation, coalescence rate (dispersion numbers), and solvent density. Although minor compromises within acceptable limits were made in flowsheet robustness and solvent density, significant benefits were gained in lower risk of third-phase formation and lower solvent cost. Data are also reported for the optimized solvent regarding the temperature dependence of  $D_{Cs}$  in extraction, scrubbing, and stripping (ESS); ESS performance on recycle; partitioning of BOBCalixC6, Cs-7SB, and TOA to aqueous process solutions; partitioning of organic anions; distribution of metals; solvent phase separation at low temperatures; solvent stability to elevated temperatures; and solvent density and viscosity. Overall, the technical risk of the CSSX process has been reduced by resolving previously identified issues and raising no new issues.

## 1. INTRODUCTION

The Caustic-Side Solvent-Extraction (CSSX) process [1,2] for cesium removal from alkaline high-level waste has been developed for application at the United States Department of Energy (USDOE) Savannah River Site (SRS) [3]. In 2001 the USDOE selected the CSSX process flowsheet as the preferred technology for this application [4,5] following an evaluation of alternative technologies [6–10]. This selection was largely founded on extensive testing and demonstration data that successfully addressed four high technology risks, including chemical stability [11], radiation stability [11–15], proof-of-concept demonstration with waste simulant [15], and demonstration with actual SRS high-level waste [16]. All criteria were met or even exceeded. The contactor tests using simulated- and actual-waste feeds met their goals for decontamination factor ( $DF \geq 40,000$ ) and concentration factor ( $CF \geq 15$ ) [15,16]. The stability of solvent to chemical, thermal, and radiation stresses was shown to be high, indicating a solvent lifetime significantly greater than one year [11-15]. Extensive data characterizing the distribution behavior of major and minor system components in extraction, scrubbing, and stripping (ESS) were collected, and effective means for solvent cleanup were described [11]. As work for technology selection drew to a close in April 2001, issues for continued research and development (R&D) were identified [7,11], ultimately leading to renewed effort through the end of FY 2002 [18]. The most important issue regarding chemical and physical properties was the probable supersaturation of the solvent. Namely, the solubility of the calixarene in the solvent comprising the modifier and tri-*n*-octylamine in Isopar<sup>®</sup> L

appeared to be lower than the 10 mM used in the baseline solvent. Since the calixarene solubility increased with increasing concentration of modifier, the issue of supersaturation was apparently resolvable with little risk by an adjustment of the concentrations of the solvent components. Hence, technology selection proceeded with the understanding that such an adjustment would be necessary early in the subsequent R&D phase.

Following the selection of the CSSX technology, systematic measurements were performed in late FY 2001 and early FY 2002 toward selection of the new optimized concentrations of the three solvent components. In addition to BOBCalixC6 solubility, the dependence of cesium ESS behavior, flowsheet robustness, coalescence, third-phase formation, and solvent density also were factored into the optimization. The conclusions of this initial phase of the work reported herein form the basis of the selection of the optimum solvent composition described in Chapter 2. In the course of the solvent-optimization effort and subsequent experiments, the flowsheet and its requirements were assumed to be unchanged. Hence, the compositions of the aqueous waste simulant, scrub solution, and strip solution remained the same. The reader is referred to a prior report for a complete description of the baseline simulant [11]; its composition may be found in Chapter 7 of the present report.

The changed solvent composition necessitated further characterization of the properties of the optimized solvent, as reflected in program plans [18]. Since rather minor changes were expected in the behavior of the optimized solvent as compared with the previous baseline solvent, a less ambitious testing regimen was undertaken. Chapter 3 describes the cesium distribution behavior in batch ESS tests, its temperature dependence, and a confirmation of the recyclability of the solvent. Chapter 4 re-examines the question of partitioning of the solvent components between the solvent and aqueous process solutions, affording an opportunity to reduce the uncertainties in evaluating loss rates of the solvent components. Chapter 5 focuses on how other system constituents, including both organic and inorganic species, distribute under process conditions. Chapter 6 confirms the chemical and thermal stability of the solvent under process conditions. Finally, Chapter 7 provides data on solvent density and viscosity, as well as its dispersion numbers in contact with process solutions. Overall, the experiments conducted on the optimized solvent were intended to reduce the risk that the changed composition would lead to an unacceptable change in process performance. In reporting results toward reducing this risk, this document not only establishes the properties of the optimized solvent, but it also serves as a companion to the previous inclusive report on the previous baseline solvent [11].

## 2. CAUSTIC-SIDE SOLVENT EXTRACTION SOLVENT-COMPOSITION RECOMMENDATION

### 2.1. BASIS FOR TASK AND SUMMARY RECOMMENDATION

The purpose of this chapter is to provide the experimental information that forms the basis for a recommended change in the baseline composition of the caustic-side solvent extraction (CSSX) solvent. In the year and a half prior to technology selection in May 2001, the baseline CSSX solvent composition was 0.010 M calix[4]arene-bis(*tert*-octylbenzo-crown-6), known as BOBCalixC6; 0.5 M 1-(2,2,3,3-tetrafluoropropoxy)-3-(4-*sec*-butylphenoxy)-2-propanol, known as Cs-7SB modifier; and 0.001 M tri-*n*-octylamine (TOA) in the diluent Isopar<sup>®</sup> L [3]. Data for the solubility of BOBCalixC6 acquired and reported for the Salt Processing Program (SPP) alternative technology down-select decision showed the above composition is supersaturated with respect to BOBCalixC6 [11]. Although samples of the baseline solvent have been observed for approximately one year without any solids formation, the CSSX technical team recommended a solvent-composition optimization task be undertaken to address the BOBCalixC6 solubility and other issues [19] such as third-phase formation, as a function of the plant operating temperature.

To accomplish the task of recommending a new baseline solvent composition, the CSSX technical team, the Tanks Focus Area (TFA), and SPP management team, in cooperation with the U.S. Department of Energy–Savannah River, developed an experimental program designed to provide the required information. Part of this effort included the development of the solvent-composition selection criteria [20].

The recommendation for the new solvent composition is a consensus opinion of the CSSX technical team. Based on the results to follow in this chapter, the recommended composition is as follows:

- 0.007 M BOBCalixC6 extractant,
- 0.75 M Cs-7SB modifier,
- 0.003 M TOA stripping aid (sometimes referred to as a suppressor), and
- Isopar<sup>®</sup> L diluent.

Table 1 contains a summary of the bounding and goal-selection criteria and the value of the experimental property for the respective criterion for the recommended solvent composition.

**Table 1. Summary of selection criteria and associated properties**

Criterion	Bounding condition	Goal condition	Value of property
BOBCalixC6 solubility	Thermodynamically stable	Thermodynamically stable	$\geq 7.55$ mM @ 25 °C
$D_{Cs}$ values	Extraction $D_{Cs} > 8$ Scrub $D_{Cs} > 0.6$ Strip $D_{Cs} < 0.16$	Extraction $D_{Cs} > 17.8$ Scrub $D_{Cs} > 1.6$ Strip $D_{Cs} < 0.15$	Extraction $D_{Cs} = 14.1$ Scrub $D_{Cs} = 1.3$ Strip $D_{Cs} = 0.10$
Flowsheet robustness	1.0	3.0	$> 8.0$
Third-phase formation	15 °C $\leq$ T $\leq$ 35 °C at $[K^+] = 0.05$ M	15 °C $\leq$ T $\leq$ 35 °C at $[K^+] = 0.05$ M	$< 10$ °C at $[K^+] = 0.05$ M
Dispersion number against simulant, scrub, and strip solutions	$> 4.0 \times 10^{-4}$	$> 4.0 \times 10^{-4}$	$> 5.0 \times 10^{-4}$
Dispersion number against NaOH wash solution	$> 4.0 \times 10^{-4}$	$> 4.0 \times 10^{-4}$	$> 4.5 \times 10^{-4}$ at 0.3 M NaOH
Solvent density	$\approx 0.90$ g/mL at 25 °C	$\approx 0.86$ g/mL at 25 °C	0.85 g/mL at 25.6 °C

It should be noted that the criteria dealing with the change in the cesium distribution ratio  $D_{Cs}$  values as a function of solvent composition (i.e., solvent robustness) and the cost of solvent components did not enter into the decision process. These two criteria were intended to be used if the other criteria identified multiple acceptable compositions.

The results presented in the chapter were first documented in a report [21] of limited availability for use by the CSSX technical team in planning and initiating tasks in FY 2002. This document was later converted to an Oak Ridge National Laboratory (ORNL) report whose format is prescribed by the USDOE Office of Scientific and Technical Information (OSTI) [22]. In that the results are, for practical purposes, inseparable from the other results presented herein, the information is again reported in the form of the present chapter. In addition to minor editing, the only technical change of significance made in duplicating this material is the inclusion of the BOBCalixC6 solubility data collected at longer times. Hence, the present report represents the most comprehensive source of information to date on CSSX chemical and physical properties.

## 2.2 EXPERIMENTAL APPROACHES

### 2.2.1 Solvent Test Samples

A total of 13 test samples of solvent were prepared for this study. The compositions of these samples are given in Table 2. A sample of the baseline solvent was included for reference purposes. Single lots of modifier (Lot No. PVB B000894-48P) and BOBCalixC6 (Lot No. IBC 000714HMKC-0004) were used to prepare all of the test samples. Solvents containing 3 and 10 mM TOA were prepared by adding a measured amount of 0.2 M TOA in Isopar<sup>®</sup> L to the solvents originally prepared with 1 mM TOA. All solvents were washed twice with 0.1 M NaOH, twice with 0.05 M HNO<sub>3</sub>, three times with deionized water, and allowed to stand overnight before being decanted into clean containers. Scrub (0.05 M HNO<sub>3</sub>) and strip (0.001 M HNO<sub>3</sub>) solutions were prepared by diluting commercially available stock solutions with deionized water. Sodium hydroxide solutions were prepared by diluting a commercially available standard solution. Savannah River Site (SRS) waste supernatant simulant was formulated according to the SRS procedure [23]. The nominal cesium concentration in all simulant batches used in the testing was 0.00014 M. Aliquots of the solvent were transferred to the Nuclear Sciences and Technology Division (NSTD) at Oak Ridge National Laboratory (ORNL) for measurements of dispersion number, viscosity, density, surface tension, and interfacial tension. Other measurements, plus the initial solvent preparation, were carried out in the ORNL Chemical Sciences Division (CSD).

**Table 2. Test sample compositions**

Solvent identification	Test no.	[BOBCalixC6] (mM)	[Cs-7SB] (M)	[TOA] (mM)
Previous baseline		10	0.50	1
B001107-3-1	1	10	0.65	1
B001107-3-2	2	8	0.65	1
B001107-3-3	3	10	0.75	1
B001107-3-4	4	8	0.75	1
B001107-3-5	5	6	0.75	1
B001107-3-6	6	8	0.85	1
B001107-3-7	7	6	0.85	1
B001107-3-8	8	8	1.00	1
B001107-3-9	9	6	1.00	1
B001107-3-2A	10	8	0.65	3
B001107-3-2B	11	8	0.65	10
B001107-3-4C	12	8	0.75	3
B001107-3-4D	13	8	0.75	10

## 2.2.2 Experimental Procedures

### 2.2.2.1 BOBCalixC6 solubility studies

A series of solvents were prepared from five different pristine nonwashed solutions of Cs-7SB modifier in Isopar<sup>®</sup> L (0.5, 0.65, 0.75, 0.85, and 1.0 M) containing 1 mM TOA as follows. Three and one-half grams of BOBCalixC6 (Lot 000714 HMKC-0004) was dissolved in 50 mL of modifier solution in Isopar<sup>®</sup> L by applying sonication and heating to about 50 °C, cooling to room temperature, and then seeding with about 2 mg of recrystallized BOBCalixC6. BOBCalixC6 was used as received from IBC Advanced Technologies, Inc. The modifier solutions in Isopar<sup>®</sup> L were washed following the standard washing protocol. The samples were then shaken and divided into six samples of equal volume. Samples in duplicate were placed in a water bath at 15 °C, an air box at 25 °C, and an incubator at 35 °C. Agitation was effected by shaking in the water bath and wheel rotation in the air box and incubator. The initial concentration of BOBCalixC6 in each sample was 59 mM. After a given time interval, the samples were allowed to settle for 30 to 60 min, whereupon an aliquot of the supernatant solution was withdrawn, filtered through No. 40 filter paper, diluted with chloroform, and submitted for high-performance liquid chromatography (HPLC) analysis. Samples archived from the solubility study initiated approximately 1 year ago [11] were also analyzed. A new calibration curve was prepared with fresh calixarene solutions for each analysis series.

### 2.2.2.2 Extraction, scrub and strip protocol

Extraction, scrub, and strip (ESS) tests were performed on all of the samples listed in Table 2. The experiments were conducted following the protocol defined in Ref. 11 using organic:aqueous (O:A) volume ratios of 1:3 on extraction and 5:1 on scrubs and strips. An extra scrub step was added to the previous protocol [11] to more realistically approximate the flowsheet. It should be noted that the solvent weakly extracts sodium and potassium, and the second scrub step more completely removes these metals from the solvent prior to stripping. With only one scrub, the first strip step is expected to exhibit slightly higher values of  $D_{Cs}$ , because the incomplete scrubbing of sodium and potassium results in these metal nitrates reporting to the aqueous phase of the first strip step, thereby increasing the aqueous-phase nitrate concentration. The data validating the modified ESS protocol are given in Table 3. The data confirm that addition of the second scrub improves stripping performance as expected. The  $D_{Cs}$  values are slightly dependent on the O:A ratios employed, with better performance occurring when the strip O:A ratio is lower. All stripping  $D_{Cs}$  values converge to the same value upon successive stripping. In the solvent-optimization tests, an increase in modifier concentration is expected to increase sodium and potassium extraction [11]. However, the consequent negative impact on stripping is expected to be essentially eliminated by the second scrub and thus appropriately rendered an insignificant factor in solvent selection.

### 2.2.2.3 Third-phase determination

Third-phase formation experiments involved the 10 solvents containing 1 mM of TOA and three different simulants: baseline simulant ( $[Cs^+] = 0.14$  mM,  $[K^+] = 0.02$  M), high-potassium simulant ( $[Cs^+] = 0.14$  mM,  $[K^+] = 0.05$  M); and high-potassium, high-cesium simulant ( $[Cs^+] = 0.44$  mM,  $[K^+] = 0.05$  M). These conditions encompass those that could be potentially encountered with real wastes [3]. After two repeated contacts with the simulants (O:A = 1:3) at 25 °C, the solvent samples were cooled in a water bath and shaken periodically. The presence or absence of a third phase was determined by independent visual examination by two researchers.

**Table 3. Validation data for the modified ESS protocol**

Step	Value of $D_{Cs}$ by O:A ratios <sup>a</sup>			
	1:3 (E) 5:1 (SS)	1:5 (E) 3:1 (SS)	1:3 (E) 5:1 (SS)	1:5 (E) 3:1 (SS)
Extraction	17.6	17.1	16.6	17.3
Scrub no. 1	1.55	1.57	1.56	1.57
Scrub no. 2	NA	NA	1.56	1.57
Strip no. 1	0.137	0.130	0.120	0.116
Strip no. 2	0.080	0.075	0.078	0.071
Strip no. 3	0.064	0.064	0.062	0.062
Strip no. 4	0.052	0.054	0.052	0.054

<sup>a</sup>The letter “E” denotes O:A ratio for extraction; “SS” denotes O:A ratio for scrub and strip. NA denotes “not applicable,” as the second scrub was intentionally omitted in the corresponding sequence.

### 2.2.2.4 Dispersion-number measurement

Dispersion numbers were determined under extraction, scrubbing, and stripping conditions in the presence of cesium. Prior to use, all new or previously used glassware and plastic vessels were washed by rinsing with tap water three times, rinsing with deionized water three times, rinsing with ethanol two times, and rinsing with acetone two times. The equipment was allowed to air dry or was dried with a stream of dry nitrogen or argon before use. In all tests, phase volumes proportional to the flow rates of the solvent, scrub, and strip solutions in the CSSX baseline flowsheet were placed into a 100-mL graduated Pyrex<sup>®</sup> cylinder. The position of the interface was recorded. The cylinder was capped with a ground-glass stopper, the solutions were agitated at ambient laboratory temperature for 20 s. Agitation was suspended for 10 s and then resumed for an additional 20 s. At the end of the second agitation, a stopwatch was started and the time required for the interface to return to its original position was

recorded. In these tests, the “original” position was assumed to be that within 1–2 mm of the interface prior to the agitation and when all indications of dispersed phases at the interface had disappeared. The total height of the dispersion within the cylinder was measured. Each determination was repeated three times. Dimensionless dispersion numbers were calculated according to the expression [24]:

$$N_{Di} = \frac{1}{t_b} \sqrt{\frac{z}{g_c}} \quad (1)$$

where  $t_b$  is the break time in seconds,  $z$  is the dispersion band height in centimeters, and  $g_c$  is the gravitational force of 981 cm/s<sup>2</sup>.

#### 2.2.2.5 Density

The solvent densities were measured using procedures based on ASTM D891 [25] and ASTM D1429, [25] using new 50-mL class A borosilicate glass volumetric flasks with ground-glass stoppers. Calibration of the volumetric flasks for density measurements was performed based on ASTM E542 [27]. A Mettler AE260 analytical balance (S/N J19097) capable of measuring to 0.1 mg was used to weigh the flasks. National Institute of Standards and Technology (NIST)–based test weights were used to check the balance calibration. A thermometer accurate to 0.1 °C (LaPine 398-12-53) was used to measure the temperature of the liquid in the flasks. The flasks were cleaned and dried before each use as described above, using tap water, deionized water, ethanol, and acetone, followed by drying with argon gas. Each flask was filled using a 10-mL transfer pipette to just below the line and then adjusted to the line with a small transfer pipette. The actual volume of each flask was calculated from the weight of the water contained.

#### 2.2.2.6 Viscosity

The viscosities of each of the nine candidate solvents and the previous baseline solvent were measured at 20, 25, 30, 35, and 40 °C using procedures adapted from ASTM D2196 [28] and the Brookfield viscometer operating instructions [29]. The determinations were made using a Brookfield rotational viscometer model LVTDV-II, serial number D15869, with a UL adapter. The water jacket on the UL adapter was heated and cooled by a VWR model 13270-615 circulation bath, with 190-Ws cooling, and operated at a coolant recirculation rate of 2 L/min. It contained a 50/50 mixture of ethylene glycol and water, which was circulated by the water bath circulation pump. The thermometer used, the LaPine 398-12-53, was immersed in the water bath for the temperature measurement. (There is no room in the UL adapter for a thermometer.) The spindle speed was set to give a torque percent reading in the middle or upper portion of the scale. The UL adapter (a large-diameter spindle in a cylindrical container just slightly larger in diameter than the spindle) is used for measuring low-viscosity liquids (liquids with viscosities between 1 and 20 cP). The UL adapter with spindle holds 16 mL of sample for measurement.

Each test was begun by adding the test solvent to the UL adapter, installing it on the viscometer, starting the spindle rotation at 60 rpm, and then setting the temperature bath to 20 °C. After the temperature had stabilized for several minutes, the viscosity of the sample was measured. The temperature bath was then adjusted to the next temperature and the system temperature allowed to stabilize before the next reading was taken.

### 2.2.2.7 Surface tension and interfacial tension

The surface tension of each of the nine candidate solvents, the previous baseline solvent, simulant, strip solution, and scrub solution were measured at ~25 °C using a CSC Du Nouy tensiometer (serial no. 013457) with a 6-cm-circumference ring. The experimental procedures were adapted from ASTM D971 [30] and ASTM D1331 [31]. The tensiometer was calibrated against known weights and its zero point adjusted according to the procedure of the manufacturer. Interfacial tension was determined by measuring the force necessary to detach a planar ring of platinum wire from the surface of the liquid of higher surface tension, that is, upward from the aqueous-organic interface. To calculate the interfacial tension, the force so measured was corrected by an empirically determined factor that depends upon the force applied, the densities of both organic and aqueous layers, and the dimensions of the ring. Measurements are made under rigidly standardized nonequilibrium conditions in which the measurement is completed within 60 s after formation of the interface. The surface tension of deionized water was measured to determine that the apparatus was functioning correctly. A value of 71–73 dyn/cm must be obtained; the literature value at 25 °C is 72.0 dyn/cm [32].

A Teflon<sup>®</sup> sample container having a minimum diameter of 45 mm was used. The container was cleaned as described above (with tap water, deionized water, ethanol, and acetone) between each solvent/aqueous determination. The ring was then flamed in a blue gas flame, using spinning to obtain rapid, uniform heating. The ring should barely glow orange and should be heated for no more than 5 s.

Interfacial tension measurements were made by carefully placing a layer of the organic on the surface of the aqueous layer (the aqueous layer was placed in the container first and the ring submerged in this layer) until a depth of at least 10 mm was reached using a pipette. This procedure was used to ensure that minimum mixing occurred and that the organic did not touch the surface of the submerged ring. The organic-aqueous interface was allowed to age for  $30 \pm 1$  s after the last of the organic had been layered onto the water. The platform was lowered and the value at rupture recorded. The measurement was timed so that, as nearly as possible, 30 s were required to draw the ring through the interface. The entire operation, from the time of pouring the organic onto the aqueous until the interface ruptured, was completed in about  $60 \pm 10$  s. Each solvent was tested in duplicate, with the cup and the ring cleaned between the two readings.

The interfacial tension of the sample was calculated by means of the following equation:

$$\text{Interfacial tension, dyn/cm} = P_{\text{interface}} \square F \quad (2)$$

where  $P_{\text{interface}}$  is the scale reading when the film ruptures (in dynes per centimeter) and  $F$  is the factor converting the scale reading (in dynes per centimeter) to interfacial tension, as obtained from Eq. (3). The value of the diameter ratio,  $R/r$ , for the ring, as specified by the manufacturer, is 53.6. The value of  $F$  is obtained as follows:

$$F = 0.7250 + [0.01452P_{\text{interface}}/C^2 (\rho_{\text{aq}} - \rho_{\text{org}}) + 0.04534 - 1.679/(r_{\text{ring}}/r_{\text{wire}})]^{1/2} \quad (3)$$


where  $C$  is the circumference of the ring (5.992 cm),  $\rho_{\text{aq}}$  is the density of the aqueous layer at 25 °C, in grams per milliliter;  $\rho_{\text{org}}$  is the density of the organic layer for interfacial testing at 25 °C, in grams per milliliter;  $r_{\text{ring}}$  is the radius of the ring, in centimeters; and  $r_{\text{wire}}$  is the radius of the wire of the ring, in centimeters.

## 2.3 EXPERIMENTAL RESULTS


### 2.3.1 BOBCalixC6 Solubility

The data on the BOBCalixC6 are a combination of information acquired from the experiments conducted in the latter portion of FY 2001 (see Experimental Section) and from the previous experiments [11]. This summary of the experimental results is necessary because of the long periods of time required for the BOBCalixC6 to achieve the solubility equilibrium condition. Table 4 summarizes the data obtained from the most recent solubility study.


The time-trend analysis of the data shows that after eight weeks, solubility equilibrium has not been achieved. Nevertheless, the data imply the supersaturation of the baseline solvent. After 36 weeks, the change in the calixarene content is fairly minor, as can be seen in Figs. 1–3, where the temperatures were chosen to represent respectively the minimum, medium, and maximum temperatures encountered in the process. (Note that the results after 36 weeks were not available when the composition of the optimized solvent was chosen [21]).

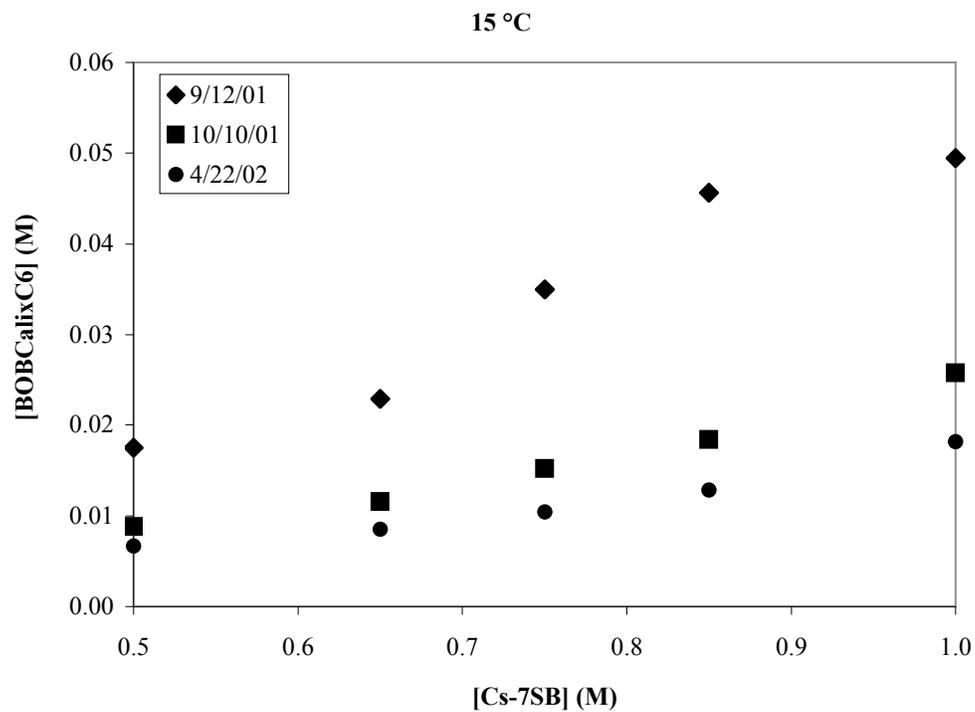

**Fig. 1. BOBCalixC6 solubility tests at 15 °C.**

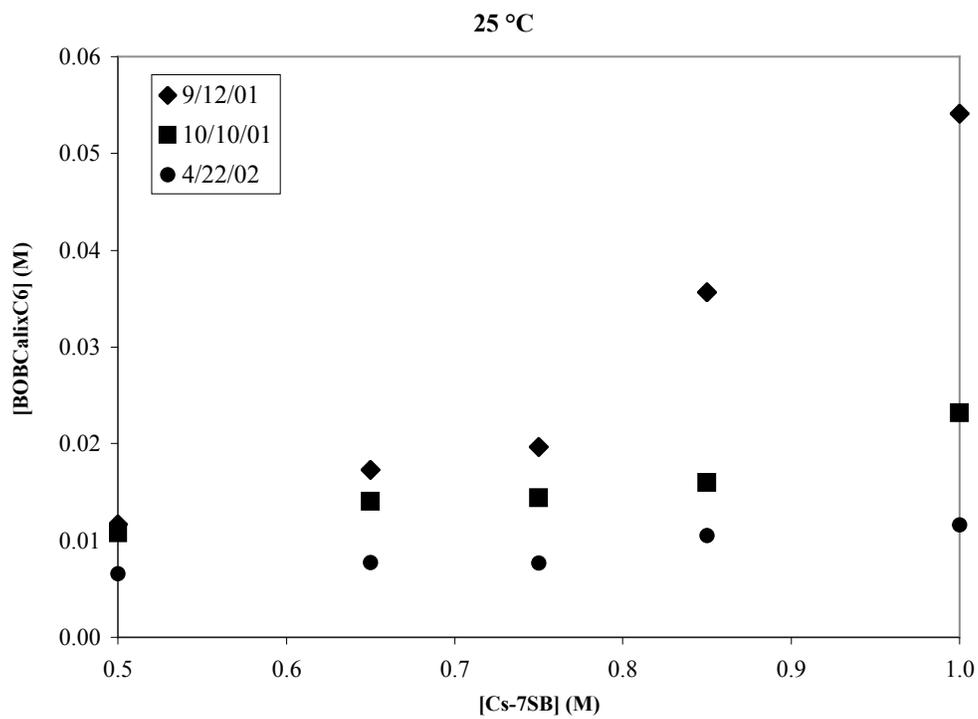

**Fig. 2. BOBCalixC6 solubility tests at 25 °C.**

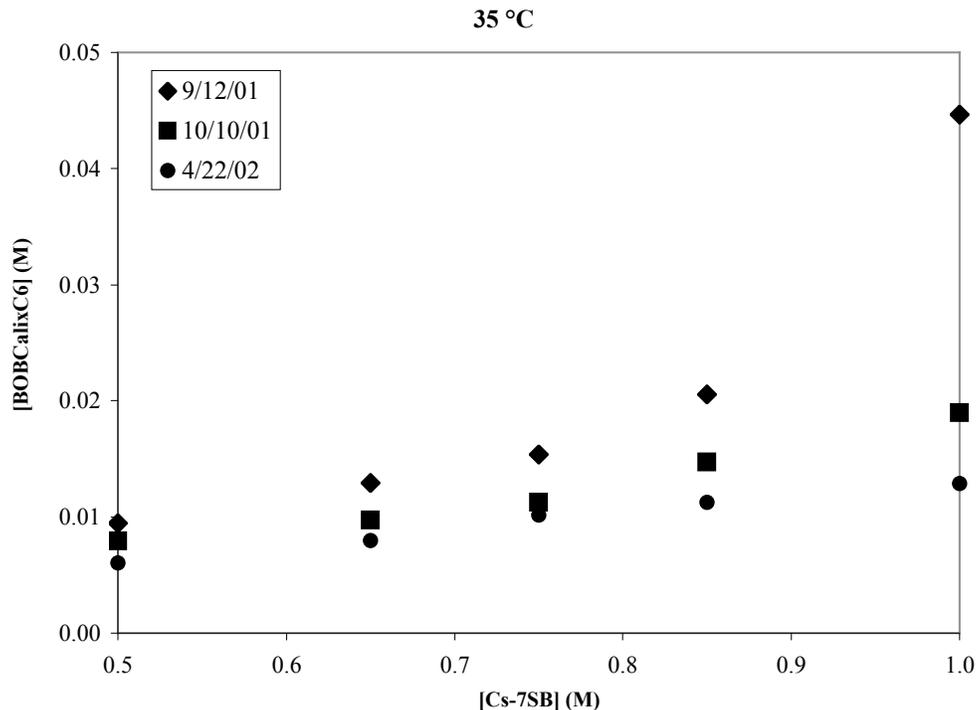

**Fig. 3. BOBCalixC6 solubility tests at 35 °C.**


The experiment carried out at 35 °C indicates that the solubility of calixarene in a solvent containing the chosen concentration of modifier for the optimized solvent (0.75 M) varied minimally in 6 months, and the concentration of soluble calixarene is still greater than 7 mM. For the two other temperatures, the gap between the measurements performed in October 2001 and in April 2002 is larger, but BOBCalixC6 is still at a concentration greater than 7 mM in both cases for a concentration of modifier of 0.75 M.

A conservative estimate of the lower bound of the BOBCalixC6 solubility at 25 °C was obtained by reanalysis of samples from the solubility study that was initiated approximately 1 year ago [11]. These samples had been stored at the original experimental temperatures with intermittent agitation. Selected results are summarized in Fig. 4. As indicated in the legend, data are shown for both as-received and recrystallized BOBCalixC6 and for equilibrium approached from the direction of both dissolution (solid BOBCalixC6 present at start) and precipitation (starting with supersaturated BOBCalixC6 upon sonication and then seeding). In each case, no TOA or water is present in the solvent; that is, solid BOBCalixC6 is suspended in Cs-7SB at the indicated concentration in Isopar<sup>®</sup> L only. A tabulation of the data after 1 year, including systems containing TOA and water, is given in Table 5. Except for the single data point at 0.25 M Cs-7SB, which shows a deviation of  $\pm 26\%$ , the average analytical deviation among duplicate samples is  $\pm 3.5\%$ . The data show that TOA and water have little or no effect on BOBCalixC6 solubility.

**Table 4. BOBCalixC6 solubility data from FY 2001 study<sup>a</sup>**

[Cs-7SB] (M)	[BOBCalixC6] (mM)									
	Initial	15 °C			25 °C			35 °C		
		4 wks	8 wks	36 wks	4 wks	8 wks	36 wks	4 wks	8 wks	36 wks
0.50	59	17.5	8.80	6.70	11.7	10.7	6.59	9.50	7.94	6.04
0.65	59	22.9	11.5	8.54	17.3	14.0	7.72	12.9	9.72	7.98
0.75	59	35.0	15.2	10.4	19.7	13.1	7.69	15.4	11.2	10.1
0.85	59	45.6	18.3	12.9	35.7	15.9	10.5	20.5	14.7	11.3
1.0	59	49.5	25.7	18.1	54.1	23.1	11.6	44.7	19.0	12.9

<sup>a</sup>Each value is the average of an analysis of each of duplicate solubility samples.

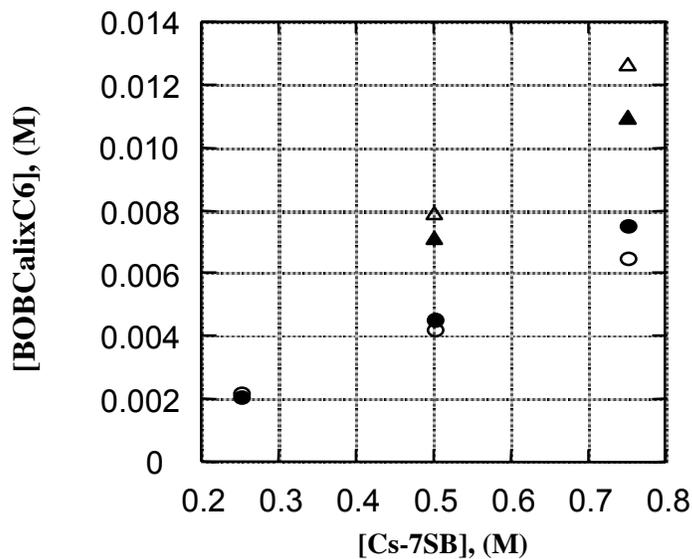

- Recrystallized BOBCalixC6, dissolution, equilibrated for 52 days
- Recrystallized BOBCalixC6, dissolution, equilibrated for 410 days
- △ As-received BOBCalixC6, precipitation, equilibrated for 38 days
- ▲ As-received BOBCalixC6, precipitation, equilibrated for 395 days

**Fig. 4. Comparison of BOBCalixC6 solubility data.** The circles correspond to solubility tests performed by dissolution with recrystallized calixarene; the triangles correspond to solubility tests performed by precipitation with calixarene used as-received.

Conservatively, the lower bound of the BOBCalixC6 thermodynamic solubility corresponds to the recrystallized BOBCalixC6 that had been dissolving over the course of 13 months. At 0.75 M Cs-7SB, the lower bound at 25 °C is 7.55 mM. Although the solubility of BOBCalixC6 generally increases with increasing Cs-7SB concentration, a gap exists between the data for the recrystallized BOBCalixC6 that is dissolving and the as-received BOBCalixC6 that is precipitating.

**Table 5. BOBCalixC6 solubility data from FY 2000 study<sup>a</sup>**

Sample no.	[Cs-7SB] (M)	[TOA] (mM)	Solvent washed?	Dissolution method	[BOBCalixC6] purification	[BOBCalixC6] (mM)	[BOBCalixC6] average (mM)
					Recrystallized		
5-A	0.25	0	No	Dissolve		2.62	
5-B	0.25	0	No	Dissolve	Recrystallized	1.55	2.08
6-A	0.50	0	No	Dissolve	Recrystallized	4.31	
6-B	0.50	0	No	Dissolve	Recrystallized	4.76	4.54
7-A	0.75	0	No	Dissolve	Recrystallized	6.98	
7-B	0.75	0	No	Dissolve	Recrystallized	8.12	7.55
8-A	0.50	1	No	Dissolve	Recrystallized	4.38	
8-B	0.50	1	No	Dissolve	Recrystallized	4.48	4.43
9-A	0.50	1	Yes	Dissolve	Recrystallized	4.26	
9-B	0.50	1	Yes	Dissolve	Recrystallized	4.64	4.45
10-A	0.50	1	No	Precipitate	Recrystallized	6.18	
10-B	0.50	1	No	Precipitate	Recrystallized	6.68	6.43
11-A	0.50	0	No	Precipitate	As Received	7.26	
11-B	0.50	0	No	Precipitate	As Received	7.05	7.15
12-A	0.75	0	No	Precipitate	As Received	11.1	
12-B	0.75	0	No	Precipitate	As Received	10.8	10.95
13-A	0.50	0	Yes	Precipitate	As Received	5.11	
13-B	0.50	0	Yes	Precipitate	As Received		

<sup>a</sup>HPLC analysis of samples held at 25 °C for approximately 13 months.

From the data shown in Fig. 1, one may conclude that the true solubility of BOBCalixC6 in Isopar<sup>®</sup> that contains only Cs-7SB at 25 °C lies within this gap. Both sets of data show a very slow convergence over the course of the past year. The increases in solubility upon dissolution were 8.4% and 16.5% for 0.5 and 0.75 M Cs-7SB, respectively. The comparable decreases upon precipitation were 9.7% and 13.4% for 0.5 and 0.75 M Cs-7SB, respectively. At this time, it is impossible to determine conclusively whether the upper set differs from the lower set because of the purity of BOBCalixC6 or because of the direction from which equilibrium is being approached. However, we believe that the latter cause is more probable, because the high concentration of Cs-7SB likely negates any effects on solubility of minor impurities in the as-received BOBCalixC6. As discussed earlier [11], these impurities apparently have an effect on the rate of dissolution of BOBCalixC6. Whereas recrystallized BOBCalixC6 can be dissolved very slowly (even with prolonged sonication and warming), the as-received material, nominally 97% pure, quickly dissolves to concentrations as high as 50 mM. For this reason, it has been impractical to experimentally approach equilibrium by precipitation of recrystallized BOBCalixC6. It is clear, then, that the lower bound of 7.55 mM BOBCalixC6 at 0.75 M Cs-7SB is a conservative estimate for the BOBCalixC6 solubility. Not only is the final plateau concentration of BOBCalixC6 likely to be higher, but the most realistic condition in a plant environment is for equilibrium to be approached by precipitation of the as-received material.

### **2.3.2 Cesium Distribution Results**

The cesium distribution data obtained with the ESS tests are summarized in Tables 6 and 7. The data in Table 6 are for the series of test samples containing 1 mM TOA, and the results in Table 7 are for the series of test samples containing varying amounts of TOA and modifier with fixed BOBCalixC6 concentration.

**Table 6. ESS results obtained with constant TOA concentration<sup>a</sup>**

[BOBCalixC6] (mM)	[Cs-7SB] (M)	$D_{Cs}$						
		Extract	Scrub # 1	Scrub # 2	Strip # 1	Strip # 2	Strip # 3	Strip # 4
10	0.50	17.2	1.52	1.52	0.114	0.070	0.055	0.051
10	0.65	19.6	1.75	1.79	0.136	0.084	0.066	0.057
10	0.75	20.7	1.91	1.91	0.152	0.092	0.072	0.062
8	0.65	15.4	1.38	1.44	0.109	0.066	0.053	0.045
8	0.75	16.1	1.52	1.54	0.120	0.075	0.056	0.050
8	0.85	17.2	1.68	1.66	0.134	0.077	0.062	0.053
8	1.00	17.7	1.87	1.78	0.145	0.086	0.069	0.060
6	0.75	12.2	1.12	1.16	0.089	0.051	0.042	0.036
6	0.85	12.3	1.23	1.25	0.095	0.055	0.044	0.040
6	1.00	13.6	1.39	1.39	0.112	0.065	0.051	0.046

<sup>a</sup>Temperature = 25 °C. [TOA] = 1 mM.

Interest in increasing the TOA concentration is twofold. First, as the TOA concentration increases, the CSSX process becomes more resistant to anionic impurities. Second, thermal [11] and radiolytic [12,14] stability test results showed that TOA is the solvent component most susceptible to decomposition. However, the concentration cannot be increased excessively, because the organic-phase concentration of nitrate in the scrub stage will increase by the protonation of TOA. This extracted nitrate will be partially released in the first strip stage, causing the value of  $D_{Cs}$  for the first strip stage to increase, which could ultimately limit stripping efficiency. Assuming an O:A ratio of 5:1 in the strip section, stripping becomes ineffective (because of “pinching”) when the first strip  $D_{Cs}$  value becomes equal to or greater than 0.2. The data show that stripping will not be so affected at TOA concentrations as high as 10 mM.

The results show that values of  $D_{Cs}$  for the two scrubs decrease as the concentration of TOA increases. This behavior is expected, because more nitrate is extracted, which both decreases the aqueous nitrate concentration and decreases the effective concentration of modifier, as more modifier molecules are tied up in solvating the nitrate. The  $D_{Cs}$  values in the initial strip stages also increase. Again, this result is expected, because greater nitrate extraction in scrubbing implies greater release of nitrate from the solvent into the strip aqueous phase. As a result of this higher nitrate concentration in the first strip stage and resultant higher  $D_{Cs}$ , more stages are required for the  $D_{Cs}$  value to converge to the limiting value. This limiting value should, in principle, be the same for all TOA concentrations. It also appears that the extraction  $D_{Cs}$  values decrease with increasing TOA concentrations. Assuming this slight decrease is real, it may reflect more modifier molecules being tied up in solvating the TOA.

**Table 7. ESS results obtained with two selected solvents with variable TOA concentrations<sup>a</sup>**

[TOA], (mM)	$D_{Cs}$						
	Extract	Scrub no. 1	Scrub no. 2	Strip no. 1	Strip no. 2	Strip no. 3	Strip no. 4
<b>[BOBCalixC6] = 8 mM, [Cs-7SB] = 0.65 M</b>							
1	15.4	1.38	1.44	0.109	0.066	0.053	0.045
3	14.9	1.08	1.39	0.116	0.081	0.069	0.056
10	14.7	1.00	0.76	0.134	0.104	0.090	0.076
<b>[BOBCalixC6] = 8 mM, [Cs-7SB] = 0.75 M</b>							
1	16.4	1.54	1.55	0.121	0.073	0.059	0.052
3	15.5	1.26	1.49	0.124	0.083	0.075	0.059
10	15.2	1.20	0.70	0.137	0.101	0.091	0.078

<sup>a</sup>Temperature = 25 °C.

Based on the cesium distribution ratio ( $D_{Cs}$ ) data contained in Tables 6 and 7, all of the tested solvent compositions meet the  $D_{Cs}$  acceptance criterion. The  $D_{Cs}$  values in Tables 6 and 7, when analyzed as  $\log D_{Cs}$  versus  $\log(\text{BOBCalixC6 concentration})$  and  $\log D_{Cs}$  versus  $\log(\text{Cs-7SB modifier concentration})$ , are linear with slopes approximately equal to one. Using these relationships, a simple set of equations can be used to predict the  $D_{Cs}$  values as a function of the BOBCalixC6 and Cs-7SB modifier concentrations. The results of the prediction for BOBCalixC6 and modifier concentrations about the recommended solvent composition are given in Appendix A, Table A.1.

### 2.3.3 Flowsheet Robustness

A series of Spreadsheet Algorithms for Stagewise Solvent Extraction (SASSE) [33] calculations were performed using the  $D_{Cs}$  values contained in Tables 6 and 7. The assumptions used in these calculations include the following: (1) the extraction and scrub  $D_{Cs}$  values are proportional to the concentration of free BOBCalixC6 in the organic phase; (2) the BOBCalixC6 is loaded with only one cesium ion; (3) the  $D_{Cs}$  value for the strip is proportional to the concentration of nitrate in the aqueous phase; (4) the total cesium concentration of the waste feed is 0.00014 M; (5) the temperature of the entire contactor cascade is 25 °C; (6) the stage efficiency is 80%; (7) 0.1% other-phase carryover occurs between stages; (8) there are 15 extraction stages, 2 scrub stages, and 15 strip stages; (9) there are 20.1 gal/min of waste feed and 1.33 gal/min of strip feed, and (10) the O:A in the scrub section is 5.0.

The results of the calculations are given in Table 8. The robustness number (Rb) is defined as the ratio of the decontamination factor for a given set of flowsheet conditions to the process-required bounding decontamination factor of 40,000. The baseline flowsheet specifies a solvent flow rate of

6.6 gal/min [3]. The maximum robustness was obtained by varying the solvent flow rate, which is shown in the fourth column of Table 8.

All of the solvent compositions tested meet the bounding criterion for robustness at the baseline solvent flow rate; however, the two solvent compositions containing 10 mM TOA do not meet the “goal” (i.e., the target criterion) for robustness. When the solvent flow rate is adjusted to achieve the maximum robustness, all of the solvent compositions meet the goal for robustness.

**Table 8. Calculated robustness for various CSSX solvent compositions**

Solvent identification <sup>a</sup>	Rb at 6.6 gal/min waste feed	Rb <sub>max</sub>	Optimum flow rate (Flow rate at Rb <sub>max</sub> , gal/min)
Previous baseline	21.9	25.3	6.1
B001107-3-1	11.9	26.4	5.3
B001107-3-2	25.0	25.3	6.7
B001107-3-3	6.6	23.6	4.9
B001107-3-4	19.3	20.7	6.2
B001107-3-5	8.8	24.3	8.5
B001107-3-6	15.7	21.2	5.8
B001107-3-7	9.1	17.8	8.0
B001107-3-8	7.3	15.4	5.4
B001107-3-9	14.3	15.6	7.0
B001107-3-2A	8.8	10.1	6.1
B001107-3-2B	1.1	3.0	5.3
B001107-3-4C	6.9	9.7	5.8
B001107-3-4D	1.0	3.2	5.1

<sup>a</sup>See Table 2 for the composition of the specified solvent.

It should be noted that the SASSE calculations are considered to be conservative, since they assume a constant process temperature and a stage efficiency of 80%. In the actual process, the extraction section will be kept cooler than the strip section, thereby improving the process robustness. For example, if the extraction section were at 25 °C, the scrub section at 29 °C, and the strip section at 33 °C, the robustness for the baseline solvent at a flow rate of 6.6 gal/min increases from 21.9 to 80.7. Thus, process robustness can be increased substantially by means of temperature control.

At the time the calculations were performed, it was believed that while a stage efficiency of 80% was assumed for the centrifugal contactor, the expected efficiency will be greater than 90% [34,35]. Assuming a 90% stage efficiency in the SASSE calculations at 25 °C, the robustness for the baseline

solvent at a flow rate of 6.6 gal/min would increase from 21.9 to 599. Higher stage efficiency, which can be expected with the plant-scale contactors, would increase process robustness. Since then, experiments carried out at INEEL with the baseline solvent in 5.5 cm contactors (ORNL design) showed a lower efficiency (72–75% on extraction, 36–60% on stripping). However, it is expected that process chemistry was not the cause, that an optimized contactor design could solve the low efficiency issue and that the assumptions considered for the SASSE calculations were still valid [36].

### 2.3.4 Third-Phase Formation

One of the major criteria the solvent must meet is the absence of third-phase formation for the expected maximum loading of the solvent at 15 °C, which occurs at the high cesium and potassium concentrations. This requirement was determined in FY 2001 at the time the process temperature range was established [3]. The results of the third-phase evaluations for solvents containing 1 mM TOA are presented in Table 9. Results of these experiments indicate that the use of any solvent containing 10 mM BOBCalixC6 is not recommended at a Cs-7SB modifier concentration less than 0.75 M.

**Table 9. Temperature range for third-phase appearance**

[BOBCalixC6] (mM)	[Cs-7SB] (M)	Temperature range ( °C)		
		Full SRS simulant	High-potassium simulant	High-cesium and high- potassium simulant
10	0.50	15.0–16.5	17.5–20.0	17.5–20.0
10	0.65	12.0–13.0	15.0–16.5	15.0–16.5
10	0.75	10.0–11.0	12.0–13.0	12.0–13.0
8	0.65	10.0–11.0	12.0–13.0	12.0–13.0
8	0.75	8.5–9.0	10.0–11.0	10.0–11.0
8	0.85	7.5–8.0	8.5–9.0	8.5–9.0
8	1.00	6.5–7.0	6.5–7.0	6.5–7.0
6	0.75	6.5–7.0	8.0–8.5	8.5–9.0
6	0.85	5.0–6.5	7.0–7.5	7.0–7.5
6	1.00	F <sup>a</sup>	F <sup>a</sup>	F <sup>a</sup>

<sup>a</sup>The letter “F” denotes that the solvent did not exhibit a third-phase at 5 °C. However, because of the high concentration of modifier, the solvent viscosity had increased significantly at that temperature, making observation of a third-phase difficult.

### 2.3.5 Solvent Dispersion Numbers


The results for the dispersion-number determinations are given in Table 10 and shown graphically in Fig. 5. The subset of the solvent test samples contained 1 mM TOA. The data for the baseline solvent are taken from earlier testing [34]. The results show that all nine compositions meet the dispersion-number criterion for extraction, scrub, and strip conditions (cf. Table 1).

Dispersion-number determinations for a selected subset of the samples against 10-mM NaOH wash solutions are shown in Fig. 6. None of the solvent samples met the NaOH solvent-wash solution criterion. The 10-mM NaOH concentration was used during the FY 2001 flowsheet tests at Argonne National Laboratory [16], which used simulant as the feed, and tests at Savannah River Technology Center [17], which used real waste as the feed. During these tests, minor emulsion formation was observed. Solvent samples B001107-3-4 and B001107-3-5 were determined to have the most desirable characteristics when compared against all of the selection criteria. These two solvents were selected for dispersion-number determinations as a function of NaOH concentrations. The results of these tests are given in Table 11 and shown graphically in Fig. 7. When the NaOH concentration was 300 mM, these two solvent compositions met the dispersion-number criterion for solvent washing.


**Table 10. Dispersion numbers for extraction, scrub, and stripping of CSSX solvents**

Solvent description <sup>a</sup>	Dispersion number			
	Simulant/solvent	Scrub/solvent	Strip/solvent	Wash/solvent 0.01 M NaOH (O:A:1)
Previous baseline	0.00149	0.00096	0.00115	–
B001107-3-1	0.00075	0.00102	0.00091	–
B001107-3-2	0.00056	0.00070	0.00078	0.00022
B001107-3-3	0.00102	0.00052	0.00088	–
B001107-3-4	0.00102	0.00053	0.00094	0.00034
B001107-3-5	0.00118	0.00050	0.00088	0.00024
B001107-3-6	0.00105	0.00059	0.00075	0.00016
B001107-3-7	0.00125	0.00058	0.00085	0.00016
B001107-3-8	0.00120	0.00062	0.00054	–
B001107-3-9	0.00141	0.00041	0.00051	–

<sup>a</sup>See Table 2 for the composition of the specified solvent.

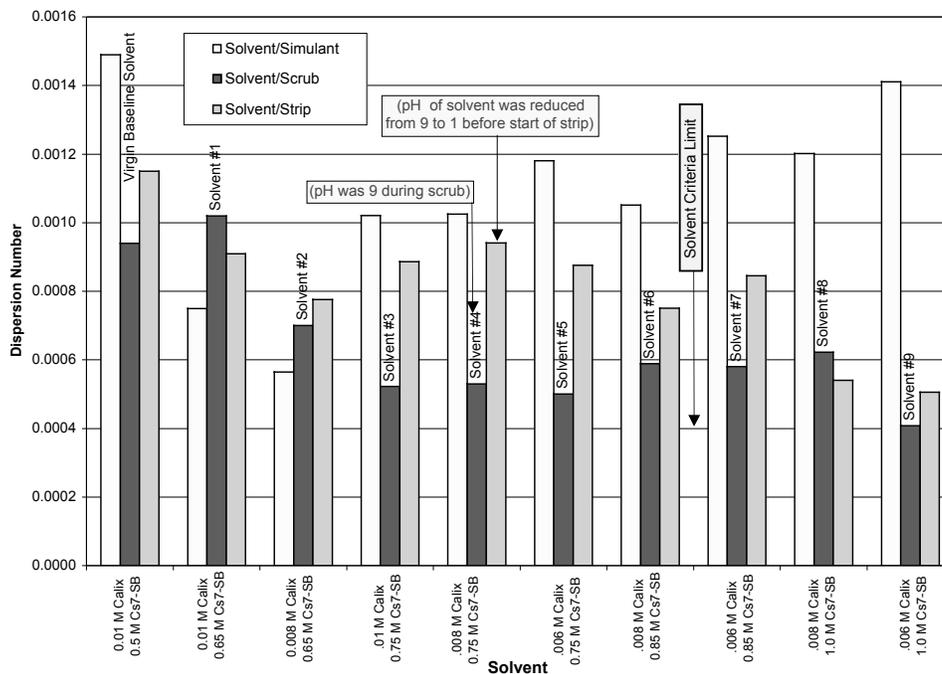

**Fig. 5. CSSX solvent dispersion numbers for extraction, scrub, and strip conditions at baseline O:A ratios.**

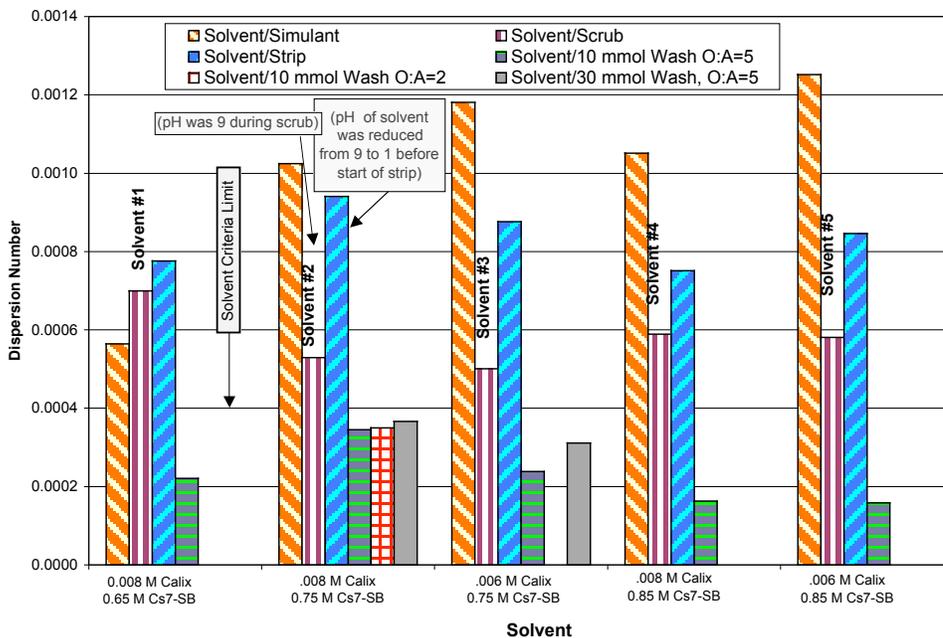


**Fig. 6. CSSX solvent dispersion numbers for solvent wash with dilute NaOH.**

**Table 11. Dispersion numbers for washing of CSSX solvents B001107-3-4 and B001107-3-5**

Solvent descriptor <sup>a</sup>	Solvent/wash dispersion number			
	0.01 M NaOH wash	0.03 M NaOH wash	0.1 M NaOH wash	0.3 M NaOH wash
B001107-3-4	0.00035	0.00037	0.00037	0.00049
B001107-3-5	0.00024	0.00031	0.00024	0.00045

<sup>a</sup>See Table 2 for the composition of the specified solvent.

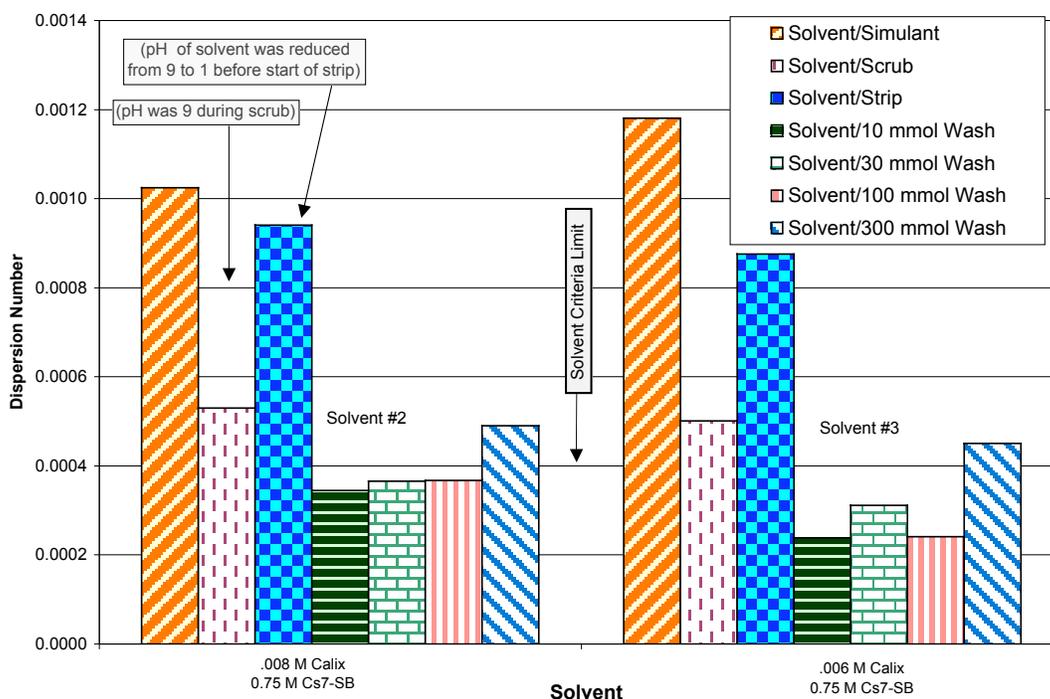

**Fig. 7. CSSX solvent dispersion numbers for solvent washing as a function of NaOH concentration.**

### 2.3.6 Solvent Density

The results of the density determinations are presented in Table 12. As expected, solvent density is primarily dependent on the modifier concentration. The relationship between density and modifier concentration is shown in Fig. 8. All the solvent samples that were tested met the bounding criterion for density (cf. Table 1); however, the solvent samples with modifier concentrations equal to or greater than 0.85 M did not meet the goal for density.


**Table 12. Solvent-density determinations**

Solvent identification <sup>a</sup>	Mass of solvent (g)	Density <sup>b</sup> (g/cm <sup>3</sup> )	[Calix] (M)	[Modifier] (M)	Corrected volume (mL)	Mass of water (g)	Specific gravity	50-mL vol. flask
Baseline <sup>c</sup>		0.810						
B001107-3-1	41.9085	0.8395	0.010	0.65	49.9202	49.7819	0.99723	1
B001107-3-2	41.9230	0.8395	0.008	0.65	49.9362	49.7979	0.99723	2
B001107-3-3	42.5920	0.8531	0.010	0.75	49.9242	49.7859	0.99723	3
B001107-3-4	42.5149	0.8525	0.008	0.75	49.8703	49.7322	0.99723	5
B001107-3-5	42.4714	0.8516	0.006	0.75	49.8703	49.7322	0.99723	5
B001107-3-6	43.0887	0.8644	0.008	0.85	49.8480	49.7099	0.99723	6
B001107-3-7	43.1036	0.8632	0.006	0.85	49.9362	49.7979	0.99723	2
B001107-3-8	44.0269	0.8819	0.008	1.00	49.9242	49.7859	0.99723	3
B001107-3-9	44.6565	0.8951	0.006	1.00	49.8925	49.7543	0.99723	4

<sup>a</sup>See Table 2 for the composition of the specified solvent.


<sup>b</sup>Temperature was 25.6 °C.

<sup>c</sup>Measured previously on previous-baseline pristine solvent.

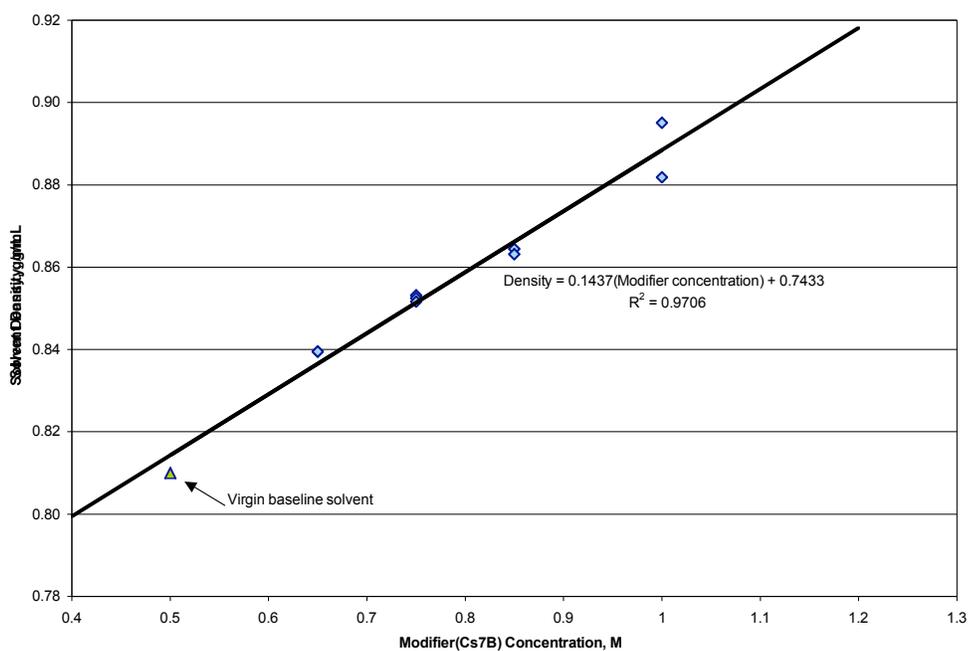
**Fig. 8. CSSX solvent density as a function of Cs-7SB modifier concentration for 25.6 °C.**

### 2.3.7 Solvent Viscosity

The results of the solvent-viscosity measurements are shown in Fig. 9, and Fig. 10 shows the shear stress as a function of temperature. The data are presented in tabular form in Table 13. The solvents with the lowest concentration of the Cs-7SB modifier have the lowest viscosity. The BOBCalixC6 concentration has only a minor effect on the viscosity decrease, because its concentration decreases at a given Cs-7SB concentration. The viscosity of all solvent samples decreases with increasing temperature, as expected for this type of liquid.

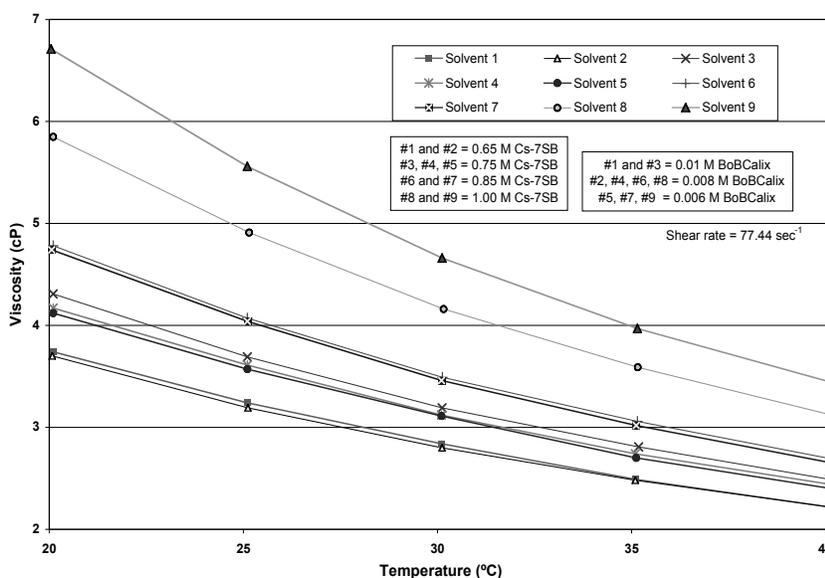

**Fig. 9. Solvent viscosity as a function of temperature.** The numbers in the legend are the test numbers from Table 2.

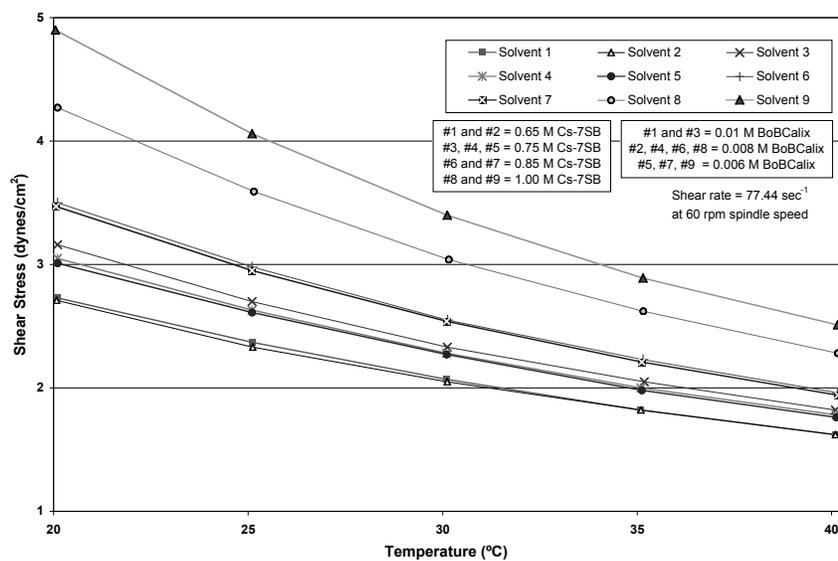

**Fig. 10. Solvent shear stress as a function of temperature.** The solvent numbers in the legend are the test numbers from Table 2.

**Table 13. Solvent-viscosity determinations<sup>a</sup>**

Solvent <sup>b</sup>	Temperature (°C)	Torque (%)	Viscosity <sup>c</sup> (cP)	Shear stress (dyn/cm <sup>2</sup> )
B001107-3-1	20.00	37.3	3.74	2.73
	25.00	32.3	3.24	2.37
	30.00	28.2	2.84	2.07
	35.00	24.9	2.49	1.82
	40.00	22.2	2.22	1.62
B001107-3-2	19.98	36.9	3.70	2.71
	25.02	31.9	3.19	2.33
	30.02	28.0	2.80	2.05
	35.00	24.8	2.48	1.82
	40.00	22.2	2.22	1.62
B001107-3-3	20.00	43.2	4.31	3.16
	25.00	36.9	3.69	2.70
	30.02	31.9	3.19	2.33
	35.08	28.0	2.81	2.05
	40.00	24.8	2.49	1.82

**Table 13 - continuation. Solvent-viscosity determinations<sup>a</sup>**

Solvent <sup>b</sup>	Temperature (°C)	Torque (%)	Viscosity <sup>c</sup> (cP)	Shear stress (dyn/cm <sup>2</sup> )
B001107-3-4	20.00	41.8	4.17	3.05
	25.00	36.0	3.61	2.63
	25.00	36.0	3.61	2.63
	30.00	31.2	3.12	2.28
	35.00	27.4	2.74	2.00
	40.02	24.4	2.44	1.78
B001107-3-5	20.00	41.3	4.12	3.01
	25.00	35.7	3.57	2.61
	30.00	31.0	3.11	2.27
	35.02	27.1	2.70	1.98
	40.02	24.0	2.40	1.76
B001107-3-6	20.00	47.8	4.78	3.50
	25.00	40.7	4.07	2.98
	30.03	34.9	3.49	2.55
	35.05	30.5	3.06	2.23
	40.05	26.8	2.69	1.96
B001107-3-7	19.96	47.3	4.74	3.47
	25.00	40.3	4.04	2.95
	30.00	34.6	3.46	2.54
	35.02	30.2	3.02	2.21
	40.06	26.6	2.65	1.94
B001107-3-8	20.00	58.5	5.85	4.27
	25.05	49.0	4.91	3.59
	30.06	41.6	4.16	3.04
	35.06	35.8	3.59	2.62
	40.06	31.3	3.12	2.28
B001107-3-9	19.95	67.1	6.71	4.90
	25.00	55.4	5.56	4.06
	30.02	46.5	4.66	3.40
	35.05	39.7	3.97	2.89
	40.05	34.3	3.44	2.51

<sup>a</sup>Brookfield LVTDV-II (Serial Number D15869) UL Adapter with heating jacket.

<sup>b</sup>See Table 2 for the composition of the specified solvent.

<sup>c</sup>Standard deviation is estimated to be  $\pm 0.1$  centipoise (cP).

### 2.3.8 Solvent Interfacial Tension

The results of the measurements are given in Tables 14–17 and are shown graphically in Figs. 11 and 12. The tables contain the data for the four series of tests. Figure 11 shows the surface tension of the solvents and also contains the surface tensions of the aqueous simulant, scrub solution, and strip solution. Figure 12 shows the interfacial tension of the solvents versus simulant, scrub, and strip solutions. The results reveal nothing unusual, and the individual solvents behave similarly with the three aqueous solutions tested.

**Table 14. Surface-tension determinations**

Solution identification <sup>a</sup>	Density (g/cm <sup>3</sup> )	Indicated surface tension (dyn/cm)		Instrument reading, average ( $P_{\text{interface}}$ )	Correction factor ( $F$ ) from Eq. 3	Actual surface tension (dyn/cm)
		Trial 1	Trial 2			
B001107-3-1	0.8395	26.9	26.8	26.9	0.8896	23.9
B001107-3-2	0.8395	26.8	26.8	26.8	0.8895	23.8
B001107-3-3	0.8531	26.8	26.7	26.8	0.8888	23.8
B001107-3-4	0.8525	26.8	26.9	26.9	0.8890	23.9
B001107-3-5	0.8516	27.0	27.1	27.1	0.8893	24.1
B001107-3-6	0.8644	27.0	26.9	27.0	0.8886	23.9
B001107-3-7	0.8632	26.9	27.0	27.0	0.8886	23.9
B001107-3-8	0.8819	27.0	27.1	27.1	0.8879	24.0
B001107-3-9	0.8951	27.1	27.0	27.1	0.8874	24.0
Strip solution	0.9974	41.0	40.0	40.5	0.8999	36.4
Scrub solution	0.9984	48.3	48.1	48.2	0.9085	43.8
Simulant	1.2536	64.6	64.8	64.7	0.9122	59.0

<sup>a</sup>See Table 2 for the composition of the specified solvent.

**Table 15. Interfacial tension versus simulant**

Solvent identification <sup>a</sup>	Density (g/cm <sup>3</sup> )	Indicated interfacial tension (dyn/cm)		Instrument reading, average ( $P_{\text{interface}}$ )	Correction factor from Eq. 3	Actual interfacial tension (dyn/cm)
		Trial 1	Trial 2			
B001107-3-1	0.8395	20.5	20.8	20.7	0.9103	18.8
B001107-3-2	0.8395	20.8	20.7	20.8	0.9106	18.9
B001107-3-3	0.8531	20.9	20.8	20.9	0.9127	19.0
B001107-3-4	0.8525	20.7	20.5	20.6	0.9119	18.8
B001107-3-5	0.8516	20.7	20.6	20.7	0.9119	18.8
B001107-3-6	0.8644	20.3	20.4	20.4	0.9129	18.6
B001107-3-7	0.8632	20.2	20.4	20.3	0.9126	18.5
B001107-3-8	0.8819	20.5	20.5	20.5	0.9160	18.8
B001107-3-9	0.8951	20.1	20.3	20.2	0.9172	18.5

<sup>a</sup>See Table 2 for the composition of the specified solvent.

**Table 16. Interfacial tension versus scrub solution**


Solvent identification <sup>a</sup>	Density (g/cm <sup>3</sup> )	Indicated interfacial tension (dyn/cm)		Instrument reading, average ( $P_{\text{interface}}$ )	Correction factor from Eq. 3	Actual interfacial tension (dyn/cm)
		Trial 1	Trial 2			
B001107-3-1	0.8395	18.6	17.5	18.1	0.9703	17.5
B001107-3-2	0.8395	16.8	16.9	16.9	0.9640	16.2
B001107-3-3	0.8531	16.5	16.6	16.6	0.9706	16.1
B001107-3-4	0.8525	16.7	16.5	16.6	0.9704	16.1
B001107-3-5	0.8516	16.6	16.5	16.6	0.9696	16.0
B001107-3-6	0.8644	16.4	16.3	16.4	0.9772	16.0
B001107-3-7	0.8632	16.1	16.1	16.1	0.9748	15.7
B001107-3-8	0.8819	16.0	16.0	16.0	0.9892	15.8
B001107-3-9	0.8951	16.0	15.8	15.9	1.0016	15.9

<sup>a</sup>See Table 2 for the composition of the specified solvent.


**Table 17. Interfacial tension versus strip solution**

Solvent identification <sup>a</sup>	Density (g/cm <sup>3</sup> )	Indicated interfacial tension (dyn/cm)		Instrument reading, average ( $P_{\text{interface}}$ )	Correction factor from Eq. 3	Actual interfacial tension (dyn/cm)
		Trial 1	Trial 2			
B001107-3-1	0.8395	16.0	16.0	16.0	0.9599	15.4
B001107-3-2	0.8395	16.0	15.9	16.0	0.9596	15.3
B001107-3-3	0.8531	15.2	15.8	15.5	0.9651	15.0
B001107-3-4	0.8525	16.0	15.8	15.9	0.9670	15.4
B001107-3-5	0.8516	15.2	15.7	15.5	0.9639	14.9
B001107-3-6	0.8644	15.7	15.6	15.7	0.9736	15.2
B001107-3-7	0.8632	15.7	15.6	15.7	0.9727	15.2
B001107-3-8	0.8819	15.6	15.8	15.7	0.9880	15.5
B001107-3-9	0.8951	16.0	15.5	15.8	1.0015	15.8

<sup>a</sup>See Table 2 for the composition of the specified solvent.

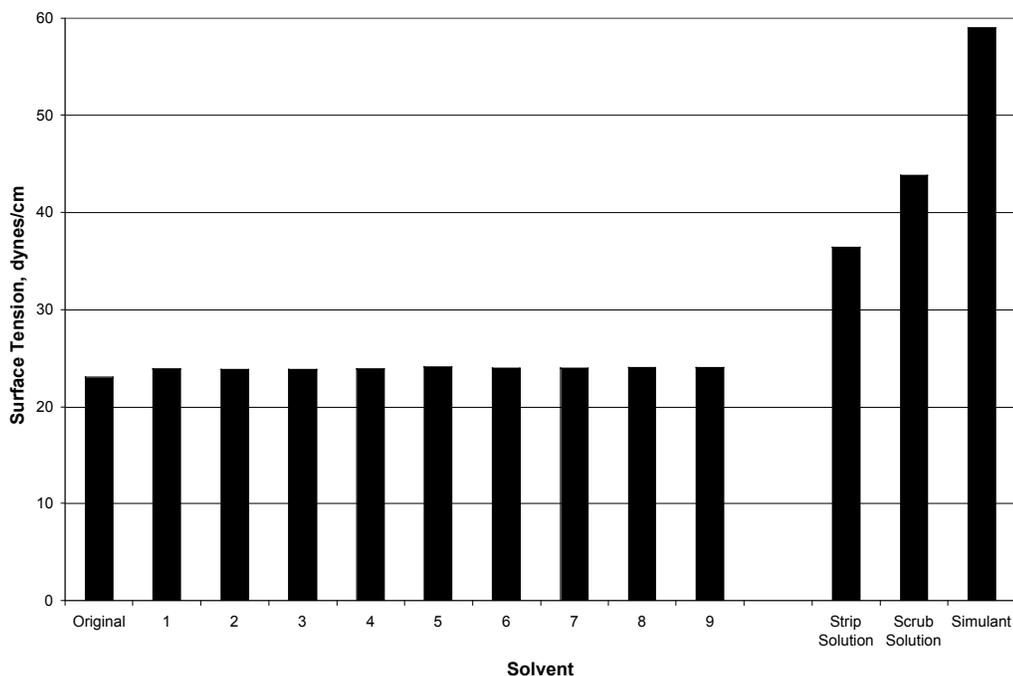

**Fig. 11. Solvent and process solution surface tension.** The numbers on the abscissa are the test numbers from Table 2.

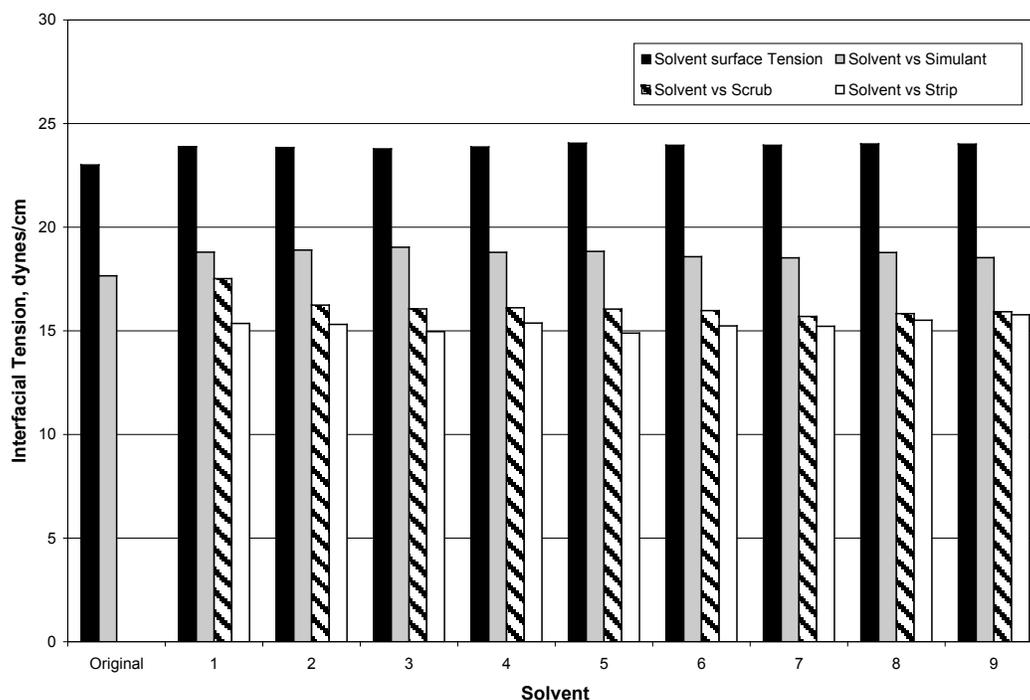

**Fig. 12. Solvent interfacial tension in extraction, scrub, and strip contacts.**  
The numbers on the abscissa are the test numbers from Table 2.

## 2.4 SOLVENT-COMPOSITION RECOMMENDATION PROCESS

The process used by the CSSX team to arrive at the solvent-composition recommendation involved several actions. First, the experimental data described in this report were distributed to the team members. Second, two conference calls were held. During the first call, the methods of data acquisition and the significance of the data relative to the selection criteria were discussed [20]. The action item from this discussion was for each participant to make a recommendation concerning the solvent composition and forward this to all of the participants. A compilation of the individual recommendations was distributed prior to the second conference call. The second call focused on the individual recommendations. Between the two calls, a technical presentation was given during the weekly TFA program status review [37]. The recommended composition was a consensus opinion of the CSSX technical team. The rationale used by the CSSX team in arriving at the recommended solvent composition is described in Ref. 20.

The primary criterion involved the selection of a composition that is thermodynamically stable with respect to the crystallization of BOBCalixC6. The fact that BOBCalixC6 has a solubility limit of 7.55 mM (for a concentration of Cs-7SB of 0.75 M) suggests that the concentration should be less than 7.5 mM to accommodate variations in solvent preparation without exceeding this limit. The solubility data also indicate that the thermodynamic solubility value for BOBCalixC6 is linked to the Cs-7SB modifier

concentration. For example, if the BOBCalixC6 concentration is 7 mM, the Cs-7SB modifier concentration should be approximately 100 times higher. The data on third-phase formation also suggest the need for a solvent composition with a BOBCalixC6 concentration of 8 mM or less and a Cs-7SB modifier concentration of at least 0.65 M. The density criterion suggests compositions with the Cs-7SB modifier concentration equal to or less than 0.85 M. Contactor throughput and phase separation are dependent on the density difference of the two phases; that is, for a given contactor size, throughput is larger and the phase separation performance generally improves as the density difference increases.

Although all of the candidate compositions met the bounding criterion for the  $D_{Cs}$  values, only the previous baseline composition meets the goal. Thus, a composition with  $D_{Cs}$  values close to the goal is preferred because it would provide the ability to process waste blends that have properties that are modestly different from those of the waste simulant composition. The flowsheet robustness calculations suggest a BOBCalixC6 concentration between 6 and 8 mM and a modifier concentration between 0.65 and 0.85 M.

The combination of BOBCalixC6 solubility,  $D_{Cs}$  values, and high flowsheet robustness, as well as the desire to have a low density, establishes the basis for the 7 mM BOBCalixC6 and 0.75 M Cs-7SB modifier concentration recommendation.

The recommended TOA concentration increase from 1 mM to 3 mM is based on three considerations. First, the flowsheet robustness calculations indicate that 10 mM TOA will require a major alteration of the solvent flow rate to achieve process performance above the bounding condition. Second, since TOA is the solvent component most susceptible to thermal and radiolytic decomposition, selecting a TOA concentration higher than the 1 mM baseline value will provide the CSSX process more resistance to the variations in anionic impurity content that are certain to be encountered with the different waste blends. Third, a TOA concentration greater than 1 mM will also provide greater flexibility in solvent preparation and process control.

The solvent dispersion numbers for all the solvent compositions tested against the waste simulant, scrub, and strip solutions met the selection criterion and consequently did not provide a means to differentiate between different solvent compositions. However, comparison of solvent dispersion numbers against the 0.01 M NaOH solvent wash solution indicates the need to re-evaluate the NaOH concentration used for solvent washing. This need was in fact addressed in contactor tests with the optimized solvent [38], showing that the 10 mM NaOH wash performs satisfactorily.

Although the viscosity, surface tension, and interfacial tension were not explicitly identified in any of the selection criteria, these physical properties can impact the dispersion number. Therefore, experimental determination of these properties was included in the study to verify that no unexpected behavior occurred. The experimental results did not reveal any such behavior.



### 3. CESIUM DISTRIBUTION BEHAVIOR

#### 3.1 INTRODUCTION

This chapter describes batch cesium distribution behavior of the optimized CSSX solvent. Since the solvent was in fact not explicitly among those tested, but rather an intermediate composition, it was first necessary to determine its extraction, scrub, and strip (ESS) behavior. Second, parameters are needed for estimation of cesium distribution ratios within the range of expected operating temperatures 15–35 °C. Finally, it was desirable to demonstrate recycle of the solvent by showing that results obtained during a second ESS cycle are within experimental error identical to those obtained with the pristine solvent. It may be recalled that  $D_{Cs}$  values on the second and subsequent cycles were found to be higher, especially on stripping, when the previous baseline solvent was employed [11]. This behavior was mainly linked to the presence of the lipophilic anion dibutylphosphate, which is readily removed upon washing the solvent with NaOH, thereby restoring normal function on subsequent cycles. Thus, it was of interest here to observe whether the increased TOA concentration of the optimized solvent suppressed this effect, with or without a NaOH wash.

#### 3.2 EXPERIMENTAL SECTION

The optimized CSSX solvent was employed (Chapter 2), as recommended previously [21,22]. The standard ESS protocol (one extraction at O:A = 0.33, two scrubs at O:A = 5, and four strips at O:A = 5) was followed. Contacts were performed in 50-mL Teflon<sup>®</sup> fluorinated ethylene propylene (FEP) tubes for the extraction step and 15-mL capacity polypropylene tubes for scrubs and strips. The contacting was carried out for 30 minutes using end-over-end rotation in a  $25.0 \pm 0.5$  °C constant-temperature air box. ESS tests at low (15 °C) and high (35 °C) temperatures were carried out respectively in a thermostated water bath and in an incubator. Agitation was effected by orbital shaking in the water bath and wheel rotation in the incubator.

#### 3.3 RESULTS AND DISCUSSION

##### 3.3.1 Extraction, Scrub, and Strip Performance

Experiments involving the determination of cesium distribution ratios with the optimized solvent were carried out in triplicate and compared to the values obtained with the previous baseline solvent. Table 18 presents the results obtained with the optimized solvent where the extraction is performed using the full simulant, the scrub using nitric acid 50 mM, and the strip using nitric acid 1 mM. The results are very close to the predicted values presented in the Table A1 in Appendix A. The values, calculated from a

double interpolation of the distribution ratios found for different concentrations of calixarene and modifier, are acceptable for process development. Additional tests were performed using strip solutions mimicking off-normal conditions in which some of the acid is neutralized.

**Table 18. Cesium batch ESS performance for previous-baseline and optimized solvents**

Conditions <sup>a</sup>	$D_{Cs}$						
	Extact	Scrub #1	Scrub #2	Strip #1	Strip #2	Strip #3	Strip #4
Standard ESS	14.05	1.14	1.35	0.115	0.076	0.117	0.053
Standard ESS	14.14	1.14	1.35	0.118	0.081	0.093	0.052
Standard ESS	14.30	1.13	1.34	0.113	0.080	0.063	0.053
NaNO <sub>3</sub> 1mM	13.53	1.13	1.35	0.119	0.125	0.078	0.066
NaNO <sub>3</sub> 1mM	14.33	1.14	1.34	0.128	0.223	0.078	0.066
NaNO <sub>3</sub> 1mM/HNO <sub>3</sub> 0.05 mM	14.24	1.13	1.33	0.123	0.087	0.078	0.064
NaNO <sub>3</sub> 1mM/HNO <sub>3</sub> 0.05 mM	14.14	1.12	1.35	0.120	0.091	0.079	0.064
Previous-baseline solvent	17.56	1.60	1.60	0.133	0.083	0.065	0.059

<sup>a</sup>Except where indicated (last line), the optimized solvent was used for each experiment. “NaNO<sub>3</sub> 1 mM” indicates that the four strips were carried out using a neutral solution of 1 mM sodium nitrate. “NaNO<sub>3</sub> 1 mM/HNO<sub>3</sub> 0.05 mM” indicates that the four strips were carried out using a mildly acidic solution of 1 mM sodium nitrate and 0.05 mM nitric acid.

Even with mildly acidic or even neutral stripping solutions, the cesium distribution ratios remain acceptable. Of course, the whole range of altered stripping solutions potentially encountered in the system was not tested. It is important to point out that these conditions include an acidic scrub, which is probably sufficient to ensure enough TOA protonation, therefore a good stripping. Poorer results could have been expected in the event that the two scrubs are alkaline due to entrained carryover of waste simulant from extraction.


### 3.3.2 Temperature Variation

Temperature-variation experiments were carried out at three different temperatures encompassing those temperatures that would potentially be encountered during the CSSX process. This experiment permits calculation of an apparent enthalpy change associated with each stage, thereby providing an approximate correction factor for any given temperature. It should be noted that the mechanism of extraction is complex [39], and thus, only an *apparent* enthalpy change is given as an empirical parameter for estimation purposes. Results are presented in Table 19.

**Table 19. ESS results for three different temperatures**

$T$ (°C)	$1000/T$ (K <sup>-1</sup> )	$D_{Cs}$						
		Extraction	Scrub #1	Scrub #2	Strip #1	Strip #2	Strip #3	Strip #4
15	3.4704	27.41	4.37	3.73	0.330	0.242	0.197	0.171
15	3.4704	24.86	4.14	3.60	0.364	0.276	0.221	0.192
25	3.3540	12.83	0.99	1.20	0.099	0.065	0.051	0.045
25	3.3540	12.89	0.98	1.19	0.098	0.064	0.051	0.045
35	3.2451	7.07	0.41	0.50	0.040	0.027	0.022	0.021
35	3.2451	7.18	0.41	0.49	0.041	0.028	0.023	0.021

Assuming that only a single equilibrium is involved in the cesium extraction, scrub, or strip steps, it may be shown that there is a direct relationship between the cesium distribution ratio and the formation constant of the considered equilibrium. For example, let's consider the simplest system:



$$D = \frac{[\overline{Cs^+}]}{[Cs^+]} = \frac{[\overline{CsNO_3Calix}]}{[Cs^+]} = K[NO_3^-][\overline{Calix}]$$


where overbars indicate organic-phase species. As long as the organic-phase cesium complex is mononuclear and neutral, such a proportionality between  $D$  and  $K$  should hold for different extraction mechanisms. Assuming that the temperature variation does not impact the loading of the calixarene or the total concentration of nitrate in the aqueous phase, one then may write:

$$\ln D = A + \ln K$$

$$\ln K = -\frac{\Delta G_{app}}{RT}, \quad \ln K = -\frac{\Delta H_{app}}{RT} + \frac{\Delta S_{app}}{R}$$

$$\ln D = B - \frac{\Delta H_{app}}{RT}$$

where  $T$  is expressed in degrees Kelvin;  $A$  and  $B$  are constants; and  $B$  includes  $A$  and  $\Delta S_{app}/R$ . The slope of the line  $\ln D$  versus  $1000/T$  should give the value of the apparent (app) enthalpies associated with the different stages of the process. The linearity of the different plots is confirmed as seen in Fig. 13. All results per stage are shown in Table 20.

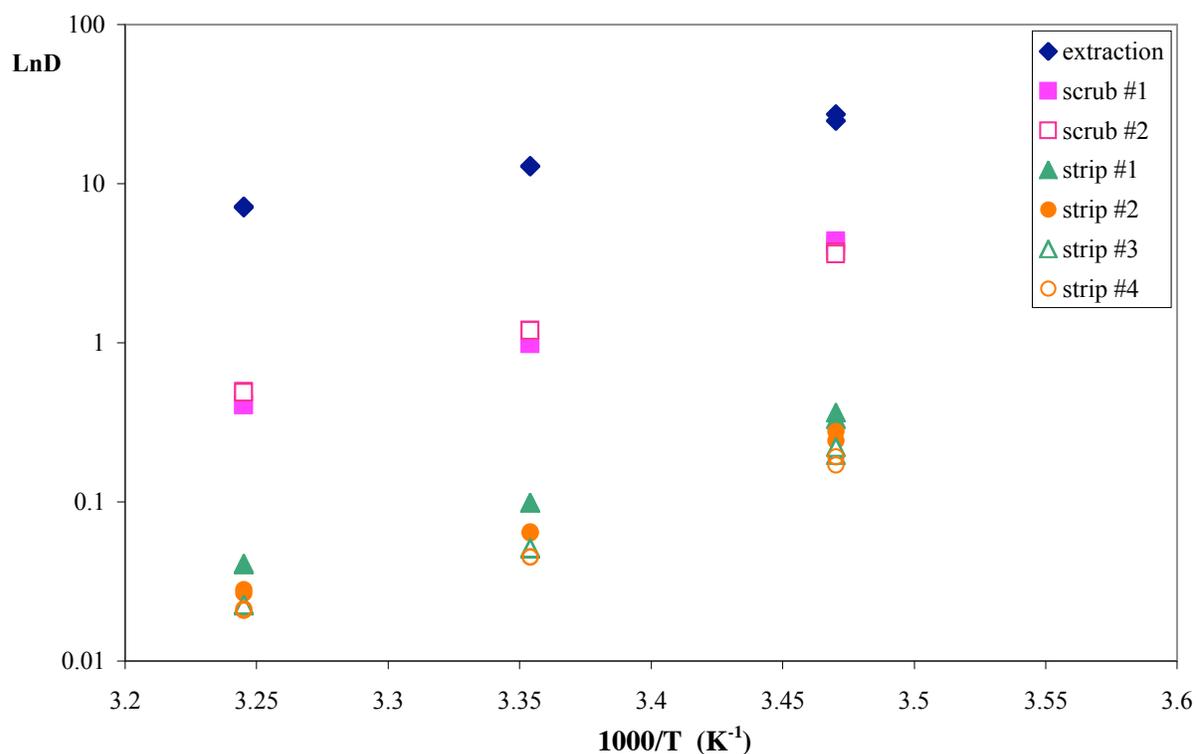

**Fig. 13. ESS test at three different temperatures.**

**Table 20. Apparent enthalpy changes for each ESS stage**

Stage	$\Delta H_{app}$ (kJ/mol)
Extraction	-47.95
Scrub #1	-86.82
Scrub #2	-74.24
Strip #1	-79.36
Strip #2	-82.94
Strip #3	-82.49
Strip #4	-79.71

The apparent enthalpy values are close to those obtained with the previous baseline solvent. Less scattering is observed here for the four strip values, probably because of the greater reliability of the data obtained at 15 °C. As observed before [11], the extraction step is the least sensitive to temperature variation, most likely because of the higher loading of BOBCalixC6 with potassium as the temperature decreases. This loading corresponds to a lower concentration of free BOBCalixC6, therefore lower  $D_{Cs}$  values, which in turn give a less steep apparent slope.

### 3.3.3 Multicycle Behavior

This test reproduces in part the multicycle tests performed in FY 2001. Based on the satisfactory results obtained with the previous baseline solvent, only two cycles were included in this test with the optimized solvent. After the first cycle, one sample was washed with sodium hydroxide 10 mM (O:A = 1:1) before going on to the extraction of the second cycle, while the other one was not. Results are summarized in Table 21.

**Table 21. Two-cycle ESS tests**

Test	$D_{Cs}$						
	Extraction	Scrub #1	Scrub #2	Strip #1	Strip #2	Strip #3	Strip #4
1 <sup>st</sup> cycle	13.88	1.110	1.267	0.1236	0.0721	0.0540	0.0478
1 <sup>st</sup> cycle duplicate	13.34	1.165	1.177	0.1107	0.0730	0.0532	0.0482
2 <sup>nd</sup> cycle	13.84	1.180	1.268	0.1356	0.0699	0.0540	0.0508
2 <sup>nd</sup> cycle with wash	13.79	1.107	1.261	0.1297	0.0724	0.0552	0.0492

A small increase in  $D_{Cs}$  is noticeable for the first and fourth strips on the second cycle, but this increase is close to, or within, the experimental error for ESS tests, approximately  $\pm 7\%$  [11]. The caustic wash seems to improve slightly the overall behavior.

### 3.4 CONCLUSIONS

The cesium extraction behavior of the optimized solvent is similar to the behavior obtained in FY 2000 and FY 2001 with the previous baseline solvent [11]. As expected, cesium distribution ratios are lower due to the decrease in the calixarene concentration, but the decrease in extraction is somewhat counterbalanced by the decrease in the cesium stripping values. As a result, the decrease in the ratio of  $D_{Cs}$  on extraction to that on stripping is not large, which corresponds to the observation in Chapter 2 that the flowsheet robustness is not unacceptably compromised. Apparent thermodynamic parameters for each stage are also very similar to those obtained with the previous baseline solvent. The results are consistent with the results of other studies showing that the formation constants associated with extraction equilibria did not vary much upon changing the solvent [41]. Finally, batch cesium extraction performance is not altered upon a second cycle, which can be taken as an indication of the effectiveness of the increased TOA concentration in the optimized solvent.



## 4. PARTITIONING OF SOLVENT COMPONENTS

### 4.1 INTRODUCTION

Partitioning ratios of solvent components are critical parameters of the CSSX process. Loss of any component (particularly of the calixarene extractant) can translate into loss of extraction performance and costs for replenishing the solvent to its original composition. Solvent components can be lost to the aqueous phase through two different mechanisms: partitioning and entrainment. Although BOBCalixC6, Cs-7SB, and TOA are each highly lipophilic, they possess small, finite tendencies to partition into the aqueous process solutions. Among these aqueous phases, the waste feed is the most important, because its flow will be much larger (15-fold in the current flowsheet) than the flow of the strip or wash solutions. Since the solvent will be recycled several thousand times in the course of a year's operation, it is clear that the partition ratios must be sufficiently high to avoid problems. For less than 10% loss of a reagent per year, the minimum partition ratio is approximately  $10^5$  (more exactly, assuming 2800 cycles,  $P > 88,600$  for O:A = 1:3). Measurement of such high  $P$  values, however, represents a considerable analytical challenge [11]. For the critical, expensive reagent, BOBCalixC6, it was thought likely that the condition of  $P > 10^5$  was met, although only a lower limit ( $P_{\text{BOBCalixC6}} > 12,500$ ) could be reported in the case of the previous baseline solvent in contact with waste simulant, strip solution, or wash solution [11]. Partition ratios for Cs-7SB and TOA were high and on the borderline of reliable measurement in that same study. For example, for partitioning into the waste simulant from the previous baseline solvent, these two reagents were found to have partition ratios of respectively  $>50,000$  and 38,000–200,000. For TOA, loss to the acidic strip solution would be more significant, since it was found that  $P = 14,000\text{--}55,000$  [11]. Overall, it thus appears likely that partitioning is not a significant issue. However, in view of both the acceptance of an optimized solvent composition and the uncertainty in the previous measurements, especially those for BOBCalixC6, it was judged desirable to address the partitioning issue again with the intent to improve upon analytical technique. Provided that partitioning losses of reagents could be more confidently shown to be small, it would then be possible elsewhere to approach the question of solvent losses in terms of entrainment, namely, the physical loss of solvent to the aqueous phase due to incomplete coalescence of fine droplets.

### 4.2 EXPERIMENTAL SECTION

#### 4.2.1 Materials and Contacting Method

Solvent Lot No. PVB B000894-87W (87W) was used for all experiments. This batch of washed solvent has the following composition: 0.007 M BOBCalixC6 (Lot #000714HMKC-0004), 0.750M Cs-7SB modifier (Lot #B000894-64DM), 0.003 M tri-*n*-octylamine (Lot #B000894-186), and Isopar<sup>®</sup> L (Lot #03081001-6-2). Full Simulant, draw #5 with Cs added to  $1.4 \times 10^{-4}$  M, was obtained in FY 2000.

Sodium hydroxide pellets (Lot # 41171126) used to prepare all caustic solutions were obtained from EM Science. Nitric acid was ultrapure Ultrex II (J. T. Baker, Lot #T19541). Dichloromethane (EM Science, Lot 38301846) was used as received.

Solvent 87W was contacted with various aqueous phases using O:A ratio of 1:100. The contacts were done by handshaking the two phases in 1 L Teflon<sup>®</sup> separatory funnels. The aqueous layers were then drained into 250-mL Teflon<sup>®</sup> centrifuge bottles and centrifuged for 20 min at 3000 rpm. The aqueous phases were carefully siphoned into clean bottles using small Tygon<sup>®</sup> capillary tubing to avoid organic-phase contamination. Known volumes of the aqueous phases (approx. 200 mL) were then back-extracted two times using a small volume (~10–15 mL) of fresh dichloromethane each time. The dichloromethane was taken to dryness by evaporation or nitrogen blow-down, and the resultant residue prepared for analysis.

## 4.2.2 Calixarene and Modifier Analyses

### Sample Preparation

All samples were originally presented as dichloromethane extracts (approximately 10 mL each) in 20-mL vials. The solvent was removed using a stream of dry flowing nitrogen while heating the bottom of each vial to 34 °C. The residues were then redissolved in 1 mL isopropanol and submitted for HPLC analysis.

### HPLC Analysis

All samples were analyzed with a Hewlett-Packard Model 1090 high-pressure liquid chromatograph equipped with an automatic sampler (maximum 100 individual samples; maximum injection volume 250 mL), ternary solvent gradient capability, and a diode array detector (wavelength range 190–600 nm). A PRP-1 (polystyrene divinylbenzene) reversed-phase column (150 × 4.1 mm), packed with 10 μm diameter particles (100 Å porosity), a product of the Hamilton Co. (Reno, NV), was used for all determinations. The analytes were eluted isocratically from the column using a 60/40 (v/v) mixture of isopropanol/acetonitrile at a flow rate of 1.00 mL/min. The sample analysis time was 5 minutes per sample; each was analyzed in duplicate. Both the analytical column and the solvent were heated to 40 °C using the internal column oven.

Because there was a difference of up to four orders of magnitude in the concentrations of BOBCalixC6 and Cs-7SB modifier, each sample was analyzed using two independent HPLC methods. In the first (used for low-level BOBCalixC6), the injection volume was 25 μL; in the second (used for high-level Cs-7SBT modifier), the injection volume was 10 μL. More significant differences between the two methods are described under “Quantitation” below.

### Quantitation

The quantitation of BOBCalixC6 was performed using the 25-μL injection volume described above and a measuring wavelength of 210 nm. The calibration procedure employed seven independently-prepared standards of BOBCalixC6, ranging in concentration between 0.001 and 0.1 mM, using

isopropanol as the diluent. Each standard was analyzed twice. The calibration data was fit to a least-squares calibration line, where the coefficient of determination,  $r^2$ , exceeded 0.9995. The detection limit was taken as the concentration that would produce the peak with the smallest integration, here 0.001 mM (i.e.,  $10^{-6}$  M).

The quantitation of Cs-7SB modifier was performed using the 10- $\mu$ L injection volume described above and a measuring wavelength of 254 nm. The calibration procedure employed seven independently-prepared standards of Cs-7SB modifier, ranging in concentration between 1 and 100 mM, using isopropanol as the diluent. Each standard was analyzed twice. The calibration data was fit to a least-squares calibration line, where the coefficient of determination,  $r^2$ , exceeded 0.998.

### 4.2.3 Tri-*n*-octylamine Analyses

#### Sample Preparation

The samples, which were originally prepared in an unspecified volume of dichloromethane, were initially taken to dryness at room temperature, then reconstituted in 1.0 mL dichloromethane. These rediluted samples were then transferred to 2-mL capacity automatic sampler vials for gas chromatographic analysis.

#### Gas Chromatographic Analysis

Gas chromatography was performed on a Hewlett Packard HP6850 series GC system using an HP-5MS (crosslinked 5% phenyl methyl siloxane) fused silica capillary column (Agilent Technologies catalog number 190915-433E) of length 30 meters, column internal diameter of 0.25 mm, phase ratio 250, and film thickness of 0.25  $\mu$ m. The carrier gas was helium (purity > 99.999%) flowing at 1 mL/min. The sample injection volume was 1  $\mu$ L, with a split ratio of 1/100. The column oven temperature was programmed from 50 °C to 280 °C at 10 °C/min, with a hold at 280 °C for 10 min. A flame ionization detector (FID) was used to detect the presence of TOA. The flows of the FID gases (i.e., air, hydrogen, and carrier) were set to factory-recommended values. All injections were performed using an Agilent Model 7683 automatic sampler.

#### Calibration

The response of the FID was calibrated using six independently-prepared standards ranging in concentration between 0.05 and 2 mM TOA in dichloromethane. The responses were fit to a linear least-squares calibration line, whose coefficient of determination,  $r^2$ , exceeded 0.9999. The detection limit of the FID was taken to be the standard concentration that produced the peak with the smallest integration, here 0.05 mM, corresponding to 177 pg actually injected on column.

## 4.3 RESULTS AND DISCUSSION

In all cases, the partitioning of the three solvent components was measured not only using the aqueous phases encountered in the different stages of the process (simulant, scrub, and strip solutions), but also using several concentrations of nitric acid (to assess the influence on tri-*n*-octylamine) and sodium hydroxide (being the candidate of choice for solvent washes in the process). All organic concentrations presented in the tables were determined by subtracting the measured aqueous concentration from the initial organic concentration. In order to be in the best possible conditions to obtain measurable amounts of organic compounds in the aqueous phases, an O:A ratio of 1:100 was used.

### 4.3.1 Calixarene Partitioning

Precision in calixarene detection was greatly improved compared to results obtained in FY 2000 and FY 2001. Results reported for similar experiments using the previous baseline solvent indicated that all partition ratios were greater than 12,500 based on the detection limit of the method [11]. Table 22 reflects the improved precision, as partition ratios are now at least 10 times greater than reported earlier, confirming the extremely low affinity of BOBCalixC6 for the aqueous phase.

In all cases, the amount of calixarene lost due to the contact with the aqueous phase is negligible. No real trend can be discerned from these experiments. Moreover, the method used to limit the potential contamination of that aqueous phase with the organic phase (siphoning) was the best available, but could not guarantee a complete contamination-free transfer. A mere contamination of 5–10  $\mu$ L of the aqueous phase with the organic phase is sufficient to mask any potential trend.

### 4.3.2 Modifier Partitioning

The modifier Cs-7SB is more soluble in the aqueous phase than the calixarene based on the partition ratios obtained with the previous baseline solvent. Moreover, its greater initial concentration in the optimized solvent (50% greater than the previous baseline solvent) makes it easier to detect in the aqueous phase after contact. Results are presented in Table 23.

Quantities of modifier solubilized in the aqueous phases are again found to be much greater than those of calixarene, which is at first not surprising in that the original amount of modifier is 100 times greater. However, that ratio is no longer maintained, which is a good indication that the technique used for subsampling the aqueous phase was adequate to minimize entrainment. Based on these experiments, it is difficult to assess with precision whether the presence of these organic components in the aqueous phase is due to true partitioning. More lengthy experiments would have been needed to add that detail. However, it can be said that if there is some entrainment contributing to the presence of solvent components in the aqueous phases, while its contribution to the calixarene partitioning is unknown, its contribution to modifier partitioning is negligible. One could assume in an extreme case that all the calixarene present in the aqueous phases is due to entrainment. By implication, this would still leave about 90% of soluble modifier that ought to be accounted for through true partitioning.

**Table 22. Partition ratios for BOBCalixC6<sup>a</sup>**

Aqueous phase	Organic concentration <sup>b</sup> (M)	Aqueous concentration (M)	Partition ratio
Full simulant	7.00E-03	3.31E-08	2.12E+05
Full simulant	7.00E-03	3.15E-08	2.22E+05
Scrub solution	7.00E-03	4.69E-08	1.49E+05
Scrub solution	7.00E-03	4.80E-08	1.46E+05
Strip solution	7.00E-03	1.09E-08	6.41E+05
Strip solution	7.00E-03	1.34E-08	5.22E+05
<hr/>			
1 M NaOH	7.00E-03	2.59E-08	2.70E+05
1 M NaOH	7.00E-03	2.56E-08	2.74E+05
0.1 M NaOH	7.00E-03	4.73E-08	1.48E+05
0.1 M NaOH	7.00E-03	4.56E-08	1.53E+05
0.01 M NaOH	7.00E-03	1.23E-08	5.68E+05
0.01 M NaOH	7.00E-03	1.54E-08	4.54E+05
0.001 M NaOH	6.99E-03	5.61E-08	1.25E+05
0.001 M NaOH	6.99E-03	5.54E-08	1.26E+05
<hr/>			
1 M nitric acid	7.00E-03	1.00E-08	6.97E+05
1 M nitric acid	7.00E-03	1.18E-08	5.93E+05
0.1 M nitric acid	7.00E-03	9.35E-09	7.49E+05
0.1 M nitric acid	7.00E-03	6.64E-09	1.05E+06
0.01 M nitric acid	7.00E-03	1.77E-08	3.96E+05
0.01 M nitric acid	7.00E-03	2.20E-08	3.18E+05

<sup>a</sup>The numeric notation used in this table and some subsequent tables in this report is the normal scientific notation, where 7.00E-03 represents  $7.00 \times 10^{-3}$ . Both notations are used interchangeably.

<sup>b</sup>Not measured. Values are calculated from the mass balance between the initial concentration of BOBCalixC6 in the solvent (0.007 M) and that measured in the aqueous phase at an O:A of 1:100.

### 4.3.3 Tri-*n*-octylamine Partitioning

Results for tri-*n*-octylamine partitioning were relatively satisfactory, but inconclusive. Tri-*n*-octylamine was probably present in amounts that were too low to be detected by the method designed to analyze the samples. A complete calibration curve was obtained, with the smallest integrable peak corresponding to  $5 \times 10^{-5}$  M. All analyzed samples fell well below the detection limit (not even a hint of peak was noticeable), corresponding to a lower limit for the partition ratio of 6000. However, based on these observations and previous results [11], it is reasonable to propose that the partitioning of TOA is not an issue for the process.

**Table 23. Partition ratios for modifier Cs-7SB**

Aqueous phase	Organic concentration <sup>a</sup> (M)	Aqueous concentration <sup>b</sup> (M)	Partition ratio
Full simulant	7.50E-01	BDL	>3.50E+04
Full simulant	7.50E-01	BDL	>3.50E+04
Scrub solution	7.44E-01	6.41E-05	1.16E+04
Scrub solution	7.44E-01	6.40E-05	1.16E+04
Strip solution	7.47E-01	3.49E-05	2.14E+04
Strip solution	7.46E-01	3.52E-05	2.12E+04
<hr/>			
1 M NaOH	7.47E-01	3.35E-05	2.23E+04
1 M NaOH	7.47E-01	3.37E-05	2.21E+04
0.1 M NaOH	7.45E-01	5.48E-05	1.36E+04
0.1 M NaOH	7.45E-01	5.36E-05	1.39E+04
0.01 M NaOH	7.45E-01	5.31E-05	1.40E+04
0.01 M NaOH	7.45E-01	5.31E-05	1.40E+04
0.001 M NaOH	7.45E-01	5.07E-05	1.47E+04
0.001 M NaOH	7.45E-01	5.09E-05	1.46E+04
<hr/>			
1 M nitric acid	7.38E-01	1.17E-04	6.29E+03
1 M nitric acid	7.39E-01	1.11E-04	6.68E+03
0.1 M nitric acid	7.44E-01	6.09E-05	1.22E+04
0.1 M nitric acid	7.44E-01	6.06E-05	1.23E+04
0.01 M nitric acid	7.44E-01	6.39E-05	1.16E+04
0.01 M nitric acid	7.44E-01	6.39E-05	1.16E+04

<sup>a</sup>Not measured. Values were calculated from the mass balance between the initial concentration of modifier in the solvent (0.75 M) and that measured in the aqueous phase at an O:A of 1:100.

<sup>b</sup>BDL denotes below detection limit.

#### 4.4 CONCLUSIONS

Partition ratios for BOBCalixC6 and Cs-7SB have been obtained with improved precision, leading to confidence that partitioning losses of these costly solvent components are small with respect to a goal of less than one solvent replacement per year. In the case of BOBCalixC6, partitioning losses to the aqueous raffinate are expected to amount to less than 4.2% per year, based on 2800 solvent cycles at O:A = 1:3 and  $P_{\text{BOBCalixC6}} = 2.2 \times 10^5$ . Taking  $P_{\text{Cs-7SB}} = 3.5 \times 10^4$ , corresponding losses of Cs-7SB are expected to be 27% per year. The partitioning of TOA to the aqueous phase was below the detection limit of the gas-chromatographic technique employed, giving  $P_{\text{TOA}} > 6000$ . No conclusion is therefore possible for TOA, but in view of results on the previous baseline solvent [11], the value of  $P_{\text{TOA}}$  is likely more than an order of magnitude larger than 6000. Based on chemical reasoning, it may be expected that loss of TOA will be more significant to the strip solution, and if one takes  $P_{\text{TOA}} > 6000$  for 2800 solvent cycles at O:A = 5:1, the implied loss of TOA will be less than 9.3%. Given that TOA is critical for good stripping, it is

recommended that more definite measurements of TOA partitioning be sought. It may be noted that commercially available trialkylamines having a higher molecular weight, such as tridecyl- or tridodecylamine, can be substituted for TOA to obtain greater lipophilicity and lower partitioning losses, if desired. On the other hand, recalling that the major breakdown product of TOA is dioctylamine, which is expected to be washed out by the strip solution [11], the analogous breakdown products of more lipophilic trialkylamines will be more difficult to wash out, making solvent cleanup possibly more difficult over extended cycling.

One of the questions asked regarding the present results is whether partitioning and entrainment can be distinguished. Based on the data obtained, it can be deduced that the predominant portion of the modifier present in the aqueous phase is due to solubility, not entrainment. It is less certain that this is the case for BOBCalixC6, since minute traces of entrainment or other artifacts (e.g., suspended dust) can mask its true partition ratio. It is again worth noting that the theoretically expected partition ratio for BOBCalixC6 is astronomical [11]. While the data obtained overall imply small partitioning losses of the solvent components, the expected gradual losses of Cs-7SB and possibly TOA likely necessitate periodic replenishment throughout the course of a year.



## 5. DISTRIBUTION OF MINOR ORGANIC AND INORGANIC COMPONENTS

### 5.1 INTRODUCTION

Besides understanding how the element of interest, cesium, and the solvent components distribute in the CSSX flowsheet, it is necessary to understand the fate of key minor inorganic and organic components. These may be introduced into the system from the waste feed or by degradation of the solvent components. Studies in FY 2001 with the previous baseline solvent showed that the strip effluent contained almost exclusively cesium nitrate in 1 mM nitric acid [11]. All other inorganic constituents of the simulant were either not detectably extracted or scrubbed out readily. Certain minor organic species extractable as anions or as neutral weak acids were found to impair stripping if present in sufficient concentration, but washing with dilute aqueous sodium hydroxide was effective in removing them and restoring solvent performance. Such organic species included dibutylphosphate, found in the waste as a breakdown product of tributylphosphate, phenol derivatives formed by degradation of Cs-7SB, or surfactants having 12 carbon atoms or less. Among the different tests run in FY 2001 with the previous baseline solvent, three experiments in which the distribution of minor organic or inorganic components may be impacted due to the change in solvent composition were chosen for repetition with the optimized solvent. Inorganic species included the competing alkali metals Na and K, radioactive metals Tc (as pertechnetate) and Sr, certain transition metals (e.g., Mn and Fe), noble metals, other metals (Ca and Al), and anions (nitrate, nitrite, and sulfate). Organic species included dibutylphosphate and the surfactant dodecanoate. Actinides were previously indicated to be negligibly extracted in simulant tests [11], as was confirmed on tests with real waste [40], and therefore actinides were not included in the present study.

### 5.2 EXPERIMENTAL SECTION

Phosphorus-31 Nuclear Magnetic Resonance spectra were obtained on a Bruker Avance 400 wide-bore spectrometer as described in Chapter 2. Chemical shifts were referenced against phosphoric acid, set to 0.0 ppm by way of a separate standard sample (sealed tube from Bruker). Preliminary contacts between the solvent 87W and the scrub, strip, or sodium hydroxide at different concentrations were performed in 15-mL polypropylene tubes at 25 °C with an O:A ratio of 1:1. Two types of experiments were performed; simulant compositions were described previously [11]. Either the full simulant (5<sup>th</sup> draw) was placed in contact with the solvent with an O:A ratio of 1:3, or the “salts+metals” simulant was used at an O:A ratio of 1:3 with the solvent in which a spike corresponding to 75 ppm of dibutylphosphate was added. The “salts+metals” simulant was the same as the full simulant but lacked the minor organic components [11]. The distribution of dibutylphosphate between the solvent 87W and the simulant, scrub, strip, or NaOH solutions were carried out as follows: solvent samples were analyzed directly with no dilution or addition of reagents for integration standards. Aliquots of solvent or simulant were placed directly into 10-mm quartz tubes. A quartz insert containing tributylphosphate (TBP) at 1

mM in deuteriochloroform was placed inside the 10-mm tube, and this solution external to the sample was used as the deuterium lock and integration standard. The insert permitted solvent or simulant samples to be run neat without the need to dilute or mix with a standard solution. Before running sample unknowns, spectra of the empty external tube with the insert and of the solvent containing 1 mM dibutylphosphate (210 ppm) were acquired. For unknown samples, an overnight acquisition (10k–12k scans) was performed to ensure that a reasonable signal/noise ratio was achieved. Data point files for each spectrum were converted to ASCII files and treated under MS Excel for deconvolution. Each peak was considered as a pure Lorentzian and approximated this way. This manipulation allowed more precise determination of the peak areas. The procedure was similar to that used earlier, and further details can be found in that document [11].

Tests involving the distribution of inorganic components (simulant components) were carried out through the regular ESS protocol [11]. The scrub and strip acidic phases were analyzed directly by inductively coupled argon plasma atomic emission spectrometry (ICAP-AES). Solvent samples were analyzed by first adding an equal volume of 1,3-diisopropylbenzene, stripping with an equal volume of deionized water, and analysis of the water layer by ICAP-AES. Strontium and technetium were added separately to the full simulant (originally prepared by Roger Spence, August 2000, filtered draw #5). Technetium was obtained from ORNL Isotope Sales as the ammonium pertechnetate form. A stock solution of  $3 \times 10^{-3}$  M was used, and a spike of 0.15 mL was added to 45 mL of simulant to obtain a final Tc concentration of  $10^{-5}$  M. Strontium nitrate was obtained from J. T. Baker. An aliquot of a 0.01 M  $\text{Sr}(\text{NO}_3)_2$  solution was used to spike the simulant.

The surfactant tested was lauric acid (dodecanoic acid), 99%, Emery Industries, Inc., Downey, CA. The surfactant was tested in the optimized solvent at  $2 \times 10^{-5}$  M. A 5-mM stock solution of dodecanoate was made by dissolving via sonication 10.1 mg of dodecanoic acid in 10 mL of Isopar<sup>®</sup> L (Exxon, Lot #0306 10967). A 48- $\mu$ L volume of 5 mM dodecanoate was added to 12 mL of Cs-7SB solvent, making an effective concentration of  $2 \times 10^{-5}$  M dodecanoate in the solvent. To wash out the surfactant, an equal volume of 10 mM NaOH was contacted with the dodecanoate-containing Cs-7SB solvent by end-over-end rotation inside a 25 °C constant-temperature air box for 30 minutes. The tube was then centrifuged and the solvent layer isolated. Three samples were subjected to the ESS protocol. Solvent designated 87P was pristine solvent; 87SS was solvent containing  $2 \times 10^{-5}$  M dodecanoate; 87WSS was dodecanoate-containing solvent that was subsequently subjected to the 10-mM NaOH wash procedure. The standard ESS protocol (extraction, two scrubs, and four strips) was followed. Contacts were performed in 50-mL Teflon<sup>®</sup> FEP tubes for the extraction step and 17-mL capacity polypropylene tubes for scrubs and strips. Contacts lasted 30 minutes using end-over-end rotation in a 25 °C air box.

## 5.3 RESULTS AND DISCUSSION

### 5.3.1 Distribution of Dibutylphosphate

The distribution of dibutylphosphate between the optimized solvent and various aqueous phases could differ from the values obtained in FY 2001 because of the variation in the solvent composition. However, the differences were found to be relatively minor. The same deconvolution technique was used to measure as precisely as possible the area of the peaks. As observed previously, dibutylphosphate partitions quantitatively to the aqueous phase when using a sodium hydroxide wash. The slight increase in the distribution value for larger concentrations of sodium hydroxide is actually due to the necessity of adding more dibutylphosphate to the system; that component was added in its acid form, and consequently some of the hydroxide was consumed.

The moderate partitioning of dibutylphosphate into the solvent was confirmed by using either the full simulant (containing the organic species) or the salts+metals simulant and a spike of dibutylphosphate to the solvent. In both cases, the partition ratios are identical. All results are summarized in Table 24.

**Table 24. Partitioning of dibutylphosphate**

	O:A	Initial concentration (ppm)	Concentration in the organic phase after contact (ppm)	Partition ratios
Simulant	1:3	25 <sup>a</sup>	43	4.1
Simulant	1:3	75 <sup>b</sup>	43	4.1
HNO <sub>3</sub> 0.05 M	1	500	60	0.12
HNO <sub>3</sub> 0.001 M	1	500	64	0.13
NaOH 0.001 M	1	500	1.5	3.0 × 10 <sup>-3</sup>
NaOH 0.01 M	1	500	BDL <sup>c</sup>	<5 × 10 <sup>-4</sup>
NaOH 0.1 M	1	3750	6	1.6 × 10 <sup>-3</sup>
NaOH 1M	1	6660	120	1.8 × 10 <sup>-2</sup>

<sup>a</sup>Dibutylphosphate is originally in the simulant. Pristine simulant was used.

<sup>b</sup>The solvent was spiked. The simulant used in this case was the Salts+Metals simulant.

<sup>c</sup>Below detection limit.

### 5.3.2 Distribution of Other Metals and Selected Radionuclides

The extraction of metals originally present in the waste simulant can be influenced by the change in solvent composition. It was determined in FY 2001 that the number of elements and their concentration in stages past the first scrub was negligible compared to the amount of cesium nitrate and nitric acid eventually present in the strip effluent. Two radionuclides potentially found in the actual waste (but not present in the baseline simulant composition [11]), strontium and technetium, were included in this study.

Concentrations presented in the three tables below were determined by stripping the organic phase, to which an equal volume of 1,3-diisopropyl benzene was added, with water. Elements presented in Table 25 along with their detection limits were not extracted by the optimized solvent. This is consistent with the results obtained with the previous baseline solvent.

**Table 25. Detection limits of non-extractable metals**

	Detection limits	
	(mg/L)	(M)
Ag	0.54	5.0E-06
Cr	0.021	4.1E-07
Cu	0.0027	4.2E-08
Hg	0.098	4.9E-07
Mn	0.0006	1.1E-08
Mo	0.014	1.5E-07
Pb	0.40	2.0E-06
Pd	0.010	9.6E-08
Rh	0.11	1.1E-06
Ru	0.094	9.3E-07
Sn	0.047	4.0E-07
Zn	0.0048	7.3E-08

Elements present in the simulant and their concentrations actually detected in one of the process stages are summarized in Table 26.

**Table 26. Concentrations of metals present in the solvent after extraction<sup>a</sup>**

Stage	Concentrations (M)				
	Al	Ca	Fe	K	Na
Extraction	6.60E-06	7.29E-07	1.17E-05	5.50E-03	3.82E-03
Scrub #1	BDL	5.52E-06	5.20E-06	1.49E-04	1.83E-05
Scrub #2	BDL	BDL	BDL	1.20E-05	4.03E-05
Strip #1	BDL	BDL	BDL	BDL	3.24E-05

<sup>a</sup>BDL = below detection limit. Detection limits are respectively  $4.2 \times 10^{-6}$  M for Al,  $3.0 \times 10^{-8}$  M for Ca,  $7.0 \times 10^{-8}$  M for Fe,  $3.9 \times 10^{-6}$  M for K, and  $4.3 \times 10^{-6}$  M for Na.

As expected, potassium and sodium are fairly well extracted and remain in the system following the cesium pattern. Except for sodium, all elements are scrubbed from the solvent by the second scrub stage. The analysis involved also the major anions present in the system. Results for nitrite, nitrate, and sulfate are shown in Table 27.

**Table 27. Concentrations of anions present in the solvent at each stage<sup>a</sup>**

	NO <sub>2</sub> <sup>-</sup>	NO <sub>3</sub> <sup>-</sup>	SO <sub>4</sub> <sup>2-</sup>
Extraction	3.79E-04	1.06E-03	2.10E-05
Scrub #1	BDL	4.72E-03	1.12E-05
Scrub #2	BDL	9.54E-03	5.12E-06
Strip #1	BDL	1.56E-03	BDL

<sup>a</sup>BDL = below detection limit. Detection limits are respectively 2.2  $\times 10^{-6}$  M for NO<sub>2</sub><sup>-</sup>, 8.1  $\times 10^{-6}$  M for NO<sub>3</sub><sup>-</sup>, and 2.0  $\times 10^{-6}$  M for SO<sub>4</sub><sup>2-</sup>.

As expected, only nitrate remains after the second scrub. Its concentration increases in the two scrub stages because of the protonation of tri-*n*-octylamine. Two other anions were taken under consideration, but their concentrations fell below the detection limit, respectively 7.0  $\times 10^{-6}$  M for Cl<sup>-</sup> and 1.0  $\times 10^{-6}$  M for PO<sub>4</sub><sup>3-</sup>. Chloride and phosphate did not appear in any of the phases analyzed above.

Based on the direct aqueous measurements (first part of Table 28) and the washes (indirect measurements of the organic phase), it is reasonable to say that strontium is very poorly extracted and is readily scrubbed from the solvent.

**Table 28. Concentrations of strontium in the aqueous phase at each stage<sup>a</sup>**

Stage	Aqueous [Sr] (M)
Scrub #1	3.99E-08
Scrub #2	BDL
Strip	7.99E-09
Extraction wash	6.85E-09
Scrub #1 wash	BDL
Scrub #2 wash	BDL
Strip wash	BDL

<sup>a</sup>Washes were performed by adding to the organic phase an equal volume of 1,3-diisopropyl benzene and contacting that phase with deionized water. BDL denotes analysis was below detection limit, which is 15 ppb or 1.71  $\times 10^{-9}$  M for strontium.

On the contrary, it was found that, while technetium is poorly extracted, it remains in the solvent as long as the aqueous phase in contact is acidic. However, its build-up in the solvent is not a concern in that a sodium hydroxide wash (concentrations 10–300 mM) is sufficient to remove it quantitatively from the solvent. Table 29 presents the results obtained at each stage and also for a water wash done on solvent after each contact.

**Table 29. Distribution ratios of technetium obtained in ESS tests**

Stage	$D_{Tc}$	$D_{Tc}$ upon stripping the organic phase with water
Extraction	3.78E-02	2.61E-02
Scrub #1	9.35E-01	5.27E+00
Scrub #2	6.77E-01	4.21E+00
Strip #1	9.03E+00	4.61E+00
Strip #2	9.73E+00	
Strip #3	1.31E+01	
Wash of strip #3 with 0.01M NaOH	2.85E-02	
Wash of strip #3 with 0.3 M NaOH	1.21E-02	

All inorganic elements identified to be potentially in the actual wastes have been determined to be of no impact on the extraction system. The change in solvent composition does not affect the previous conclusions regarding the partition of inorganic components and confirms the robustness of the solvent found in FY 2001.

### 5.3.3 Effect of Organic Surfactants

Distribution of organic surfactants has been considered to be of major interest [11], particularly after anticaking agents present in salts used to prepare waste simulants were found to create stripping problems [41]. This aspect of the process chemistry had been extensively investigated with the previous baseline solvent, and a remedy was found in every case, the best one being the TOA already present in the solvent. A repeat experiment involving solely sodium dodecanoate has been performed in the present work using the regular ESS test, with and without a wash of the solvent using sodium hydroxide. The results are presented in Table 30.

From the data, it may be observed that dodecanoate-containing solvent (at  $2 \times 10^{-5}$  M) performed almost no differently than the pristine or NaOH-washed solvent. The higher level of TOA chosen for the optimized solvent apparently offsets effects of the surfactant at this low concentration.

**Table 30. Effect of dodecanoate on cesium extraction in ESS tests**

Test	$D_{Cs}$						
	Extraction	Scrub #1	Scrub #2	Strip #1	Strip #2	Strip #3	Strip #4
87P <sup>a</sup>	13.36	0.9765	1.235	0.0923	0.0594	0.0494	0.0430
87SS <sup>b</sup>	13.50	0.9428	1.195	0.0917	0.0596	0.0472	0.0445
87WSS <sup>c</sup>	13.83	0.9569	1.139	0.0912	0.0600	0.0479	0.0424

<sup>a</sup>87P indicates pristine solvent.

<sup>b</sup>87SS indicates solvent initially containing dodecanoate at an initial concentration of  $2 \times 10^{-5}$  M.

<sup>c</sup>87WSS indicates solvent initially containing dodecanoate at an initial concentration of  $2 \times 10^{-5}$  M that was, prior to the ESS test, washed with 10 mM NaOH at a 1:1 ratio by end-over-end rotation for 30 minutes on a Glas-Col Rugged Rotator in a 25 °C airbox.

## 5.4 CONCLUSIONS

The distribution of the solvent constituents and of the trace organic and inorganic components was characterized. The major difference noticed between the results [11] involving the previous baseline solvent and the present results involving the optimized solvent is the demonstration of the ineffective stripping of technetium (as the pertechnetate anion form) from acidic solutions and the need to have a caustic wash following the last strip. All other components behaved as expected based on the results obtained earlier with the previous baseline solvent.



## 6. THERMAL STABILITY

### 6.1 INTRODUCTION

Experiments conducted in FY 2001 involved a series of extraction, scrub, and strip steps where the solvent was allowed to remain in contact with one of the corresponding aqueous phases for an extended period of time at 35 °C or 60 °C. The ultimate conclusion was that chemical and thermal stability of the previous baseline solvent significantly exceeds requirements. Logically, the optimized solvent is not expected to differ in this regard in that its chemical constituents are the same, and the work described in this chapter was accordingly intended to provide experimental support for this expectation [11]. In addition to a repeat of the ESS experiments run at the two temperatures 35 °C and 60 °C, experiments at two low temperatures were added, simulating conditions potentially encountered by the solvent upon shipping during winter months. Since only the solvent would be subject to such temperature stress, no contact with aqueous phases was performed before warming the solvent back to room temperature. Performance of the optimized solvent having been subjected to the different thermal and chemical conditions was assessed by ESS experiments uniformly performed at 25 °C.

### 6.2 EXPERIMENTAL SECTION

#### 6.2.1 Materials, Equipment, and Contacting Method

Three different solvents were used for these tests: two different batches of the previous baseline solvent and the optimized solvent. Batches PVB B000718-156W and B000718-124W of the previous baseline solvent are composed of 0.010 M BOBCalixC6 (IBC Advanced Technologies, Lot No. B000718-100CP), 0.50 M Cs-7SB modifier (Lot No. PVB B000718-10DMP), 0.001 M tri-*n*-octylamine (Lot No. PVB B000718-105L) in Isopar<sup>□</sup> L (ExxonMobil, Lot No. 0306 10967A). The optimized solvent (Batch PVB B000894-87W) is composed of 0.007 M BOBCalixC6 (IBC Advanced Technologies, Lot No. 000714HMKC-004), 0.75 M Cs-7SB modifier (Lot No. B000894-64DM), 0.003 M tri-*n*-octylamine (Lot No. PVB B000894-86) in Isopar<sup>□</sup> L (ExxonMobil, Lot No. 03081001-6-2).

Low-temperature experiments involving the solvents were carried out in a VWR laboratory refrigerator (0 °C) and in the freezer section of VWR combination refrigerator-freezer (−24 °C). Calibrated thermometers were used to determine the temperatures in the freezer and the refrigerator.


Experiments conducted at  $35 \pm 0.5$  °C (35 °C) and  $60 \pm 0.5$  °C (60 °C) were performed in Labline Imperial III (Model 305PI) incubators. The samples were agitated by end-over-end rotation on Glas-Col rugged rotators placed inside the incubators. Manipulations of the solvent and aqueous phases were performed using calibrated Eppendorf pipettes. ESS performance tests were run in standard order beginning with the solvent phase that had undergone thermal exposure over a 43-day contacting period.

## 6.2.2 ESS Analyses of Phase-Stability Samples

In order to remix the phases that had separated at low temperature, the test samples were agitated by end-over-end rotation on a Glas-Col rugged rotator located in an air box under a constant temperature of 25 °C. The optimized-solvent (-87W) samples were placed on the wheel first, and the -156W baseline samples followed two days later.

The ESS testing was performed on the -87W samples after 7 days on the wheel in the 25 °C airbox and involved an extraction step (O:A = 1:3), two scrub steps (O:A = 5:1), and four strips (O:A = 5:1). Waste simulant (SRS full simulant, draw #5 with  $1.4 \times 10^{-4}$  M Cs added) was spiked with  $^{137}\text{CsCl}$  at an activity of 0.30  $\mu\text{Ci/mL}$  (56.25  $\mu\text{L}$  of 80  $\mu\text{Ci/mL}$  into 15 mL of simulant using a calibrated Eppendorf pipette). In order to have sufficient counts for the third and fourth strips, a second spike (5  $\mu\text{L}$  of 88  $\mu\text{Ci/mL}$   $^{137}\text{CsNO}_3$ , affording a  $^{137}\text{Cs}$  activity of 0.629  $\mu\text{Ci/mL}$ , in the aqueous phase) was added to the third strip.

Teflon<sup>®</sup> FEP tubes (50 mL) were used for extraction, whereas 17-mL capacity polypropylene tubes were used in scrubs and strips. All tubes were washed prior to use according to the standard tube-washing protocol [11]. Individual tubes were shaken 10 times before being rotated on the wheel for 35 minutes. Phase separation was accomplished by centrifuging for 3 minutes at 2910 rpm in a refrigerated tabletop centrifuge (set point of 25 °C). A 0.250-mL sample was removed from each phase for  $^{137}\text{Cs}$  gamma counting using a Packard Cobra Quantum Model 5003 gamma counter equipped with a 3-inch NaI(Tl) crystal through-hole detector. A count time of 10-minutes duration was used with a window setting of 580–750 keV ( $^{137m}\text{Ba}$ ) for determining  $^{137}\text{Cs}$  activity. The protocol is represented in Fig. 14.

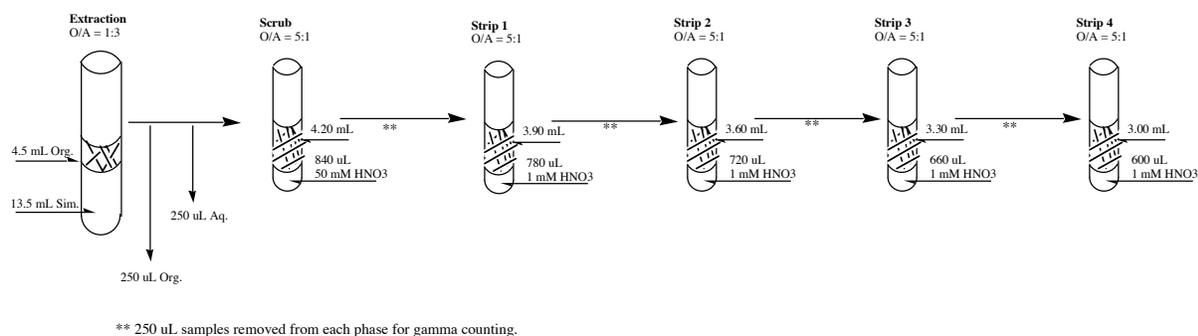

**Fig. 14. ESS protocol for optimized solvent phase-stability test.**

### 6.2.3 HPLC Analyses of Phase-Stability Samples

In the cases where solvent samples displayed stratification (separation into different layers) upon cooling in the refrigerator and freezer, aliquots of each layer were submitted for compositional analysis by HPLC. Samples were prepared for HPLC analysis by diluting 100  $\mu$ L of the solvent with 2-propanol to a final volume of 1 mL. All samples were analyzed according to the method described in section 5.2.2.

#### Quantitation


The analytes, BOBCalixC6 and Cs-7SB modifier, were quantitated using the wavelengths 226 nm and 254 nm, respectively, set using the diode array detector. Each analyte was calibrated using seven independent standards prepared in isopropanol/Isopar<sup>®</sup> L, each analyzed in duplicate. The calibration ranges for BOBCalixC6 and Cs-7SB modifier were 0.02 to 2 mM and 1 to 100 mM, respectively. The measured integrated peak areas were fit to a linear least-squares line, where the coefficient of determination,  $r^2$ , exceeded 0.999.

## 6.3 RESULTS AND DISCUSSION

Experiments involving the temperatures of  $-24$  °C and  $0$  °C are presented below in section 6.3.1. Experiments in which the solvent was contacted for an extended period of time with simulant, scrub, or strip solutions at  $35$  °C or  $60$  °C are described in section 6.3.2.

### 6.3.1 Phase Stability at Low Temperature

Samples of the pristine previous-baseline and optimized solvents that were stored in the refrigerator at  $0$  °C in 10-mL volumetric flasks overnight were observed to have split into two phases (Figure 15). As the density of the modifier (1.197 g/mL at  $25$  °C) is substantially more than the Isopar<sup>®</sup> L diluent (0.76 g/mL at  $20$  °C), the lower, heavier phase was presumed to be enriched in modifier relative to the upper, lighter phase. The thickness of the heavier layer was observed to increase with storage time over the course of 4 days (Table 31), after which the phase thickness was essentially unchanged. The composition of lower and upper layers for both solvents was determined by HPLC analysis (Table 32).

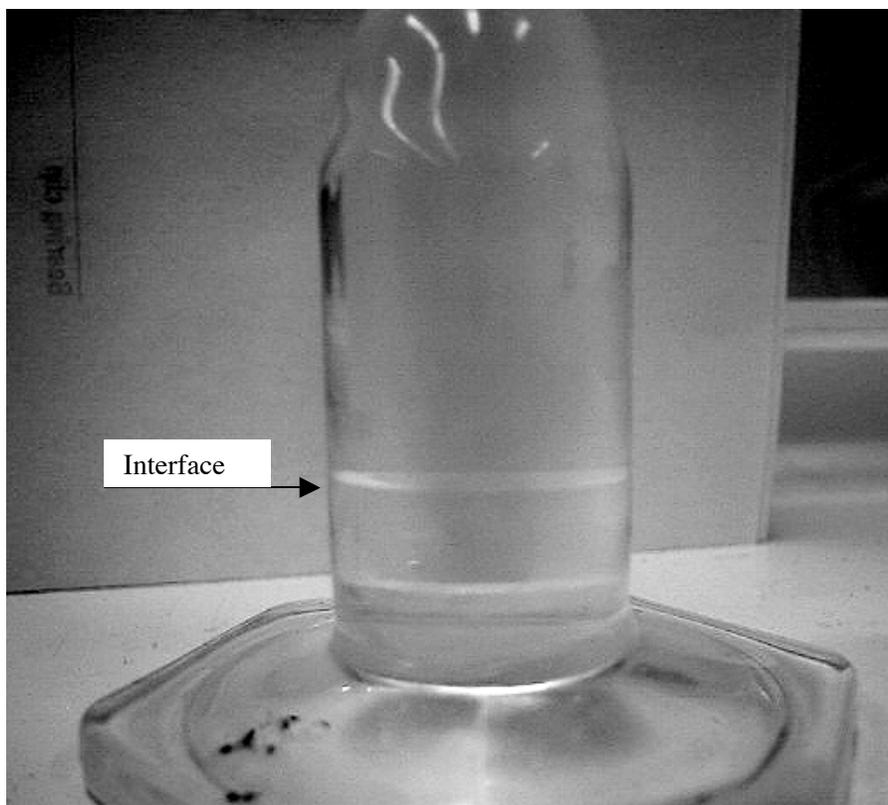

**Fig. 15. Phase separation in the optimized solvent at 0 °C.**

**Table 31. Phase separation at 0 °C for the previous-baseline and the optimized solvents**

Phase	Optimized solvent –87W			Original solvent –156W		
	Phase mass (g)	Phase density (g/mL)	Calculated volume (mL)	Phase mass (g)	Phase density (g/mL)	Calculated volume (mL)
Top	5.9115	0.826	7.157	7.517	0.825	9.111
Bottom	2.2776	0.969	2.350	0.6777	0.985	0.688
TOTAL	8.1891		9.51	8.1947		9.80

**Table 32. Phase compositions at 0 °C for the previous-baseline and the optimized solvents**

		Optimized solvent		Original solvent	
		Repeats (mM)	Avg. (mM)	Repeats (mM)	Avg. (mM)
Top layer	BOBCalixC6	2.81	2.85	7.05	7.04
		2.88		7.02	
	Cs-7SB	412.7	417.8	409.7	408.6
		422.9		407.5	
Bottom	BOBCalixC6	18.9	17.9	40.5	40.5
		16.9		40.5	
	Cs-7SB	1665.0	1611.6	1557.1	1555.8
		1558.3		1554.4	

A similar experiment was performed by placing 10-mL volumetric flasks filled with the optimized and previous baseline solvents in the freezer at  $-24\text{ }^{\circ}\text{C}$  overnight. The result is shown in Fig. 16, where, in spite of the frost, it is clearly evident that a white phase had separated. That heavier phase also seems to be frozen, likely due to the water contained in the solvent from the solvent-washing operation.

**Fig. 16. Phase separation in the optimized solvent at  $-24\text{ }^{\circ}\text{C}$ .**

**Table 33. Phase separation at -24 °C for the previous-baseline and the optimized solvents**

Phase	Optimized solvent -87W			Original solvent -156W		
	Phase mass (g)	Phase density (g/mL)	Calculated volume (mL)	Phase mass (g)	Phase density (g/mL)	Calculated volume (mL)
Top	5.1245	0.803	6.382	6.1929	0.788	7.859
Bottom	3.0263	1.006	3.008	1.9418	1.036	1.874
TOTAL	8.1508		9.39	8.1347		9.73

**Table 34. Phase compositions at -24 °C for the previous-baseline and the optimized solvents**

		Optimized solvent		Original solvent	
		Repeats (mM)	Avg. (mM)	Repeats (mM)	Avg. (mM)
Top layer	BOBCalixC6	0.49	0.49	0.87	0.88
		0.48		0.89	
	Cs-7SB	119.5	117.9	93.6	93.7
		116.4		93.8	
Bottom	BOBCalixC6	20.0	20.0	43.0	43.0
		20.0			
	Cs-7SB	1913.9	1916.2	2012.5	2012.5
		1918.6			

When the refrigerator-cooled samples were allowed to stand at room temperature for about four hours, the interface or boundary separating the two layers was no longer visible. However, when the samples were shaken gently, schlieren effects (“swirls” in the solvent) were visible suggesting that the solvent was not yet homogeneous (a density gradient still remained). Subsamples at the very top and very bottom of the flasks were taken, and the composition of these phases were again determined by HPLC. Note that the concepts of “very top” and “very bottom” are subjective. Results are presented in Table 35.

**Table 35. Solvent compositions at 0 °C for the previous-baseline and the optimized solvents**

		Optimized Solvent		Original Solvent	
		Repeats (mM)	Avg. (mM)	Repeats (mM)	Avg. (mM)
Top Surface	BOBCalixC6	3.35	3.36	9.78	9.77
		3.37		9.75	
	Cs-7SB	458.5	459.7	475.9	474.9
		461.0		473.9	
Very Bottom	BOBCalixC6	14.7	14.8	9.6	9.70
		14.9		9.7	
	Cs-7SB	1347.5	1355.5	481.9	483.6
		1363.5		485.2	

Similarly, the freezer-cooled samples were allowed to stand at room temperature to see how long it would take for the interface between the layers to be no longer visible. After a couple of days at room temperature, the interface was gone, and the “very top” and “very bottom” portions of the solvent in the flasks were again analyzed by HPLC (Table 36). It is noteworthy that, despite there being no visible sign of a phase separation, there remained a density gradient in the static samples. Of course, mixing the solvent results in homogenization.

**Table 36. Solvent compositions at –24 °C for the previous-baseline and the optimized solvents**

		Optimized solvent		Original solvent	
		Repeats (mM)	Avg. (mM)	Repeats (mM)	Avg. (mM)
Top surface	BOBCalixC6	0.65	0.67	1.06	1.06
		0.68		1.06	
	Cs-7SB	156.1	157.7	125.6	126.1
		159.4		126.5	
Very bottom	BOBCalixC6	18.8	19.0	34.6	34.2
		19.1		33.8	
	Cs-7SB	1883.5	1889.0	1594.2	1574.3
		1894.5		1554.5	

It is apparent and not surprising that the miscibility of the nonpolar aliphatic diluent Isopar<sup>®</sup> L and the polar fluorinated alcohol modifier is not infinite at all temperatures. Thus, static storage of the wet solvent at temperatures at or below freezing can result in phase separation, in which the concentrations of the solvent components in each layer are quite different. The phase separation is presumed to be fully reversible upon mixing and warming, but to verify that this is the case, the cesium-distribution behavior of the solvent following remixing was determined. After a 1-week equilibration at room temperature, solvents were subjected to ESS testing. Experiments were run in duplicate, and a pristine-solvent control was added to the series. These tests were done for both previous-baseline and optimized solvents. Results are summarized in Tables 37 and 38.

**Table 37. ESS tests at 25 °C using the low temperature-conditioned previous baseline solvent**

Conditions	$D_{Cs}$					
	Extraction	Scrub #1	Strip #1	Strip #2	Strip #3	Strip #4
0 °C	17.03	1.521	0.133	0.074	0.055	0.052
0 °C	17.41	1.542	0.135	0.076	0.056	0.053
–24 °C	17.03	1.487	0.138	0.081	0.061	0.055
–24 °C	16.87	1.482	0.136	0.078	0.058	0.050
Control	17.54	1.537	0.140	0.075	0.057	0.048

**Table 38. ESS tests at 25 °C using the low temperature-conditioned optimized solvent**

Conditions	$D_{Cs}$						
	Extraction	Scrub #1	Scrub #2	Strip #1	Strip #2	Strip #3	Strip #4
0 °C	13.39	1.03	1.15	0.103	0.066	0.054	0.048
0 °C	13.57	1.01	1.24	0.102	0.066	0.052	0.047
-24 °C	13.34	1.03	1.25	0.107	0.068	0.055	0.048
-24 °C	13.46	1.05	1.23	0.102	0.065	0.053	0.046
Control	13.29	1.04	1.23	0.098	0.064	0.052	0.048

The results indicate that cold conditions did not impair the performance of the solvents, previous-baseline or optimized, and that the phase separation is a fully reversible phenomenon. The cesium distribution behavior of the “cold-conditioned” solvents is comparable to their corresponding controls.

### 6.3.2 Chemical Stability at High Temperature

Stability tests at elevated temperatures (35 °C and 60 °C) were similar to those carried out in FY 2001. Solvent samples were carried partially through an ESS procedure and allowed to remain in prolonged contact with one of the aqueous solutions used in the sequence: the waste simulant, scrub solution, or strip solution. For example, to test the stability of the solvent to prolonged contact with strip solution, the solvent sample would undergo an extraction and two scrubs before being placed in prolonged contact with the strip solution. The experiments were carried out for 43 days. Cesium extraction performance of the thermally treated solvent samples was assessed by running ESS tests at 25 °C. Results are summarized in Table 39. Explanations for the entry nomenclature are given in the footnotes to the table, where the numbers in the sample codes indicate the temperature of the prolonged contact, either 35 or 60 °C.

In all cases, the solvents behaved similarly to the controls and furthermore gave ESS results remarkably close to those obtained in Chapter 3 with pristine solvent. Over a 43-day treatment, performance remained essentially unchanged for both 35 °C and 60 °C samples. In only one case, TS60SCB (treatment over scrub solution at 60 °C), did the  $D_{Cs}$  value seem high on stripping, but only for the second strip. This thermal-stability study thus yielded results comparable to those obtained in FY 2001.

## 6.4 CONCLUSIONS

The results validate the expectation that the optimized solvent would possess adequate thermal stability. It was clear from the thermal-stability tests on the previous baseline solvent [11] that the solvent undergoes degradation only when in contact with the acidic scrub and strip solutions, owing to

**Table 39. ESS tests at 25 °C using the high temperature-stressed optimized solvent**

Test	$D_{Cs}$									
	Extract	Scrub #1	Scrub #2	Strip #1	Strip #2	Strip #3	Strip #4	Extract	Scrub #1	Scrub #2
TS35P <sup>a</sup>	14.69	1.096	1.276	0.1065	0.0647	0.0513	0.0486			
TS60P <sup>a</sup>	13.90	1.101	1.298	0.1164	0.0718	0.0547	0.0485			
TS35S <sup>b</sup>	13.88	1.110	1.267	0.1344	0.0673	0.0516	0.0472			
TS60S <sup>b</sup>	13.34	1.165	1.177	0.1109	0.0693	0.0544	0.0475			
TS35SCB <sup>c</sup>		1.063	1.273	0.1018	0.0696	0.0539	0.0483	13.89		
TS60SCB <sup>c</sup>		1.165	1.305	0.1240	0.0971	0.0602	0.0484	13.90		
TS35ST <sup>d</sup>				0.1156	0.0699	0.0540	0.0478	13.84	1.180	1.268
TS60ST <sup>d</sup>				0.1397	0.0724	0.0552	0.0482	13.79	1.107	1.261

<sup>a</sup>TS35P or TS60P indicates use of pristine solvent, no contact with aqueous phases over the course of 43 days at either 35 °C or 60 °C.

<sup>b</sup>TS35S or TS60S indicates use of solvent that was in contact with simulant at O:A = 1:3 (draw #5 to which was added  $1.4 \times 10^{-4}$  M Cs) via end-over-end rotation for 43 days at either 35 °C or 60 °C.

<sup>c</sup>TS35SCB or TS60SCB indicates use of solvent that was contacted with simulant for 30 minutes at 25 °C via end-over-end rotation; the solvent phase was then contacted at O:A = 5:1 with scrub solution via end-over-end rotation for 43 days at either 35 °C or 60 °C.

<sup>d</sup>TS35ST or TS60ST indicates use of solvent that was contacted with simulant for 30 minutes at 25 °C via end-over-end rotation; the solvent phase was then contacted at O:A = 5:1 with scrub solution for 30 minutes at 25 °C via end-over-end rotation; the solvent phase then contacted at O:A = 5:1 with strip solution for 43 days via end-over-end rotation at either 35 °C or 60 °C.

degradation of the TOA. This effect was only detectable for the elevated-temperature samples (61 °C) held for 46 days or more. Pristine solvent held for 235 days at 61 °C underwent no noticeable degradation in performance, which was also true of solvent contacted with the waste simulant for 235 days at 61 °C. The present study reflects almost the same behavior, though the duration of the test (43 days) was insufficient to detect any impact to performance at either temperature. Making the assumption that only 4.4% of the solvent inventory resides in the scrub and strip sections of the flowsheet at any given time and that negligible degradation occurs outside of these sections [11], 43 days at the maximum normal operating temperature of 35 °C corresponds to a minimum of 977 days of solvent lifetime. Thus, it can be reasonably said that thermal stress should not have a significant impact on the performance of the optimized solvent.

It also was informative to examine the behavior of the optimized solvent under low-temperature conditions, which may be encountered during storage or shipping in winter months. The phase separation that occurs at low temperature does not impair the solvent performance upon warming and remixing. ESS experiments proved that the cesium extraction performance of the previous-baseline and optimized solvents is not altered by a cold-temperature conditioning resulting in a phase separation, possibly even a freezing of these phases. It is clear that solvent stored or shipped under cold conditions should be remixed at room temperature to ensure good quality results.



## 7. PHYSICAL-PROPERTIES MEASUREMENTS

### 7.1 INTRODUCTION

Laboratory-scale physical-property evaluations of the optimized Caustic-Side Solvent Extraction (CSSX) formulation have been completed to help determine the operating characteristics for design of the centrifugal contactors used in cesium removal at the Savannah River Site [20]. The properties measured in these tests were solvent density, viscosity, and dispersion numbers for the solvent against full simulant, scrub, and strip solutions at temperatures between 15 and 35 °C.

The evaluations included determination of phase separation by gravity settling under conditions present in the extraction, scrubbing, and stripping sections of the CSSX cascade, measurement of solvent density, measurements of solvent viscosity at several temperatures, and measurements of solvent surface tension and the interfacial tension of each solvent/simulant, solvent scrub, and solvent/strip combination. Results of these tests show that all of the formulations will perform the required separations and will perform satisfactorily in the contactors.

### 7.2 EXPERIMENTAL PROCEDURES

#### 7.2.1 Chemicals

The CSSX solvent is a blend of the organic materials listed above. Scrub (0.05 M HNO<sub>3</sub>) and strip (0.001 M HNO<sub>3</sub>) aqueous solutions were formulated using 1.0 M HNO<sub>3</sub>, procured from J. T. Baker Co. and diluted with water that had been deionized using a Barnstead Nanopure B filtration system. Sodium hydroxide solutions used to wash the solvent were formulated using a standard 0.1 M sodium hydroxide solution (ACS reagent grade, procured from the J. T. Baker Co.). SRS waste supernatant simulant was formulated according to SRS procedure [23], but the composition listed in that document for “average” SRS supernatant simulant was adjusted slightly as shown in Table 1 to match the new average simulant. The cesium concentration in the simulant batch used in testing was 0.000143 M. The simulant was prepared by first combining the ingredients shown below except for the cesium and silica. These were added along with the metals and organic components shown in Table 2 to make the complete simulant. After the materials in Tables 40 and 41 were all combined and allowed to age over a three-day period, the simulant was filtered through a 0.45-µm Gelman polypropylene groundwater filter to remove any precipitates formed. The simulant remained clear after filtration during all remaining testing.

## 7.2.2 Determination of Dispersion Number

The purpose of these tests was to determine phase-separation performance of the optimized CSSX solvent under conditions approximating those present in the extraction, scrubbing, and stripping sections of the CSSX cascade. Phase-separation performance was quantified in terms of dimensionless dispersion numbers, determined at temperatures ranging from 15 °C to 35 °C. Prior to phase-separation determinations, the solvent was equilibrated according to the test condition. Extraction-condition test solvent was equilibrated under extraction conditions.

**Table 40. Simulant composition (major components)**

Component	Avg. SRS <sup>a</sup> simulant (M)	New Avg. SRS <sup>b</sup> waste diluted with H <sub>2</sub> O (M)	Compound used	Mol. Wt.	Mass for new avg. (g/L)
Na <sup>+</sup>	5.6	5.6			
Cs <sup>+</sup>	0.00014	0.000143	CsCl	168.37	0.024077
K <sup>+</sup>	0.015	0.0146	KNO <sub>3</sub>	101.10	1.47606
OH <sup>-</sup>	1.91	2.086	NaOH	40.00	81.56
NO <sub>3</sub> <sup>-</sup>	2.14	2.039	NaNO <sub>3</sub>	84.99	173.295
NO <sub>2</sub> <sup>-</sup>	0.52	0.494	NaNO <sub>2</sub>	69.00	34.086
AlO <sub>2</sub> <sup>-</sup>	0.31	0.289	Al(NO <sub>3</sub> ) <sub>3</sub> ·9H <sub>2</sub> O	375.14	108.415
CO <sub>3</sub> <sup>2-</sup>	0.16	0.147	Na <sub>2</sub> CO <sub>3</sub> ·H <sub>2</sub> O	124.01	18.2295
SO <sub>4</sub> <sup>2-</sup>	0.15	0.137	Na <sub>2</sub> SO <sub>4</sub>	142.04	19.4595
Cl <sup>-</sup>	0.025	0.025	NaCl	58.44	1.4610
F <sup>-</sup>	0.032	0.030	NaF	41.99	1.2597
PO <sub>4</sub> <sup>3-</sup>	0.010	0.007	Na <sub>2</sub> HPO <sub>4</sub> ·7H <sub>2</sub> O	268.09	1.8766
C <sub>2</sub> O <sub>4</sub> <sup>2-</sup>	0.008	0.018	Na <sub>2</sub> C <sub>2</sub> O <sub>4</sub> (Sodium Oxalate)	134.00	2.412
SiO <sub>3</sub> <sup>2-</sup>	0.004	0.003	Na <sub>2</sub> SiO <sub>3</sub> ·9H <sub>2</sub> O	284.20	0.8526
MoO <sub>4</sub> <sup>2-</sup>	0.0002	0.0002	Na <sub>2</sub> MoO <sub>4</sub> ·2H <sub>2</sub> O	241.95	0.04839

<sup>a</sup>WSRC-RP-98-00168, Rev. 1.

<sup>b</sup>WSRC-RP-99-00006, Rev. 3.

**Table 41. Materials for full simulant (added trace metals and organic species)**

Component	Concentration in simulant (M)	Compound used	Molecular weight	Mass (g/L)
Cu <sup>2+</sup>	2.27 × 10 <sup>-5</sup>	CuSO <sub>4</sub> ·5H <sub>2</sub> O	249.68	0.00566
Cr <sup>6+</sup>	1.44 × 10 <sup>-3</sup>	Na <sub>2</sub> CrO <sub>4</sub>	161.97	0.2336
Zn <sup>2+</sup>	1.22 × 10 <sup>-4</sup>	Zn(NO <sub>3</sub> ) <sub>2</sub> ·6H <sub>2</sub> O	297.47	0.0364
Pb <sup>2+</sup>	1.01 × 10 <sup>-5</sup>	Pb(NO <sub>3</sub> ) <sub>2</sub>	331.20	0.00336
Fe <sup>3+</sup>	2.58 × 10 <sup>-5</sup>	Fe(NO <sub>3</sub> ) <sub>3</sub> ·9H <sub>2</sub> O	404.00	0.01042
Sn <sup>2+</sup>	2.02 × 10 <sup>-5</sup>	SnCl <sub>2</sub> ·2H <sub>2</sub> O	225.63	0.00456
Hg <sup>2+</sup>	2.49 × 10 <sup>-7</sup>	Hg(NO <sub>3</sub> ) <sub>2</sub> ·H <sub>2</sub> O	342.61	0.0000854
Rh <sup>3+</sup>	2.04 × 10 <sup>-6</sup>	Rh(NO <sub>3</sub> ) <sub>3</sub> ·2H <sub>2</sub> O	324.95	0.000663
Pd <sup>2+</sup>	3.85 × 10 <sup>-6</sup>	Pd(NO <sub>3</sub> ) <sub>2</sub>	230.43	0.000888
Ag <sup>+</sup>	9.27 × 10 <sup>-8</sup>	AgNO <sub>3</sub>	169.87	0.0000157
Ru <sup>3+</sup>	8.11 × 10 <sup>-6</sup>	RuCl <sub>3</sub>	207.43	0.00168
TPB	1.88 × 10 <sup>-6</sup>	Tributylphosphate	266.32	0.0005
DBP	1.19 × 10 <sup>-4</sup>	Dibutylphosphate	210.21	0.025
MBP	1.62 × 10 <sup>-4</sup>	Monobutylphosphate	154.10	0.025
<i>n</i> -Butanol	2.70 × 10 <sup>-5</sup>	C <sub>4</sub> H <sub>9</sub> OH	74.12	0.002
CHO <sub>2</sub> <sup>-</sup>	3.33 × 10 <sup>-2</sup>	NaCHO <sub>2</sub> (sodium formate)	68.01	1.5
TMA	1.69 × 10 <sup>-4</sup>	Trimethylamine	59.11	0.01

Scrub-conditioned solvent was obtained from extraction-equilibrated solvent and was batch equilibrated with scrub solution prior to testing. Strip-conditioned solvent was obtained from extraction- and scrub-equilibrated solvent, and was equilibrated with strip solution prior to testing. Single-batch pre-equilibrations were used to mitigate errors that might be introduced due to variations in technique that could affect split-batch operations. Dispersion numbers were determined as described in Chapter 2.

### 7.2.3 Laboratory Dispersion-Number Procedures

The procedure above was used with the solvent for each extraction, scrub, and strip contact at each temperature from 15 to 35 °C at 5 °C increments simulating the operations in each step of the CSSX process. A total of 300 mL of optimized solvent, 1500 mL of simulated SRS waste supernatant (full recipe), 200 mL of CSSX scrub solution (0.05 M HNO<sub>3</sub>), and 100 mL of CSSX strip solution (0.001 M HNO<sub>3</sub>) were required for the tests. Glass graduated cylinders (100 mL) with ground glass stoppers, an electronic stopwatch, a thermometer (LaPine 398-12-53), a refrigerated water bath (VWR model 13270-615 circulation bath, with 190 watts cooling and operated at about 5 L/min coolant recirculation rate and filled with distilled water), and a millimeter scale rule were used. Prior to use, all new or previously used

glassware and plastic vessels were washed by rinsing with tap water three times, rinsing with demineralized water three times, rinsing with ethanol two times, and rinsing with acetone two times. The equipment was allowed to air dry or dried with a stream of dry nitrogen or argon before use.

To pre-equilibrate the solvent to extraction conditions, 300 mL of solvent was combined with 936 mL of supernatant simulant and 60 mL of scrub solution in a 2-L flask at room temperature (24.5 °C). The flask was shaken vigorously for 20 s, held for 10 s, agitated for 20 s, held for 10 s, and agitated for 20 s again. The dispersion was allowed to separate, the solvent phase was collected, and the aqueous simulant solution was discarded.

## **7.3 DISPERSION-NUMBER DETERMINATIONS**

### **7.3.1 Extraction Dispersion-Number Determinations**

Extraction dispersion-number determinations were made using the full SRS simulant containing salts, metals, and organics and with non-radioactive cesium at a cesium concentration of 0.000143 M as shown in Tables 40 and 41. The tests were begun by placing 17.66 mL of solvent, 3.53 mL of scrub solution, and 53.81 mL of simulant in each graduated cylinder using Rainin EDP electronic 1 and 10-mL digital pipettes. The position of the stable interface between organic and aqueous phases and the height of the liquid column were measured. The cylinders were then placed in the temperature bath. After reaching the desired test temperature, the solution temperature was measured and each stoppered cylinder was removed from the bath and manually agitated for 20 s, held still for 10 s, and agitated for another 20 s, and then placed back into the water bath. The time elapsed between cessation of agitation and the return of the interface to its original position (i.e., the collapse of the dispersion) was recorded. The total height of the dispersion column in the graduate at the beginning of the settling period was also recorded. (If agitated correctly, the dispersion column height should be the height of the liquid column inside the graduate.) This was repeated two more times, and after the third time, the temperature of the solution in the graduate was measured again. This procedure was then repeated for 20, 25, 30, and 35 °C temperatures.

An additional extraction dispersion-number determination was made, again using the full simulant. The solvent (40 mL) was again pre-equilibrated with simulant (124.9 mL) and 8 mL of scrub solution as described above. The 17.66 mL of solvent, 3.53 mL of scrub solution, and 53.81 mL of simulant was added to each of the graduates and the extraction contacts were completed at 15, 20, 25, 30, and 35 °C.

A separate experiment following a similar procedure as that described above was completed using solvent that was not pre-equilibrated with simulant. The first time this was attempted, at 15 °C, one of the two graduates, when shaken, had the look of a gel for the dispersion and this took longer to separate. At 20 °C, the other one had the gel-like look and took longer to separate. That graduate continued to have the gel-look when shaken at the rest of the temperatures and the gel-like dispersion took longer to separate than the other. When it was separated, though, there was no visual difference between the two graduates except that in the one that had the gel-like formation, both organic and aqueous were clear as

soon as the break was achieved. When the normal shake and break occurred, the tube had foam after shaking and both phases were slightly cloudy for 30 min to 2 h after break. No data was taken for break time during this trial. The gel-like formation is shown in the photos in Fig. 17 at various stages of phase separation.


The graduates were left as they were, and after five days in the graduates, the shakeouts were repeated. This time, both tubes were clear the first two shakes at 15 °C, but on the third shake, the gel-like formation returned in the second tube, and it took about a minute to separate. At 20 °C, no gel appeared in either tube. Then the temperature was increased to 35 °C, and shakeouts continued. On the second shake, gel-like formation occurred in the second tube. It took slightly longer to separate, but then on the third shake, both were normal again. At 30 and 25 °C, neither tube had the gel like formations on any shakeouts. The trigger for the gel-like formation is not known. Sometimes it occurred in one tube, then the other, and most times not at all. It could not be predicted when or at what temperature the material would behave this way and if it did, whether it would continue. All data are shown in Table 42 and Fig. 18.

### **7.3.2 Scrubbing-Condition Dispersion-Number Determinations**


Solvent for the stripping dispersion number determinations was recovered from the single-batch extraction-condition equilibration and was determined to be 261.6 mL. It was placed into a clean 500-mL separatory funnel and a volume of scrub solution equal to one-fifth the solvent volume was added (52.32 mL). The funnel was agitated vigorously for 20 s, held for 10 s, agitated for 20 s, held for 10 s, and agitated for 20 s again. The temperature of the dispersion was determined (24.5 °C) and the dispersion was allowed to separate. The solvent phase was collected and the aqueous solution was discarded.



At the start of settling (gel on left)

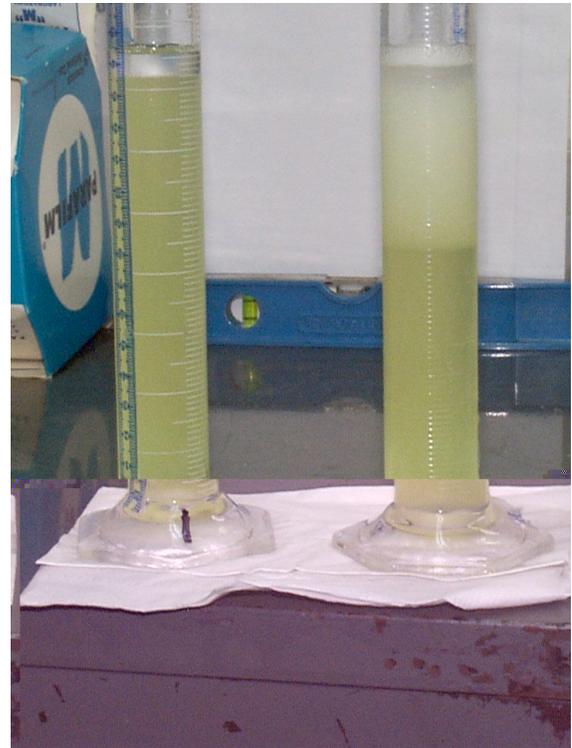

After about 1 minute

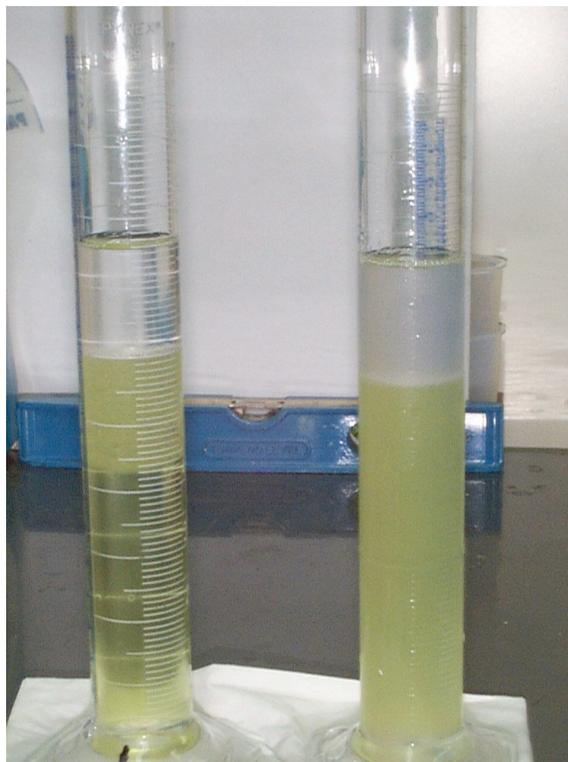

About 90% complete settling.




Completion of settling.

**Fig. 17. Gel-like material formed during dispersion-number determinations.**

**Table 42. Dispersion numbers for extraction with optimized CSSX solvent**

Solvent sample	Dispersion height (cm)	Simulant/solvent dispersion number	Determination temperature (°C)
Trial 1			
15C#1	13.3	0.001013	15.6
15C#2	13.75	0.000864	15.6
20C#1	13.3	0.001243	20.6
20C#2	13.75	0.001070	20.6
25C#1	13.3	0.001431	25.2
25C#2	13.75	0.001371	25.2
30C#1	13.3	0.001581	30.0
30C#2	13.75	0.001629	30.0
35C#1	13.3	0.001782	34.8
35C#2	13.75	0.001909	34.8
Trial 2			
15C#1	14.0	0.000623	15.3
15C#2	13.2	0.000680	15.3
20C#1	14.0	0.000872	20.2
20C#2	13.2	0.000893	20.2
25C#1	14.0	0.001001	25.2
25C#2	13.2	0.001212	25.2
30C#1	14.0	0.001107	30.0
30C#2	13.2	0.001338	30.0
35C#1	14.0	0.001226	34.9
35C#2	13.2	0.001591	34.9
Trial 3			
15C#1	14.2	0.000451	15.2
15C#2	14.6	0.000436	15.2 (gel on one shakeout)
20C#1	14.2	0.000424	20.1
20C#2	14.6	0.000438	20.1
25C#1	14.2	0.000516	25.2
25C#2	14.6	0.000485	25.2
30C#1	14.2	0.000632	30.0
30C#2	14.6	0.000569	30.0
35C#1	14.2	0.000813	35.0
35C#2	16.7	0.000664	35.0 (gel on one shakeout)

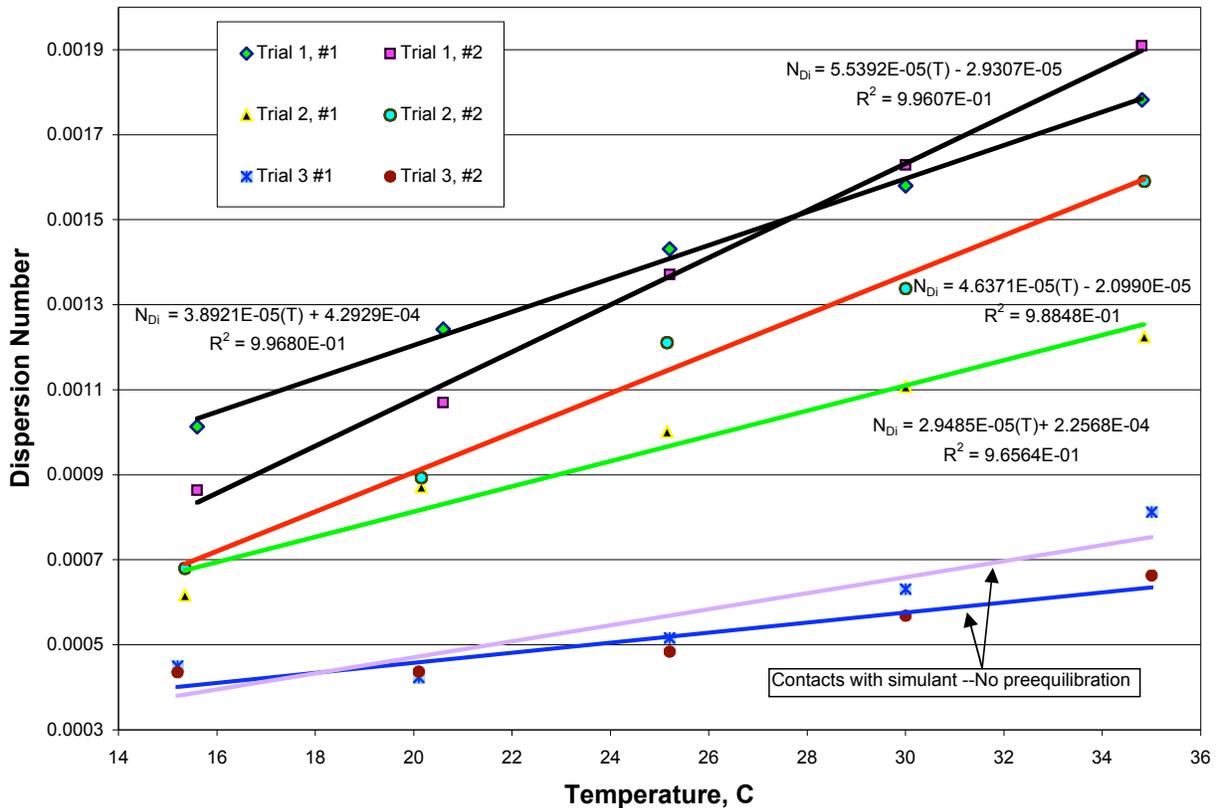

**Fig. 18. Graph of CSSX solvent extraction equilibration dispersion numbers.**

Then, 62.5 mL of recovered solvent was placed into each of two clean, 100 mL graduated cylinders and 12.5 mL of scrub solution (0.05 M HNO<sub>3</sub>) was added to each cylinder. The position of the stable interface between organic and aqueous phases and the height of the liquid column were measured. They were then placed in the water bath and equilibrated to the test temperature. After reaching the desired test temperature, the solution temperature was measured and each stoppered cylinder was removed from the bath and manually agitated for 20 s, held still for 10 s, agitated for another 20 s, and then placed back into the water bath. The time from the cessation of agitation to the reestablishment of the interface was measured as the breaktime. Each equilibration was repeated two times, and then the temperature of the solution in the graduate was measured after the third equilibration. The temperature of the bath was then adjusted to the next test temperature and the equilibration process was repeated at 20, 25, 30, and 35 °C. The scrub-condition dispersion numbers results are shown in Fig. 19 and in Table 43.

### 7.3.3 Stripping-Condition Dispersion-Number Determinations


Solvent for the stripping determinations was recovered from the single-batch scrub-condition equilibration. A total of 130 mL solvent was placed into a clean 500-mL separatory funnel. A volume of

strip solution equal to one-fifth the solvent volume (26 mL) was added. The funnel was agitated vigorously for 20 s, held for 10 s, agitated for 20 s, held for 10 s, and agitated for 20 s again. The temperature of the dispersion was determined (24.5 °C) and the dispersion was allowed to separate. The solvent phase was collected and the aqueous solution was discarded.


Then, 62.5 mL of the recovered solvent was placed into each of two clean, 100-mL graduated cylinders and 12.5 mL of strip solution (0.001 M HNO<sub>3</sub>) was added to each cylinder. The position of the stable interface between organic and aqueous phases and the height of the liquid column was measured. The cylinders were then placed in the water bath and equilibrated to the test temperature. After reaching the desired test temperature, the solution temperature was measured and each stoppered cylinder was removed from the bath and manually agitated for 20 s, held still for 10 s, agitated for another for another 20 s, and then placed back into the water bath. The time from the cessation of agitation to the reestablishment of the interface was measured as the breaktime. Each equilibration was repeated two times, and then the temperature of the solution in the graduate was measured after the third equilibration. The temperature of the bath was then adjusted to the next test temperature and the equilibration process was repeated at 20, 25, 30, and 35 °C. The stripping dispersion number results are shown in Fig. 20 and in Table 44.

**Table 43. Dispersion numbers for scrub with optimized CSSX solvent**

Solvent sample	Dispersion height (cm)	Scrub/solvent Dispersion number	Determination temperature (°C)
15C#1	14.5	0.000602	15.6
15C#2	14.3	0.000623	15.6
20C#1	14.4	0.000856	20.4
20C#2	14.4	0.000828	20.4
25C#1	14.6	0.001070	25.2
25C#2	14.5	0.001045	25.2
30C#1	14.6	0.001289	29.75
30C#2	14.5	0.001254	29.75
35C#1	14.6	0.001506	34.55
35C#2	14.5	0.001453	34.55

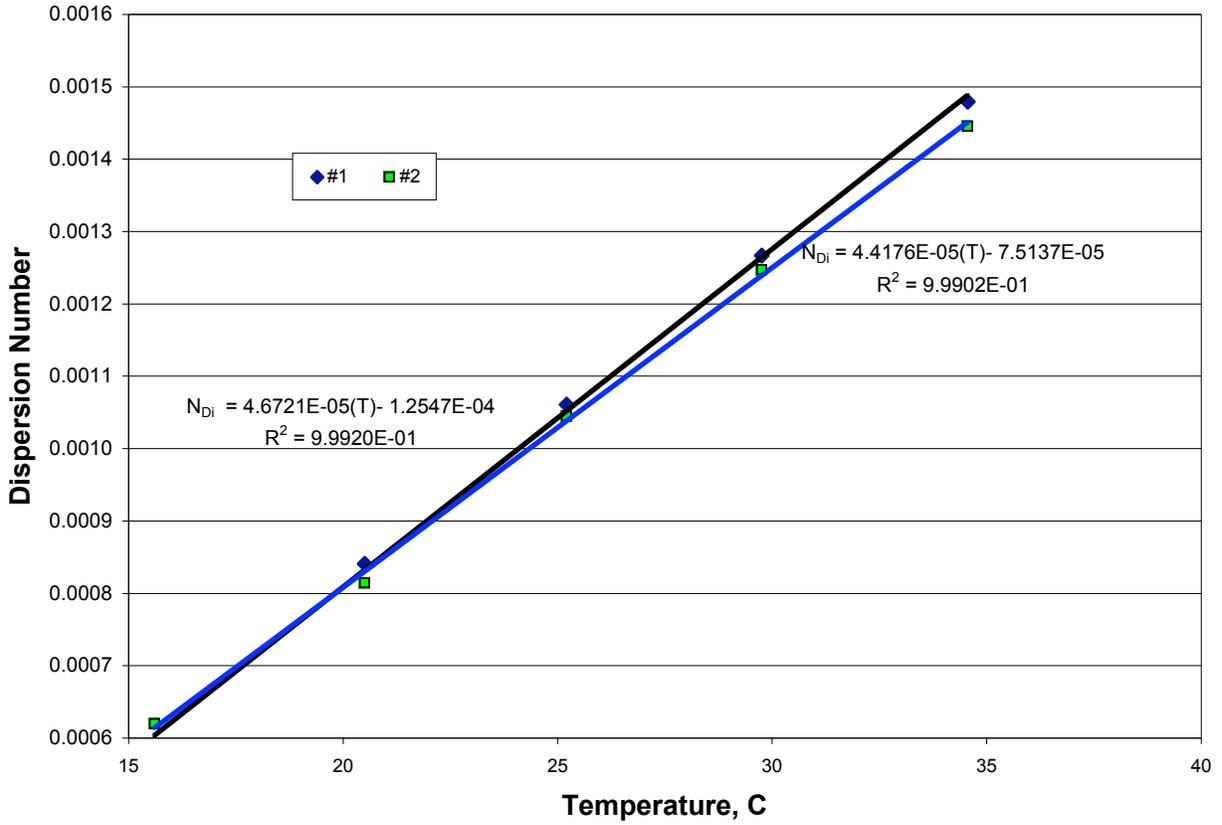

**Fig. 19. Graph of CSSX solvent scrub equilibration dispersion numbers.**

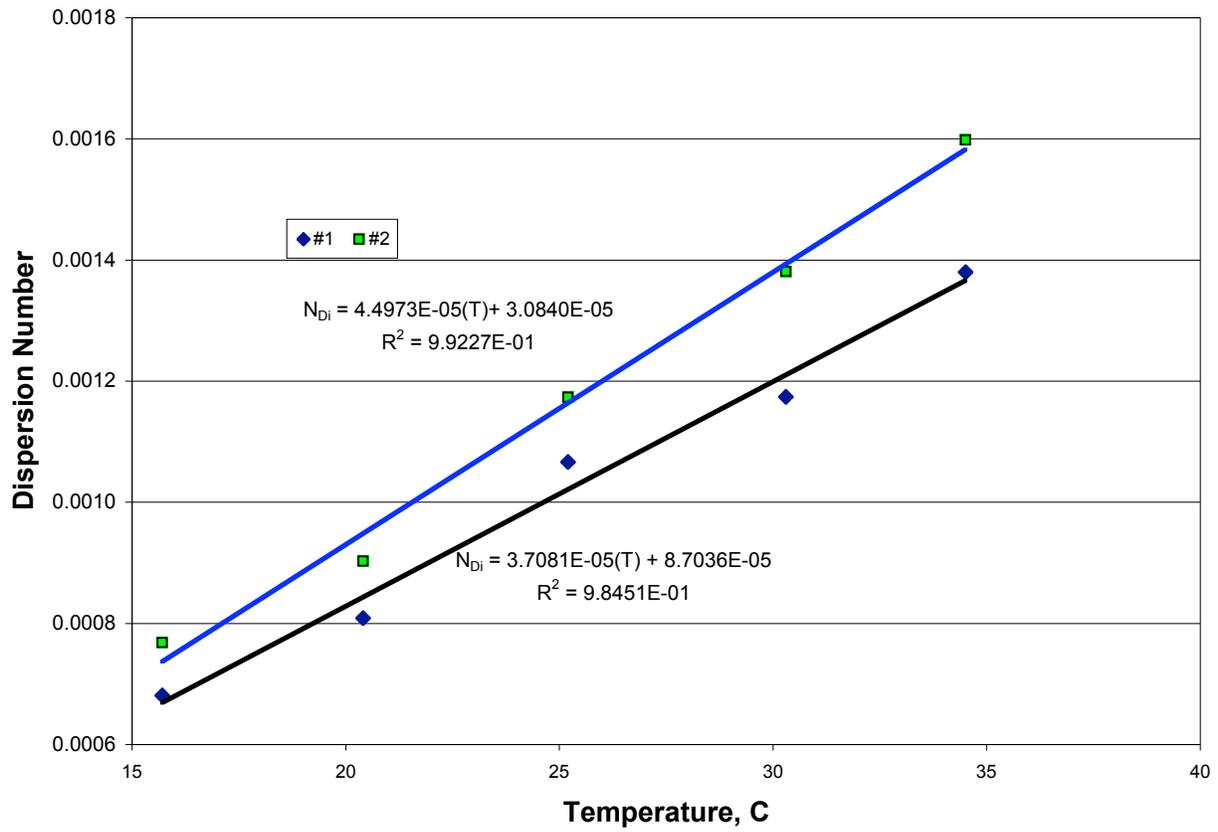

**Fig. 20. Graph of CSSX solvent strip equilibration dispersion numbers.**

**Table 44. Dispersion numbers for strip with optimized CSSX solvent**

Solvent sample	Dispersion height (cm)	Scrub/solvent dispersion number	Determination temperature (°C)
15C#1	14.0	0.000686	15.7
15C#2	14.9	0.000779	15.7
20C#1	14.0	0.000813	20.4
20C#2	14.9	0.000915	20.4
25C#1	14.1	0.001080	25.2
25C#2	14.8	0.001190	25.2
30C#1	14.15	0.001189	30.3
30C#2	14.9	0.001400	30.3
35C#1	14.2	0.001398	34.5
35C#2	14.95	0.001620	34.5

#### 7.4 MEASUREMENT OF SOLVENT DENSITIES

The solvent densities were measured using procedures described in Chapter 2. Each flask was filled using a 500-mL separatory funnel to just below the line and then adjusted to the line with a small transfer pipette after coming to temperature in the water bath. The actual volume of each flask was calculated from the weight of the water contained at 20 °C, and the volume at the other test temperatures was calculated according to ASTM E542. The density of water at each temperature was measured and then compared to the published data for water density at those temperatures. The calculated volume was used in subsequent density determinations of the solvent at each temperature. The results for the flask volume determinations are shown in Table 45.

For the solvent densities, the same volumetric flasks were emptied and rinsed twice with ethanol, twice with acetone, and allowed to air dry over night. They were weighed and then filled to the line with solvent using a separatory funnel. They were then placed in the water bath at 15 °C and allowed to come to bath temperature. After reaching bath temperature, the levels in each flask were adjusted by adding or removing (at higher temperatures) solvent using a small pipette. After adjustment of the levels, they remained in the bath for ten more minutes, then removed and the levels checked again and adjusted if needed. They were then dried and weighed. After weighing, they were returned to the bath and the temperature of the bath adjusted to the next test temperature. The results of the solvent density determinations are shown in Table 46 and Fig. 21.


**Table 45. Water-density determinations**

Temperature (°C)		Flask 1	Flask 2	Flask 3	Actual water density at temperature (g/cm <sup>3</sup> )
24.4	Tare wt.	60.1097	62.3954	61.1582	0.997197
	Gr. Wt.	159.6757	161.9962	160.7973	
	Net Wt.	99.5660	99.6008	99.6391	
	density	0.9966	0.9970	0.9968	
	deviation	0.00059	0.00018	0.00036	
15.10	Flask Vol <sub>24.4</sub> =	99.9046	99.8991	99.9548	0.999099
	Gr. Wt.	159.9030	162.2013	161.0086	
	Net Wt.	99.7933	99.8059	99.8504	
	density	0.9990	0.9992	0.9990	
	deviation	0.00012	-6.1E-05	5.1E-05	
20.00	Flask Vol <sub>15</sub> =	99.8953	99.8898	99.9455	0.998204
	Gr. Wt.	159.8188	162.0990	160.9174	
	Net Wt.	99.7091	99.7036	99.7592	
	density	0.9981	0.9981	0.9981	
	deviation	0.00012	0.00012	0.00012	
30.00	Flask Vol <sub>20</sub> =	99.9002	99.8947	99.9504	0.995647
	Gr. Wt.	159.5551	161.8550	160.6975	
	Net Wt.	99.4454	99.4595	99.5392	
	density	0.9953	0.9955	0.9958	
	deviation	0.00030	0.00010	-0.00014	
35.10	Flask Vol <sub>30</sub> =	99.9102	99.9047	99.9604	0.993997
	Gr. Wt.	159.4301	161.6880	160.5176	
	Net Wt.	99.3204	99.2926	99.3594	
	density	0.9940	0.9938	0.9939	
	deviation	-4.9E-05	0.00017	6.0E-05	
40.15	Flask Vol <sub>35</sub> =	99.9153	99.9097	99.9655	0.992158
	Gr. Wt.	159.2345	161.5226	160.3544	
	Net Wt.	99.1248	99.1272	99.1962	
	density	0.9920	0.9921	0.9923	
	deviation	0.00012	4.1E-05	-9.6E-05	
	Flask Vol <sub>40</sub> =	99.9204	99.9148	99.9705	

**Table 46. Optimized-solvent density determinations<sup>a</sup>**

Temperature (°C)		Flask 1	Flask 2	Flask 3	Average density	Standard deviation	Variance
15.00	Tare wt.	60.1097	62.3954	61.1582			
	Gr. Wt.	145.9414	148.2582	147.0724			
	Net Wt.	85.8317	85.8628	85.9142			
	density	<b>0.8592</b>	<b>0.8596</b>	<b>0.8596</b>	<b>0.8595</b>	0.0002	4.7E-08
	Vol <sub>15</sub> =	99.8952	99.8897	99.9454			
20.05	Gr. Wt.	145.5436	147.8496	146.6507			
	Net Wt.	85.4339	85.4542	85.4925			
	density	<b>0.8552</b>	<b>0.8554</b>	<b>0.8553</b>	<b>0.8553</b>	0.0001	1.6E-08
	Vol <sub>20</sub> =	99.9002	99.8947	99.9504			
25.00	Gr. Wt.	145.1693	147.4782	146.2873			
	Net Wt.	85.0596	85.0828	85.1291			
	density	<b>0.8514</b>	<b>0.8517</b>	<b>0.8517</b>	<b>0.8516</b>	0.00028	2.5E-08
	Vol <sub>25</sub> =	99.9052	99.8997	99.9554			
30.00	Gr. Wt.	144.7731	147.0728	145.893			
	Net Wt.	84.6634	84.6774	84.7348			
	density	<b>0.8474</b>	<b>0.8476</b>	<b>0.8477</b>	<b>0.8476</b>	0.0001	2.1E-08
	Vol <sub>30</sub> =	99.9102	99.9047	99.9604			
35.00	Gr. Wt.	144.366	146.6559	145.496			
	Net Wt.	84.2563	84.2605	84.3378			
	density	<b>0.8433</b>	<b>0.8434</b>	<b>0.8437</b>	<b>0.8434</b>	0.0002	4.2E-08
	Vol <sub>35</sub> =	99.9152	99.9096	99.9654			
40.15	Gr. Wt.	143.9722	146.2631	145.0803			
	Net Wt.	83.8625	83.8677	83.9221			
	density	<b>0.8393</b>	<b>0.8394</b>	<b>0.8395</b>	<b>0.8394</b>	0.0001	7.7E-09
	Vol <sub>40</sub> =	99.9204	99.9148	99.9705			

<sup>a</sup>Density results are bolded for easier reading.

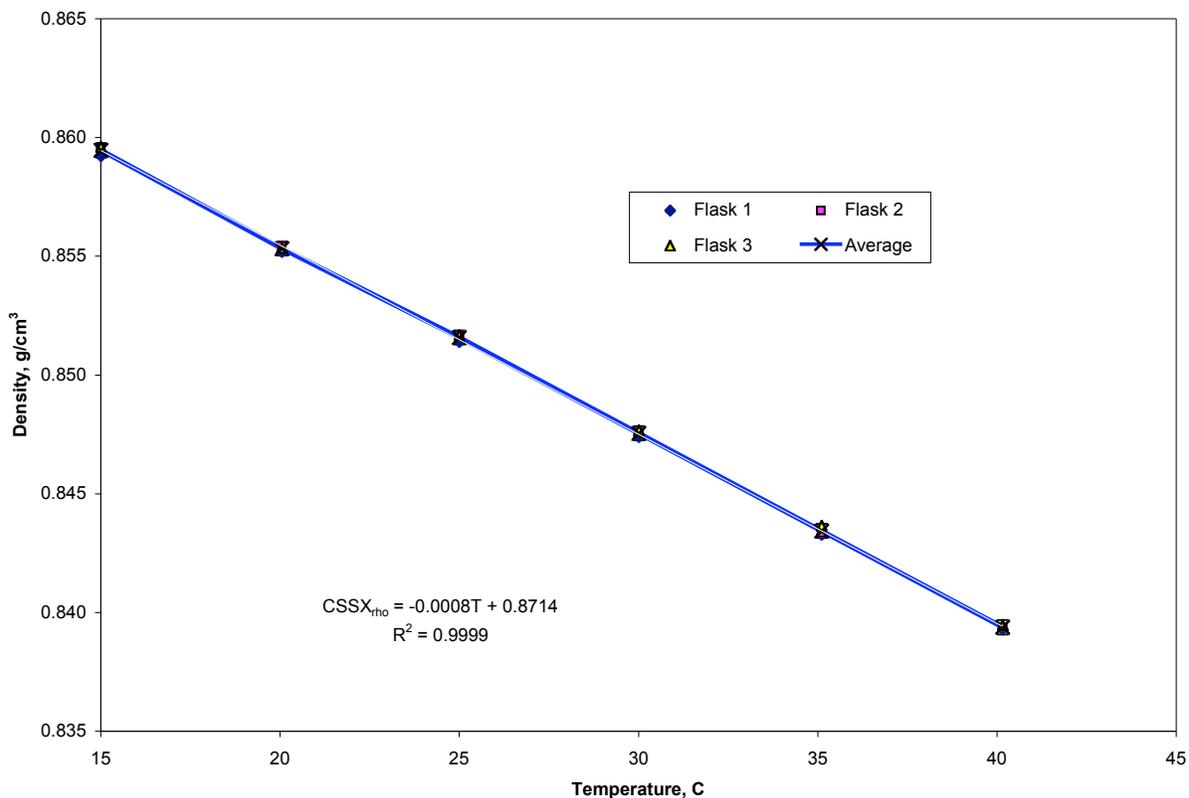

**Fig. 21. Solvent density versus temperature.**

## 7.5 MEASUREMENT OF SOLVENT VISCOSITIES

The viscosity of the new formulation of solvents was measured as described in Chapter 2. Each test was begun by adding 16 mL of the solvent to the UL adaptor, installing it on the viscometer, starting the spindle rotation at 60 rpm, and then setting the temperature bath to 15°C. After the temperature had stabilized for several minutes, the viscosity of the sample was measured. The temperature bath was then adjusted to the next temperature and the system temperature allowed to stabilize before the next reading. The set of viscosity determinations were made three times. The second set was completed with fresh solvent, and the third set repeated the tests in reverse order with the same solvent after 30 min at 40 °C. The results of three determinations of the solvent viscosity measurements are shown in Table 47. The results are given for the percent torque, the viscosity, and the shear rate at each temperature. The results are also presented graphically in Figs. 22 and 23. Figure 22 is a plot of the viscosity versus temperature and Fig. 23 is a plot of the shear stress versus the temperature. The solvent’s viscosity decreases with increasing temperature as expected for this type of liquid.

**Table 47. Solvent-viscosity determinations<sup>a</sup>**

Solvent	Temperature (°C)	Torque (%)	Viscosity (cP)	Shear Stress (dyn/cm <sup>2</sup> )
Optimized solvent	15.05	48.2	4.83	3.53
	20.10	40.9	4.09	2.99
	25.00	35.1	3.51	2.57
	30.00	30.5	3.07	2.23
	35.10	26.8	2.69	1.96
	40.10	23.8	2.38	1.73
-----				
Repeat fresh solvent	15.05	48.6	4.86	3.55
	20.10	41.2	4.12	3.01
	25.08	35.3	3.54	2.59
	30.05	30.6	3.07	2.24
	35.02	26.9	2.69	1.96
	40.10	24.0	2.39	1.74
-----				
Repeat same solvent starting at 40 °C	40.10	23.9	2.39	1.74
	35.08	26.9	2.70	1.98
	30.04	30.6	3.07	2.24
	25.10	35.1	3.52	2.57
	20.10	40.8	4.07	2.99
	15.05	48.4	4.84	3.54

<sup>a</sup>Brookfield LVTDV-II (Serial Number D15869) UL Adapter with heating jacket was used. Precision of viscosity measurement is  $\pm 0.1$  cP.

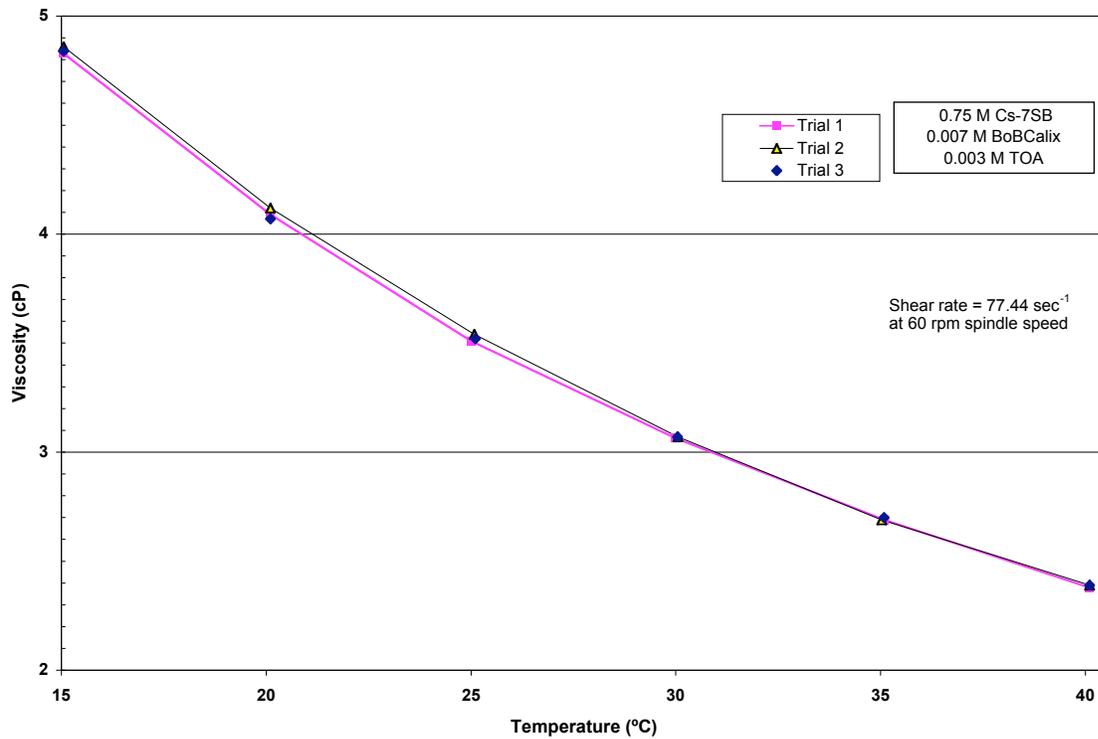


Fig. 22. Solvent viscosity versus temperature.

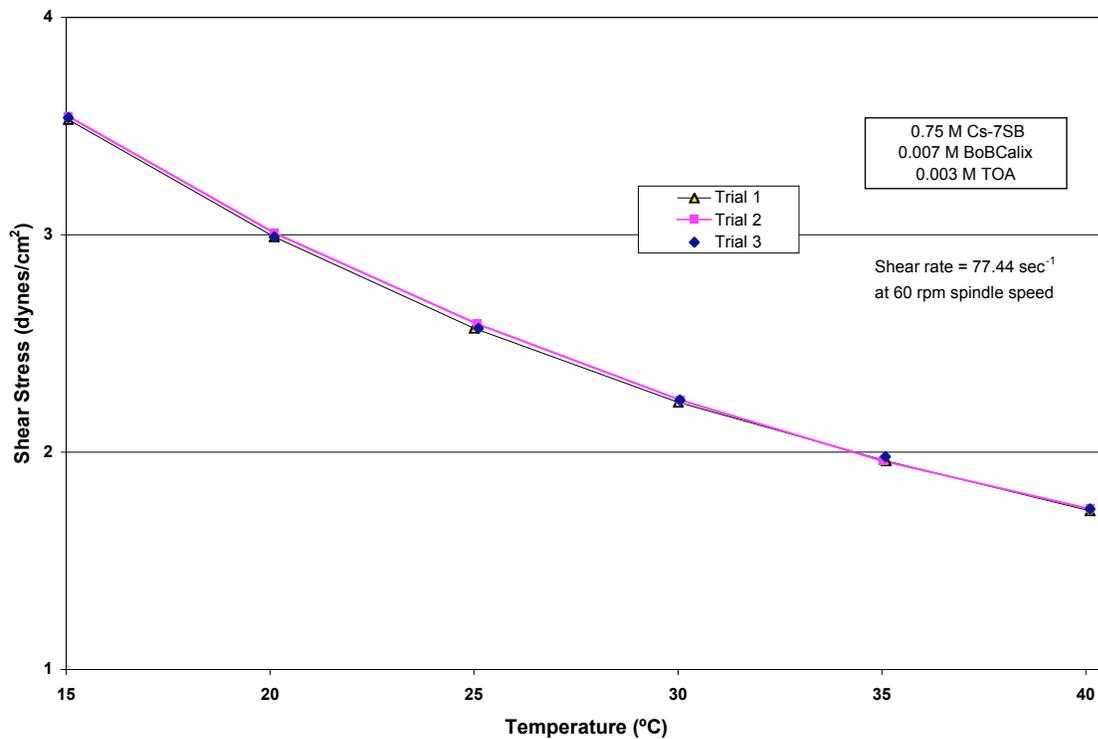


Fig. 23. Solvent shear stress versus temperature.

## 7.6 DISCUSSION AND CONCLUSIONS

### 7.6.1 Dispersion Numbers

The phase-coalescence behavior of the optimized CSSX solvent in contact with aqueous process solutions was characterized by dispersion numbers, as needed for centrifugal-contactors design. The criteria required the solvent dispersion number be greater than or equal to  $4 \times 10^{-4}$  when contacted with the waste simulant, scrub, and strip solutions at the baseline flowsheet O:A ratios [20]. Table 48 summarizes the dispersion numbers obtained for optimized solvent contacted with waste simulant and scrub and strip solutions at 25 °C. It may be seen that these values all meet the criteria. Within the usual wide variability of such results, the values also compare favorably with the dispersion numbers obtained for the previous test solvents (portion of the table below the dashed line) taken at ambient laboratory temperature for solvent selection (see Chapter 2). For extraction contacts, the dispersion numbers covered the range of dispersion numbers obtained for all of the previous test solvents but were in the range of acceptability defined in the composition criteria. For the scrub and strip contacts, the optimized

**Table 48. Dispersion numbers for CSSX solvent extraction, scrub, and stripping**

Solvent <sup>a</sup>	Simulant/solvent dispersion number	Scrub/solvent dispersion number	Strip/solvent dispersion number
Optimized solvent trial 1 (#1)	0.00143	0.00107	0.00108
Optimized solvent trial 1 (#2)	0.00137	0.00104	0.00119
Optimized solvent trial 2 (#1)	0.00100		
Optimized solvent trial 2 (#2)	0.00121		
Optimized solvent trial 3 (#1)	0.00052		
Optimized solvent trial 3 (#2)	0.00048		
-----			
Previous baseline solvent	0.00149	0.00096	0.00115
B001107-3-1	0.00075	0.00102	0.00091
B001107-3-2	0.00056	0.00070	0.00078
B001107-3-3	0.00102	0.00052	0.00088
B001107-3-4	0.00102	0.00053	0.00094
B001107-3-5	0.00118	0.00050	0.00088
B001107-3-6	0.00105	0.00059	0.00075
B001107-3-7	0.00125	0.00058	0.00085
B001107-3-8	0.00120	0.00062	0.00054
B001107-3-9	0.00141	0.00041	0.00051

<sup>a</sup>Optimized solvent was run at 25 °C. Data below the dashed line were collected at ambient laboratory temperature, as taken from Chapter 2 (Table 10).

solvent gave comparable, if not better, dispersion numbers.

Earlier, a gel-like formation was described that occurred during the extraction contacts using the optimized solvent. The formation of the gel-like material was not predictable, and it occurred at least once at each test temperature and in either or both of the two tubes used. Attempts to cause the occurrence of the gel-like material were inconclusive; no specific triggering event or required condition was found.

## 7.6.2 Solvent Density

The density of the optimized solvent is 0.8516 g/cm<sup>3</sup> at 25 °C which is comparable to the density at 25.6 °C for the solvent compositions measured previously that are close in composition to the optimized solvent as shown below in Table 49. The Cs-7SB contributes the most to the changes in total solvent density among the different formulations and the three formulations with 0.75 M Cs-7SB have densities very close to the optimized solvent, as expected.

**Table 49. Comparison of CSSX solvent densities**

Solvent	[BOBCalixC6] (M)	[Cs-7SB] (M)	[TOA] (M)	Density at 25 °C (g/cm <sup>3</sup> )
Optimized solvent	0.007	0.75	0.003	0.8516
Original solvent	0.010	0.50	0.001	0.8100
B001107-3-1	0.010	0.65	0.001	0.8395
B001107-3-2	0.008	0.65	0.001	0.8395
B001107-3-3	0.010	0.75	0.001	0.8531
B001107-3-4	0.008	0.75	0.001	0.8525
B001107-3-5	0.006	0.75	0.001	0.8516
B001107-3-6	0.008	0.85	0.001	0.8644
B001107-3-7	0.006	0.85	0.001	0.8632
B001107-3-8	0.008	1.00	0.001	0.8819
B001107-3-9	0.006	1.00	0.001	0.8951

### 7.6.3 Solvent Viscosity

The optimized solvent viscosity also compares well with the viscosities measured for the same test solvents listed above with similar Cs-7SB content as shown in Table 50.

**Table 50. Comparison of CSSX solvent viscosities**

Solvent	Temperature (°C)	Viscosity (cP)
Optimized solvent	15.05	4.83
	20.10	4.09
	25.00	3.51
	30.00	3.07
	35.10	2.69
	40.10	2.38
B001107-3-3	20.00	4.31
	25.00	3.69
	30.02	3.19
	35.08	2.81
	40.00	2.49
B001107-3-4	20.00	4.17
	25.00	3.61
	30.00	3.12
	35.00	2.74
	40.02	2.44
B001107-3-5	20.00	4.12
	25.00	3.57
	30.00	3.11
	35.02	2.70
	40.02	2.40

## 8. CONCLUSIONS

### 8.1 OVERALL ASSESSMENT

As necessitated by the supersaturation of the previous CSSX baseline solvent by the calixarene extractant, the purpose of this investigation was to optimize the solvent composition and to measure key chemical and physical properties related to its performance. This purpose has been fulfilled. Overall, it may be said that the optimization of the solvent composition has reduced the overall technical risk in meeting processing requirements using the CSSX process. Experimental results indicate that the changed solvent composition shifted various process performance measures incrementally, some with minor compromise and some with real improvement. A greater understanding of solvent properties and process performance has been obtained, and the precision with which performance can be predicted has been increased.

### 8.2 EVALUATION OF RESULTS

The optimization of the solvent composition specifically reduced technical risk by ensuring the integrity of the solvent with regard to crystallization of BOBCalixC6, to third-phase formation, and to the effects of impurities. Based on an established set of criteria [20], a matrix of trial concentrations of the baseline solvent components was examined toward the objective of a new, optimum solvent composition. No new constituents were added to the solvent; only the component concentrations were changed. The results led to a straightforward recommendation of a new baseline solvent having the following component concentrations in Isopar<sup>®</sup> L diluent: 0.007 M BOBCalixC6 extractant, 0.75 M Cs-7SB modifier, and 0.003 M TOA stripping aid. This composition met all of the criteria with regard to BOBCalixC6 solubility, third-phase formation, cesium batch distribution ratios, calculated flowsheet robustness, coalescence rate, and solvent density. Acceptable compromises were made in flowsheet robustness and solvent density, with no impact on process goals. Improved resistance to third-phase formation allows the process to operate at lower temperatures (as low as 11 °C) compared with the previous baseline solvent (20 °C), a significant advantage. In addition, the reduction of the concentration of the expensive BOBCalixC6 extractant implies a reduction in the total materials cost of the solvent by approximately 16%. Finally, the higher TOA concentration decreases the risk that buildup of minor anionic species in the solvent could impact stripping performance.

Further data were collected to characterize the performance of the optimized solvent more thoroughly and to ensure that the optimization procedure did not unexpectedly produce unacceptable changes in process performance. Experiments specifically dealt with the temperature dependence of  $D_{Cs}$  in extraction, scrubbing, and stripping (ESS); ESS performance on recycle; partitioning of BOBCalixC6, Cs-7SB, and TOA to aqueous process solutions; partitioning of organic anions; distribution of metals; solvent phase separation at low temperatures; solvent stability to elevated temperatures; and solvent

density and viscosity. In general, these system properties were changed only incrementally by solvent optimization, as judged from data presented earlier [11]. The temperature dependence of cesium distribution was found to exhibit approximately the same tendency toward decreasing extraction strength with increasing temperature as the former baseline solvent. This property may be used to advantage to increase extraction efficiency by cooling the extraction section and to increase stripping efficiency by warming the stripping section. New parameters were measured for quantifying the temperature dependence of cesium distribution in extraction, scrubbing, and stripping stages. Better measurements of the partitioning of the solvent components now allow a more confident assertion to be made that the solubility losses of solvent components to the aqueous phase are acceptable within the goal of a maximum of one solvent replacement per year. Some uncertainty remains with regard to the exact loss rate of the modifier, but loss of the expensive calixarene was shown to be definitely negligible. Thus, this conclusion has impact on methods for solvent recovery in that the major expected loss pathway is entrainment, which may be dealt with by mechanical methods. No changes in qualitative conclusions regarding the impacts of minor organic or metallic components on process performance have been found for the optimized solvent. Limited thermal-stability experiments again confirm earlier conclusions concerning the high stability of the solvent. A thermal-chemical stability of the solvent of more than 977 days at the maximum normal operating temperature of 35 °C is indicated by the data. A more focused examination of phase stability at low temperatures was necessitated by observation of unusual ESS behavior on batches of optimized CSSX solvent shipped to other laboratories. It was confirmed from earlier indications [11] that the solvent splits into two phases on storage at low temperatures, conditions expected during shipment or outside storage in the winter, necessitating warming to room temperature and remixing before use. Overall, solvent performance was found to be similar to that of the former baseline solvent, with no issues raised concerning unexpected phenomena.

## **8.3 RECOMMENDATIONS FOR FUTURE WORK**

### **8.3.1 Summary Remarks**

From the perspective of a year and a half since the previous assessment of needs for research and development in the area of CSSX chemistry [11], it is instructive to examine current needs. In particular, Chapter 9 of the previous report enumerated nine areas of possible investigation. These areas were listed under nine secondary headings similar to those given below. Additional information on potential needs may be found in FY 2002 program planning [18] and in documentation issued in connection with the solicitation for design, construction, and commissioning of the SRS Salt Waste Processing Facility [42].

### **8.3.2 Solvent Composition**

The first need identified was for solvent optimization [11], which has now been fulfilled. Nevertheless, it may still be worthwhile to pursue additional measurements on BOBCalixC6 solubility

with resolve to continue tests until true equilibrium is reached. The needed measurement time is perhaps a year or more. In addition, it would be valuable to understand if the solubility is impacted by variables such as TOA and aqueous-phase composition. Given the rate of diluent evaporation recently measured [43], possible questions on the environmental acceptability of hydrocarbon emissions or on the ease of process control could motivate consideration of the use of less volatile diluents. Finally, alternative calixarenes are being developed that behave similarly to BOBCalixC6 but have improved solubility [44]. A particularly promising example is calix[4]arene-bis(2-ethylhexylbenzo-crown-6), which has the same framework structure as BOBCalixC6, but with alternative alkyl groups.

### **8.3.3 Actinide and Strontium Extraction**

It would be an obvious advantage toward an overall footprint reduction in the Salt Processing Facility if the CSSX process could also remove the traces of actinides and strontium from the waste. Based on current data, actinides are not significantly extracted by the CSSX solvent [11,40]. A project is under way to examine whether new solvent-extraction chemistry may be developed to remove actinides and strontium from alkaline high-level waste such as that stored at the SRS [45]. This might be accomplished by developing a new solvent and corresponding flowsheet to operate in tandem with the CSSX process. Or possibly the CSSX solvent chemistry may be augmented in a way that enables it to extract cesium, actinides, and strontium simultaneously.

### **8.3.4 Radiation Stability**

Testing in FY 2001 on the previous baseline solvent indicated no significant technical risks due to radiation-induced degradation of the CSSX solvent components [11–14]. In support of this conclusion, an encouraging review of the literature [46] recently suggested that the rate of degradation of the solvent components should be no higher than 1% per year. Although these studies reduce the urgency for further examination of this issue, it remains desirable to pursue unanswered questions. That same literature review [46] also suggested that the aging of the solvent under process conditions should yield a complex mixture of possible organic degradation products that might not wash out. Only two key degradation products have so far been identified, dioctylamine and 4-*sec*-butylphenol [11–14], and these were fairly predictable. There remain the questions of how these products may further react and whether other, less obvious, products are also formed. An open issue exists as to the impact of slow degradation processes that occur after an initial irradiation period [11]. A further question pertains to whether the effects of irradiation differ between static batch tests and the dynamic flowsheet in which the solvent cycles between alkaline and acid conditions. The present report has provided no new data on radiation degradation, and little new data have become available in the past year. Although the risk from radiolysis effects appears low, further radiation experiments to provide data on the optimized solvent would be helpful, especially from the point of view of solvent aging and possible impurity buildup (see section 8.3.7 below).

### 8.3.5 Thermal Stability

Static tests continue to show the high chemical and thermal stability of the CSSX, as verified herein and elsewhere [47] for the optimized solvent. As pointed out above, a recent review [46] suggests the solvent should have adequate chemical stability in terms of the rate of breakdown of the solvent components. Nevertheless, the same general questions remain as were identified above in the case of radiation stability. Such questions pertain to the reactions of dioctylamine and 4-*sec*-butylphenol, the formation of other as-yet unidentified degradation products, the difference between static and dynamic behavior, and the effects of solvent aging. In particular, it continues to be desirable to understand TOA degradation, particularly under acidic conditions. Earlier work showed that TOA is the most easily degraded solvent component, with deleterious consequences for stripping [11].

### 8.3.6 Solvent Cleanup

As previously recommended [11], it would be prudent to prepare for the possibility (see below) that strongly lipophilic anions accumulate in the solvent and eventually overcome the ability of TOA to suppress their harmful effect on stripping. In the work reported herein, limited data were collected to show that the effect of small amounts of dibutylphosphate and dodecanoate was negligible, as expected. Whereas dibutylphosphate is expected to be removed easily by a sodium hydroxide wash step, surfactants having more than 12 carbons are sufficiently lipophilic that their removal will be incomplete by washing [11]. Hence, alternative solvent cleanup methods, such as anion exchange, should be further developed as a ready solution to potential difficulties.

### 8.3.7 Minor Species

In simple batch contacting, it was found herein that minor organic and inorganic species pose no particular recognizable risks based on current knowledge of the waste composition, solvent breakdown products, the distribution behavior of minor species, and available solvent-cleanup methods. This limited conclusion agrees with the results of more extensive testing with the previous baseline solvent, including results from batch tests with waste simulant [11] and from contactor tests with simulant [16,48] and with real waste [17,49] over a relatively small number of cycles. On the other hand, experience in solvent-extraction hydrometallurgy shows that long-term operation generally leads to buildup of species that can eventually impact the performance of a process [50]. Fortunately, the types of problems that may be encountered (e.g., poor phase disengagement, interfacial crud, or loss of extraction and stripping performance) generally yield to acceptable technical solutions. It may be expected that the impact to schedule and facility cost will decrease the earlier the problems are recognized and dealt with. Thus, the more that is known regarding the behavior of minor species prior to facility design, the lower the technical risk will be. Accordingly, contactor tests with long run times using real waste are especially recommended. Given that the solvent will be cycled approximately 3000 times in a year, tests running at least 300 cycles would start to be fruitful in revealing potential problems that may be encountered over

the course of operating a plant for a full year. Thus far, flowsheet tests with real waste have been carried out for only ~1% of the number of annual cycles. In addition, analysis of the wastes for lipophilic organic species should continue, as should study of the fate of surfactant species in the flowsheet. Certain metals such as technetium should be further studied to understand observed behavior in contactor testing. As pointed out above, it does not appear that actinides [40] nor any metals other than the alkali metals are extracted to a significant degree by the pristine CSSX solvent [11]. An unanswered question, though, is how minor waste components distribute when the solvent is aged from extended use and presumably accumulates organic species that do not wash out. For example, do degradation products or surfactant species that build up over a year begin to extract other metals? Such questions suggest the need for tests designed to simulate aging and to reveal how the aged solvent behaves, particularly with regard to the buildup of minor components and their effects.

### **8.3.8 Fate of Trimethylamine**

Trimethylamine is a minor component expected at low concentrations in the waste feed. Its origin is thought to be the breakdown of strong-base anion-exchange resins in the waste. In previous tests, trimethylamine was shown to have the potential to build up in a loop between the extraction and scrub sections [11]. Although this species was not observed to cause any particular difficulties in batch tests, more evaluation is needed to definitely establish its fate in the flowsheet and its impacts on process performance.

### **8.3.9 Role of Nitrite**

It has been recently established that impaired stripping associated with high nitrite concentrations in certain simulant testing [11] was caused by a surfactant added to the reagent sodium nitrite used to make the simulants [41]. The presence of nitrite as nitrous acid was also shown not to increase the already low risk of nitration of solvent components in scrubbing [47]. Hence, the effects of nitrite appear reasonably minimal. It should be noted, however, that nitrous acid is generated from co-extracted nitrite as the solvent moves from the extraction section into the scrubbing section. As nitrite is a reactive species [46,47], its continuous generation in the flowsheet could contribute to more rapid solvent aging effects than static tests indicate, as nitrous acid quickly dissipates in a static test [47].

### **8.3.10 Modeling**

Progress has been made in modeling the CSSX process using the optimized solvent system, where it has been possible to predict with reasonable accuracy the cesium distribution ratios on variable aqueous-feed composition [39]. It is now desirable to factor in the effect of certain minor components, variation of the concentration of solvent components, and temperature variation. Data on the partitioning of Cs-7SB and TOA presented in this report together with data on diluent evaporation [42] reveal that variation of both the relative and absolute concentrations of the solvent components may be expected in normal process operation. It would therefore be helpful if the effects of such variation were easily predicted.

Acid extraction by TOA needs to be studied and incorporated into the model, as this phenomenon affects how the cesium distribution ratio changes from stage to stage in scrubbing and stripping. In terms of making the model more accessible, a convenient user interface is needed, and the equilibrium model must be incorporated into a flowsheet model.

## 9. REFERENCES

1. P. V. Bonnesen, L. H. Delmau, B. A. Moyer, and R. A. Leonard, "A Robust Alkaline-Side CSEX Solvent Suitable for Removing Cesium from Savannah River High Level Waste," *Solvent Extr. Ion Exch.* **18** (6), 1079–1107 (2000).
2. B. A. Moyer, P. V. Bonnesen, R. A. Sachleben, and D. J. Presley, "Solvent and Process for Extracting Cesium from Alkaline Waste Solutions," U.S. Patent 6,174,503, January 16, 2001.
3. R. A. Dimenna et al., *Bases, Assumptions, and Results of the Flow Sheet Calculations for the Decision Phase Salt Disposition Alternatives*, WSRC-RP-99-00006, Rev. 3, Westinghouse Savannah River Company, Aiken, South Carolina, May 2001.
4. *Savannah River Site Salt Processing Alternatives Final Supplemental Environmental Impact Statement (EIS)*, DOE/EIS-0082-S2D, U.S. Department of Energy, Aiken, South Carolina, July 20, 2001.
5. *Federal Register*, **66** (201), 52752–52756, October 17, 2001.
6. National Research Council, Committee on Radionuclide Separation Processes for High-Level Waste at the Savannah River Site, *Research and Development on a Salt Processing Alternative for High-Level Waste at the Savannah River Site*, National Academy Press, Washington, D.C., 2001.
7. H. Harmon, S Schlahta, D. Wester, J. Walker, S. Fink, and M. Thompson, *Tanks Focus Area Savannah River Site Salt Processing Project Research and Development Summary Report*, TFA-0105, Pacific Northwest National Laboratory, Richland, Washington, May 2001.
8. J. T. Case, J. G. Burritt, J. L. Kovach, R. W. Kupp, R. P. Palluzi, L. L. Tavlarides, and R. F. Vance, *Evaluation of Alternatives for Salt Waste Processing at the Savannah River Site*, TAT Report, Rev. H., Savannah River Salt Processing Project Technical Advisory Team, U.S. Department of Energy, May 31, 2001.
9. K. Lang, W. F. Spader, K. Picha, and K. Gerdes, *Final Report on the Salt Processing Project Technology Selection, Technical Working Group*, U.S. Department of Energy, June 2001.
10. M. Frei, L. Erickson, B. Smith, C. Hansen, and T. Fryberger, *Salt Processing Project Management Review Board Summary Report*, U.S. Department of Energy, May 24, 2001.
11. B. A. Moyer, S. D. Alexandratos, P. V. Bonnesen, G. M. Brown, J. E. Caton, Jr., L. H. Delmau, C. R. Duchemin, T. J. Haverlock, T. G. Levitskaia, M. P. Maskarinec, F. V. Sloop, Jr., and C. L. Stine, "Caustic-Side Solvent Extraction Chemical and Physical Properties: Progress in FY 2000 and FY 2001," Report ORNL/TM-2001/285, Oak Ridge National Laboratory, Oak Ridge, Tennessee, February 2002.

12. R. A. Peterson, T. L. White, S. Crump, and L. H. Delmau, *Solvent Extraction External Radiation Stability Testing*, WSRC-TR-2000-00413, Rev. 0, Westinghouse Savannah River Company, Aiken, South Carolina, November 20, 2000.
13. R. A. Peterson, T. L. White, and N. E. Gregory, *Solvent Extraction External Irradiation Update*, SRT-LWP-2000-00101, Westinghouse Savannah River Company, Aiken, South Carolina, June 16, 2000.
14. R. D. Spence, L. N. Klatt, L. H. Delmau, F. V. Sloop, Jr., P. V. Bonnesen, and B. A. Moyer, *Batch-Equilibrium Hot-Cell Tests of Caustic-Side Solvent Extraction (CSSX) with SRS Simulant Waste and Internal <sup>137</sup>Cs Irradiation*, ORNL/TM-2001/49, Oak Ridge National Laboratory, Oak Ridge, Tennessee, September 2001.
15. J. F. Birdwell, Jr., and R. L. Cummings, *Irradiation Effects on Phase-Separation Performance Using a Centrifugal Contactor in a Caustic-Side Solvent Extraction Process*, ORNL/TM-2001/91, Oak Ridge National Laboratory, Oak Ridge, Tennessee, August 2001.
16. R. A. Leonard, S. B. Aase, H. A. Arafat, D. B. Chamberlain, C. Conner, M. C. Regalbuto, and G. F. Vandegrift, *Multi-day Test of the Caustic-Side Solvent Extraction Flowsheet for Cesium Removal from a Simulated SRS Tank Waste*, ANL-02/11, Argonne National Laboratory, Argonne, Illinois, January 15, 2002.
17. S. G. Campbell, M. W. Geeting, C. W. Kennell, J. D. Law, R. A. Leonard, M. A. Norato, R. A. Pierce, T. A. Todd, D. D. Walker, and W. R. Wilmarth, *Demonstration of Caustic-Side Solvent Extraction with Savannah River Site-High-Level Waste*, WSRC-TR-2001-00223, Rev. 0, Westinghouse Savannah River Company, Aiken, South Carolina, April 19, 2001.
18. H. Harmon, R. Leugemors, S. Schlahta, S. Fink, M. Thompson, and D. Walker, *Savannah River Site Salt Processing Project: FY 2002 Research and Development Program Plan*, PNNL-13707, Rev. 1, Pacific Northwest National Laboratory, Richland, Washington, December 2001.
19. H. Harmon, S. Schlahta, J. Walker, D. Wester, K. Rueter, and S. Fink, *Tanks Focus Area, Savannah River Site Salt Processing Project, Research and Development Program Plan*, PNNL-13253, Rev. 1, Pacific Northwest National Laboratory, Richland, Washington, November 2000.
20. L. N. Klatt, *Criteria for Optimum Composition of the Caustic-Side Solvent Extraction (CSSX) Solvent*, CERS/SR/SX/025, Rev. 0, Nuclear Science and Technology Division, Oak Ridge National Laboratory, Oak Ridge, Tennessee, August 2001.

21. L. N. Klatt, J. F. Birdwell, Jr., P. V. Bonnesen, L. H. Delmau, L. J. Foote, D. D. Lee, R. A. Leonard, T. G. Leviskaia, M. P. Maskarinec, and B. A. Moyer, *Caustic-Side Solvent Extraction Solvent-Composition Recommendation*, CERS/SR/SX/026, Rev. 0, Nuclear Science and Technology Division, Oak Ridge National Laboratory, Oak Ridge, Tennessee, November 8, 2001.
22. L. N. Klatt, J. F. Birdwell, Jr., P. V. Bonnesen, L. H. Delmau, L. J. Foote, D. D. Lee, R. A. Leonard, T. G. Leviskaia, M. P. Maskarinec, and B. A. Moyer, *Caustic-Side Solvent Extraction Solvent-Composition Recommendation*, ORNL/TM-2001/258, Oak Ridge National Laboratory, Oak Ridge, Tennessee, January 2001.
23. R. A. Peterson, *Preparation of Simulated Waste Solutions for Solvent Extraction Testing*, WSRC-RP-2000-00361, Rev. 0, Westinghouse Savannah River Company, Aiken, South Carolina, May 2000.
24. R. A. Leonard, "Solvent Characterization Using The Dispersion Number," *Sep. Sci. Technol.* **30** (7–9), 1103–1122 (1995).
25. ASTM Standard D 891–95, "Standard Test Method for Specific Gravity, Apparent, of Liquid Industrial Chemicals," American Society for Testing and Materials, Philadelphia, 2000.
26. ASTM Standard D 1429–95, "Standard Test Methods for Specific Gravity of Water and Brine," American Society for Testing and Materials, Philadelphia, 2000.
27. ASTM Standard E 542–00, "Standard Practice for Calibration of Laboratory Volumetric Apparatus," American Society for Testing and Materials, Philadelphia, 2000.
28. ASTM Standard D 2196–99, "Standard Test Method for Rheological Properties of Non-Newtonian Materials by Rotational (Brookfield type) Viscometer," American Society for Testing and Materials, Philadelphia, 1999.
29. "The Brookfield Digital Viscometer Model DV-II Operating Instructions," Manual No. M/85-160-F, Brookfield Engineering Laboratories, Inc., Stoughton, Massachusetts, 1985.
30. ASTM Standard D 971–99a, "Standard Test Method for Interfacial Tension of Oil Against water by the Ring Method," American Society for Testing and Materials, Philadelphia, 1999.
31. ASTM Standard D 1331–89, "Standard Test Method for Surface and Interfacial Tension of Solutions of Surface-Active Agents," American Society for Testing and Materials, Philadelphia, 1989.

32. *CRC Handbook of Chemistry and Physics*, 66<sup>th</sup> ed., CRC Press, Boca Raton, Florida, 1985, p. 32.
33. R. A. Leonard and M. C. Regalbuto, "A Spreadsheet Algorithm for Stagewise Solvent Extraction," *Solvent Extr. Ion Exch.* **12** (5), 909–930 (1994).
34. J. F. Birdwell, Jr., and K. K. Anderson, *Evaluation of 5-cm Centrifugal Contactor Hydraulic and Mass Transfer Performance for Caustic-Side Solvent Extraction of Cesium*, ORNL/TM-2001/137, Oak Ridge National Laboratory, Oak Ridge, Tennessee, August 2001.
35. J. F. Birdwell, Jr., "Throughput Performance of a Fully-Pumping 5-cm Centrifugal Contactor with Vane Modifications," Tanks Focus Area (TFA) Plan of the Week (POW) Technical Discussion, Oak Ridge National Laboratory, Oak Ridge, Tennessee, November 5, 2001.
36. J. D. Law, R. D. Tillotson, and T. A. Todd, "Evaluation of the Hydraulic Performance and Mass Transfer Efficiency of the CSSX Process with the Optimized Solvent in a Single Stage of 5.5-cm Diameter Centrifugal Contactor," INEEL/EXT-02-01109, Idaho National Engineering and Environmental Laboratory, Idaho Falls, Idaho, September 2002.
37. L. H. Delmau, L. J. Foote, P. V. Bonnesen, H. Jennings, T. G. Levitskaia, M. P. Maskarinec, B. A. Moyer, D. D. Lee, K. K. Anderson, and L. N. Klatt, "Solvent Optimization," TFA POW Technical Discussion, Oak Ridge National Laboratory, Oak Ridge, Tennessee, October 29, 2001.
38. J. F. Birdwell, Jr., K. K. Anderson, and D. E. Hobson, *Investigation of Emulsion Formation in Solvent Washing in the Caustic-Side Solvent Extraction (CSSX) Process*, ORNL/TM-2002/126, Oak Ridge National Laboratory, Oak Ridge, Tennessee, June 2002.
39. L. H. Delmau, D. A. Bostick, T. J. Haverlock, and B. A. Moyer, *Caustic-Side Solvent Extraction: Extended Equilibrium Modeling of Cesium and Potassium Distribution Behavior*, ORNL/TM-2002/116, Oak Ridge National Laboratory, Oak Ridge, Tennessee, May 2002.
40. W. R. Wilmarth, V. H. Dukes, J. T. Mills, C. C. DiPrete, and D. P. DiPrete, *Solvent Composition Impacts on the Extraction of Uranium and Plutonium in the Caustic Side Solvent Extraction Process*, WSRC-TR-2002-00060, Westinghouse Savannah River Company, Aiken, South Carolina, January 18, 2002.
41. L. H. Delmau, T. J. Haverlock, and B. A. Moyer, *Caustic-Side Solvent Extraction: Anti-Caking Surfactants Found to Be Cause of Apparent Effect of High Nitrite Concentration on Cesium Stripping*, ORNL/TM-2002/104, Oak Ridge National Laboratory, Oak Ridge, Tennessee, May 2002.

42. *Design, Construction, and Commissioning of a Salt Waste Processing Facility*, Request for Proposal No. DE-RP09-02SR22210, Amendment 002, U. S. Department of Energy, Savannah River Operations Office, Aiken, South Carolina, January 9, 2002.

43. D. D. Lee, J. F. Birdwell, Jr., P. V. Bonnesen, and B. A. Tomkins, *Density Changes in the Optimized CSSX Solvent System*, ORNL/TM-2002/204, Oak Ridge National Laboratory, Oak Ridge, Tennessee, October 2002.

44. B. A. Moyer, P. V. Bonnesen, J. C. Bryan, N. L. Engle, T. J. Keever, T. G. Levitskaia, R. A. Sachleben, R. A. Bartsch, V. S. Talanov, H. W. Gibson, J. W. Jones, and B. P. Hay, *Next Generation Extractants for Cesium Separation from High-Level Waste: From Fundamental Concepts to Site Implementation*, FY 2002 Annual Report, Environmental Management Science Program, August, 2002; posted on the EMSP web site <http://emsp.em.doe.gov/>.

45. L. H. Delmau, K. N. Raymond, and D. T. Hobbs, *Combined Extraction of Cesium, Strontium, and Actinides from Alkaline Media: An Extension of the Caustic-Side Solvent Extraction (CSSX) Process Technology*, FY 2002 Annual Report, Environmental Management Science Program, June, 2002; posted on the EMSP web site <http://emsp.em.doe.gov/>.

46. L. M. Stock, D. M. Camaioni, D. W. Wester, and C. D. Gutsche, *Decomposition Pathways for the Savannah River Site Caustic-Side Solvent Extraction System*, PNNL-13935, Pacific Northwest National Laboratory, Richland, Washington, July 2002.

47. P. V. Bonnesen, F. V. Sloop, Jr., and N. L. Engle, *Stability of the Caustic-Side Solvent Extraction (CSSX) Process Solvent: Effect of High Nitrite on Solvent Nitration*, ORNL/TM-2002/115, Oak Ridge National Laboratory, Oak Ridge, Tennessee, July 2002.

48. M. P. Maskarinec, *Analysis of a Sample of the Solvent Used in the Argonne National Laboratory Multiday Flowsheet Test*, CERS/SR/SX/027, Rev. 0, Chemical Sciences Division and Nuclear Science and Technology Division, Oak Ridge National Laboratory, Oak Ridge, Tennessee, February 19, 2002.

49. S. L. Crump, M. A. Norato, R. A. Pierce, R. J. Ray, D. D. Walker, and T. L. White, *Demonstration of Caustic-Side Solvent Extraction with Savannah River Site High-Level Waste: Results of Organic and Trace Component Analyses*, WSRC-TR-2001-00372, Rev. 0, Westinghouse Savannah River Company, Aiken, South Carolina, December 7, 2001.

50. B. Grinbaum and L. Kogan, "Verification of a Process in a Demonstration Plant: How Long Does it Take to Find All the Problems?" Proc. Internat. Solvent Extraction Conf. (ISEC 2002), Cape Town, South Africa, Mar. 17–21, 2002, K. C. Sole P. M. Cole, J. S. Preston, D. J. Robinson, Eds., Chris van Rensburg Publications, Melville, South Africa, 2002; Vol. 2, pp. 1408–1413.



## Appendix A

PREDICTED  $D_{Cs}$  VALUES USING THE log VERSUS log RELATIONSHIPS BETWEEN  $D_{Cs}$  VALUES AND BOBCalixC6 AND Cs-7SB MODIFIER CONCENTRATIONS

**Table A.1. Predicted  $D_{Cs}$  values**

Process step	$D_{Cs}$		
	[Cs-7SB] = 0.70 M	[Cs-7SB] = 0.75 M	[Cs-7SB] = 0.80 M
<b>[BOBCalixC6] = 6.5 mM</b>			
Extraction	12.76	13.08	13.40
Scrub no. 1	1.16	1.22	1.28
Scrub no. 2	1.21	1.26	1.31
Strip no. 1	0.91	0.096	0.101
Strip no. 2	0.054	0.057	0.059
Strip no. 3	0.043	0.045	0.047
Strip no. 4	0.037	0.039	0.041
<b>[BOBCalixC6] = 7.0 mM</b>			
Extraction	13.77	14.13	14.48
Scrub no. 1	1.26	1.32	1.38
Scrub no. 2	1.30	1.35	1.40
Strip no. 1	0.099	0.104	0.109
Strip no. 2	0.059	0.062	0.065
Strip no. 3	0.047	0.049	0.051
Strip no. 4	0.040	0.043	0.045
<b>[BOBCalixC6] = 7.5 mM</b>			
Extraction	14.78	15.18	15.56
Scrub no. 1	1.35	1.42	1.49
Scrub no. 2	1.39	1.45	1.50
Strip no. 1	0.106	0.112	0.117
Strip no. 2	0.060	0.070	0.070
Strip no. 3	0.051	0.053	0.055
Strip no. 4	0.044	0.046	0.048



## INTERNAL DISTRIBUTION

1. J. F. Birdwell, Jr.
2. P. V. Bonnesen
3. J. L. Collins
4. R. L. Cummins
- 5-7. L. H. Delmau
8. R. D. Hunt
- 9-10. T. J. Keever
11. D. D. Lee
12. M. P. Maskarinec
13. A. J. Mattus
14. C. P. McGinnis
- 15-16. B. A. Moyer
17. F. V. Sloop, Jr.
18. R. D. Spence
19. J. F. Walker, Jr.
20. J. S. Watson
21. ORNL Central Research Library
22. Laboratory Records, RC
23. Laboratory Records, OSTI

## EXTERNAL DISTRIBUTION

24. J. T. Carter, Westinghouse Savannah River Company, P.O. Box 616, Building 766-H, Aiken, SC 29808
25. D. Chamberlain, Argonne National Laboratory, Building 205, 9700 South Cass Avenue, Argonne, IL 60439
26. N. F. Chapman, Westinghouse Savannah River Company, P.O. Box 616, Building 704-3N, Aiken, SC 29808
27. W. D. Clark, U.S. Department of Energy, Savannah River Operations Office, Bldg. 704-3N, Aiken, SC 29808
28. C. Conner, Argonne National Laboratory, Building 205, 9700 South Cass Avenue, Argonne, IL 60439

29. R. G. Edwards, Westinghouse Savannah River Company, P.O. Box 616, Building 704-3N, Aiken, SC 29808
30. S. D. Fink, Westinghouse Savannah River Company, P.O. Box 616, Building 773-A, Aiken, SC 29808
31. H. D. Harmon, Tank Focus Area Salt Processing Program, P.O. Box 616, Building 704-3N, Aiken, SC 29808
32. R. T. Jones, Westinghouse Savannah River Company, P.O. Box 616, Building 704-3N, Aiken, SC 29808
33. L. N. Klatt, 111 Carnegie Drive, Oak Ridge, TN 37830
34. R. A. Leonard, 224 Franklin Ave, River Forest, IL 60305
35. T. G. Levitskaia, Pacific Northwest National Laboratory, P.O. Box 999; MSIN P7-22, Richland, WA 99352
36. J. R. Noble-Dial, U.S. Department of Energy, Oak Ridge Operations Office, P.O. Box 2001, Oak Ridge, TN 37831-8620
37. M. Norato, Westinghouse Savannah River Company, P.O. Box 616, Building 773-A, Aiken, SC 29808
38. R. Pierce, Westinghouse Savannah River Company, P.O. Box 616, Building 773-A, Aiken, SC 29808
39. S. N. Schlahta, Battelle, Pacific Northwest National Lab, P.O. Box 999 / MS K9-14 Richland, WA 99352
40. P. C. Suggs, U.S. Department of Energy, Savannah River Operations Office, P.O. Box A, Building 704-3N, Aiken, SC 29808
41. W. L. Tamosaitis, Westinghouse Savannah River Company, P.O. Box 616, Building 773-A, Aiken, SC 29808
42. M. C. Thompson, Westinghouse Savannah River Company, P.O. Box 616, Building 773-A, Aiken, SC 29808

43. T. A. Todd, Idaho National Engineering & Environmental Laboratory, Building 637, MS-5218, Idaho Falls, ID 834415-5218
44. G. F. Vandegrift, Argonne National Laboratory, Building 205, 9700 South Cass Avenue, Argonne, IL 60439
45. D. D. Walker, Westinghouse Savannah River Company, P.O. Box 616, Building 773-A, Aiken, SC 29808
46. D. Wester, Battelle, Pacific Northwest National Lab, P.O. Box 999 / MS K8-93 Richland, WA 99352
47. Vickie Wheeler, U.S. Department of Energy, Savannah River Operations Office, P.O. Box A, Building 776-H, Aiken, SC 29808
48. W. R. Wilmarth, Westinghouse Savannah River Company, P.O. Box 616, Building 773-A, Aiken, SC 29808
49. Tanks Focus Area Technical Team, c/o B. J. Williams, Pacific Northwest National Laboratory, P.O. Box 999, MSIN K9-69, Richland, WA 99352
50. Tanks Focus Area Field Lead, c/o T. P. Pietrok, U.S. Department of Energy, Richland Operations Office, P.O. Box 550, K8-50, Richland, WA 99352
51. Tanks Focus Area Headquarters Program Manager, c/o K. D. Gerdes, DOE Office of Science and Technology, 19901 Germantown Rd., 1154 Cloverleaf Building, Germantown, MD 20874-1290
49. Nicole Simon and Jean-François Dozol, CEA Cadarache, DESD/SEP/LPTE, Bat.326, 13108 St Paul lez Durance Cedex, France
50. Charles Madic, CEA Valrhô-Marcoule, DCC, BP 171, 30207 Bagnols s/Ceze Cedex, France