

Post-Irradiation Examination of Array Targets—Part I

December 2003

Prepared by

**A. S. Icenhour
R. M. Wham
R. R. Brunson
R. R. McMahon**

DOCUMENT AVAILABILITY

Reports produced after January 1, 1996, are generally available free via the U.S. Department of Energy (DOE) Information Bridge:

Web site: <http://www.osti.gov/bridge>

Reports produced before January 1, 1996, may be purchased by members of the public from the following source:

National Technical Information Service
5285 Port Royal Road
Springfield, VA 22161
Telephone: 703-605-6000 (1-800-553-6847)
TDD: 703-487-4639
Fax: 703-605-6900
E-mail: info@ntis.fedworld.gov
Web site: <http://www.ntis.gov/support/ordernowabout.htm>

Reports are available to DOE employees, DOE contractors, Energy Technology Data Exchange (ETDE) representatives, and International Nuclear Information System (INIS) representatives from the following source:

Office of Scientific and Technical Information
P.O. Box 62
Oak Ridge, TN 37831
Telephone: 865-576-8401
Fax: 865-576-5728
E-mail: reports@adonis.osti.gov
Web site: <http://www.osti.gov/contact.html>

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

POST-IRRADIATION EXAMINATION OF ARRAY TARGETS—PART I

A. S. Icenhour
R. M. Wham
R. R. Brunson
R. R. McMahon

Date Published: December 2003

Prepared by
OAK RIDGE NATIONAL LABORATORY
P.O. Box 2008
Oak Ridge, Tennessee 37831-6283
managed by
UT-Battelle, LLC
for the
U.S. DEPARTMENT OF ENERGY
under contract DE-AC05-00OR22725

CONTENTS

	Page
LIST OF FIGURES	v
LIST OF TABLES	vii
ABSTRACT	ix
1. INTRODUCTION	1
2. ARRAY TARGET DESCRIPTION	2
3. ATR IRRADIATION	6
4. TARGET PROCESSING	10
4.1 TARGET-CUTTING JIG	10
4.2 DISSOLVER EQUIPMENT	11
4.3 CAUSTIC DISSOLUTION OF TARGET SECTIONS	12
4.4 ACID DISSOLUTION	14
4.5 DOSIMETER DISSOLUTION	16
5. RESULTS AND DISCUSSION	18
6. SUMMARY	26
REFERENCES	27
APPENDIX A: Detailed Data Sheets for Targets and Dosimeters	29

LIST OF FIGURES

Figure	Page
2.1 Schematic of aluminum-clad target that contains three NpO_2 -Al pellets and a dosimeter package.	3
3.1 Depiction of aluminum basket similar to that used in the array target irradiations.	6
3.2 Depiction of configuration of the 10 vol % and 20 vol % NpO_2 arrays relative to the center of the ATR core.. . . .	7
3.3 Cross section of the ATR core showing position B-10, which was used in the array target irradiation.	8
4.1 Photograph of stainless steel saw jig used to section targets.	10
4.2 Photograph of dissolver used for pellet dissolution.	11
4.3 Typical flowsheet for the caustic dissolution.	13
4.4 Typical flowsheet for the acid dissolution.	15
4.5 Photographs of vials, vial holders, and receptacle used in the dosimeter dissolution.	17
5.1 Percentage of neptunium converted to plutonium as a function of relative power for the targets and dosimeters.	23
5.2 Plutonium-238 production (percentage of total plutonium production) as a function of relative power for the targets and dosimeters.	23
5.3 Plutonium-236 content at discharge from the ATR as a function of relative power for the targets and dosimeters.	24
A.1 Detailed data sheet for target MK-10.4.	31
A.2 Detailed data sheet for target MK-10.6.	32
A.3 Detailed data sheet for target MK-10.2.	33
A.4 Detailed data sheet for target MK-10.1.	34
A.5 Detailed data sheet for target MK-20.4.	35
A.6 Detailed data sheet for target MK-20.5.	36
A.7 Detailed data sheet for target MK-20.6.	37

LIST OF FIGURES (continued)

A.8	Detailed data sheet for target MK-20.2.	38
A.9	Detailed data sheet for target MK-20.1.	39
A.10	Detailed data sheet for dosimeter MK-10.4.	40
A.11	Detailed data sheet for dosimeter MK-10.6.	41
A.12	Detailed data sheet for dosimeter MK-10.1.	42
A.13	Detailed data sheet for dosimeter MK-20.4.	43
A.14	Detailed data sheet for dosimeter MK-20.6.	44
A.15	Detailed data sheet for dosimeter MK-20.2.	45
A.16	Detailed data sheet for dosimeter MK-20.1.	46

LIST OF TABLES

Table	Page
2.1 Summary of fabrication data for 10 vol % NpO ₂ targets	4
2.2 Summary of fabrication data for 20 vol % NpO ₂ targets	5
3.1 Summary of data for the two ATR cycles used to irradiate the array targets	9
5.1 List of the array targets that were processed	19
5.2 Summary of results for array target analysis	20
5.3 Fission products in caustic dejacket stream (ppm) relative to ²³⁸ Pu production	21
5.4 Fission products in acid dissolution stream (ppm) relative to ²³⁸ Pu production	21
5.5 Summary of dosimeter data	22

ABSTRACT

During FY 2001, two arrays, each containing seven neptunium-loaded targets, were irradiated at the Advanced Test Reactor in Idaho to examine the influence of multi-target self-shielding on ^{236}Pu content and to evaluate fission product release data. One array consisted of seven targets that contained 10 vol % NpO_2 pellets, while the other array consisted of seven targets that contained 20 vol % NpO_2 pellets. The arrays were located in the same irradiation facility but were axially separated to minimize the influence of one array on the other. Each target also contained a dosimeter package, which consisted of a small NpO_2 wire that was inside a vanadium container. After completion of irradiation and shipment back to the Oak Ridge National Laboratory, nine of the targets (four from the 10 vol % array and five from the 20 vol % array) were punctured for pressure measurement and measurement of ^{85}Kr . These nine targets and the associated dosimeters were then chemically processed to measure the residual neptunium, total plutonium production, ^{238}Pu production, and ^{236}Pu concentration at discharge. The amount and isotopic composition of fission products were also measured. This report provides the results of the processing and analysis of the nine targets.

1. INTRODUCTION

During FY 2001, two arrays, each containing seven neptunium-loaded targets, were irradiated at the Advanced Test Reactor (ATR) in Idaho. One array consisted of seven targets that contained 10 vol % NpO_2 pellets, while the other array consisted of seven targets that contained 20 vol % NpO_2 pellets. The arrays were located in the same irradiation facility but were axially separated to minimize the influence of one array on the other. This irradiation, which has also been referred to as Phase III irradiations in earlier reports,¹ was performed to examine the influence of multi-target self-shielding on ^{236}Pu content and to evaluate fission product release data. At the completion of the irradiation, the targets were shipped to Oak Ridge National Laboratory (ORNL) for post-irradiation examination.

To date, 9 of the 14 targets have been punctured for the measurement of the internal pressure and fission product gases. The results of these measurements have been reported separately.² The nine targets were subsequently dissolved and analyzed in order to evaluate the ^{238}Pu and ^{236}Pu yields, as well as the nonvolatile fission product yields. This report summarizes the results of the dissolutions. Because efforts are under way to enhance the gas analysis capability, the remaining five targets will be punctured for pressure measurement and then dissolved at a later date. Consequently, these targets will be the subject of a later report.

In the following sections, the array targets, ATR irradiation, and target processing flowsheets are described. Finally, the results of target dissolutions are presented.

2. ARRAY TARGET DESCRIPTION

The array targets consisted of aluminum tubing that contained three NpO_2 -Al pellets and a dosimeter package. The development work for the fabrication of the targets is described in detail in Ref. 1. The pellets were prepared by mixing the desired amount of NpO_2 with aluminum powder and then pressing the mixture to the desired dimensions and density. Pellets that contained 10 and 20 vol % NpO_2 were prepared and then uniaxially pressed to 90% theoretical density. After pressing, the pellets were fired at 350°C, under vacuum, for 3 h to remove stearic acid, which served as a lubricant in the die press. The dosimeter package consisted of a NpO_2 wire that was contained within a vanadium can.

A schematic of the target configuration is shown in Fig. 2.1. Each target had a pellet section, containing three pellets, and a dosimeter section, containing one dosimeter package. Seven of the targets were loaded with 10 vol % NpO_2 pellets, while the other seven were loaded with 20 vol % NpO_2 pellets. The pellet and dosimeter sections, which were separated by an aluminum spacer, were located in the top half of the target. The bottom half of the target contained an aluminum tube spacer that acted as a plenum for fission gas expansion. The plenum was separated from the pellets by a porous aluminum spacer, which allowed fission product gases to expand into the plenum. The pellet and dosimeter sections could be removed from a target by cutting through the solid spacers, which resulted in a pellet section, a dosimeter section, a top aluminum spacer section, and aluminum tube spacer section.

After assembly, a closure weld was performed and the weld area was radiographed. The targets were then hydrostatically compressed at 20,000 psig to ensure that the target tube was in contact with the pellets. The final assembly was then radiographed, and a helium leak test and a dye penetrate check were performed on each target. Tables 2.1 and 2.2 provide summary details about the pellet loading and dimensions for each of the targets irradiated in the ATR.

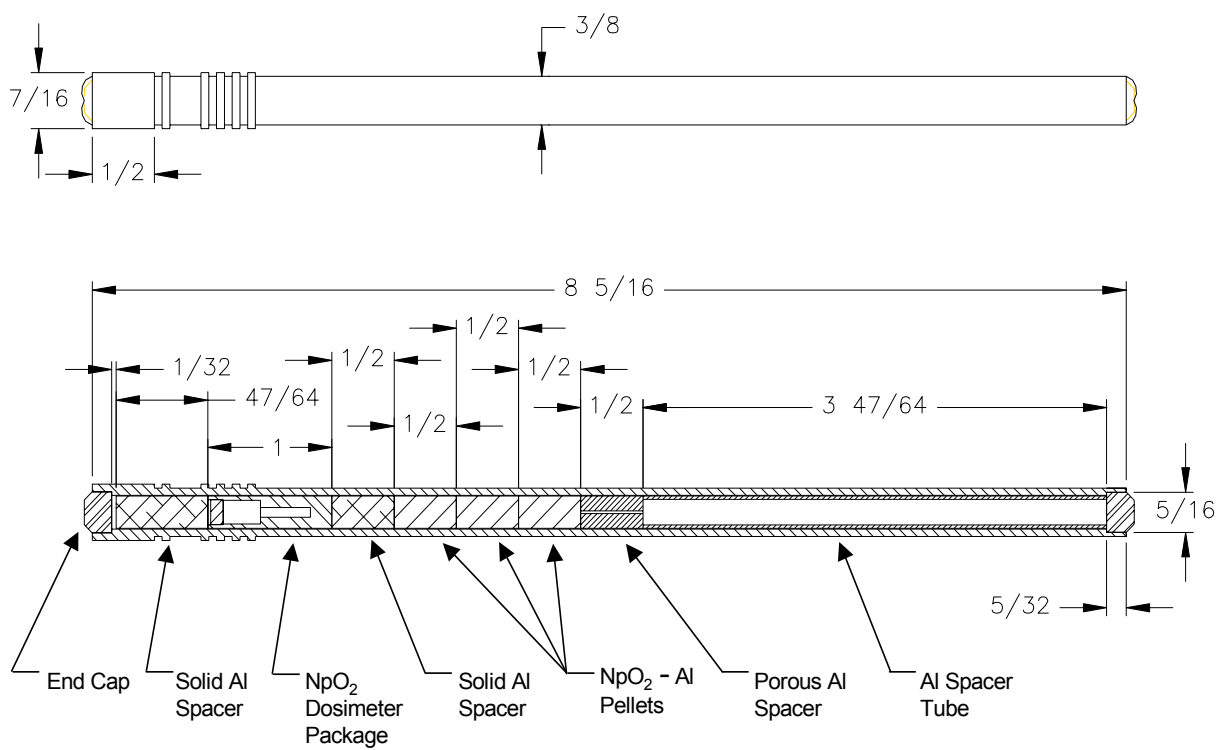


Fig. 2.1. Schematic of aluminum-clad target that contains three NpO₂-Al pellets and a dosimeter package.

Table 2.1. Summary of fabrication data for 10 vol % NpO₂ targets

Target number	Pellet number	Pellet density (g/cm ³)	Fraction of theoretical density	NpO ₂ (vol %)	Pellet dimensions		NpO ₂ (g)	Np metal (g)
					Diameter (in.)	Length (in.)		
MK-10.0	BNP-17	3.13	0.895	10.00	0.25	0.503	0.3902	0.3351
	BNP-1	3.16	0.900	10.00	0.25	0.5	0.3902	0.3351
	BNP-3	3.11	0.891	10.00	0.25	0.505333	0.3901	0.3351
	Dosimeter 0-1						0.001888	0.001668
MK-10.1	BNP-2	3.16	0.905	10.01	0.25	0.497	0.3906	0.3355
	BNP-14	3.14	0.895	10.00	0.25	0.502667	0.3902	0.3351
	BNP-7	3.14	0.896	10.01	0.25	0.502333	0.3907	0.3356
	Dosimeter 0-2						0.001712	0.001512
MK-10.2	BNP-4	3.15	0.897	10.00	0.25	0.501667	0.3902	0.3351
	BNP-16	3.13	0.893	10.00	0.25	0.504167	0.3903	0.3352
	BNP-10	3.12	0.899	10.00	0.25	0.5005	0.3902	0.3351
	Dosimeter 0-3						0.001731	0.001529
MK-10.3	BNP-25	3.15	0.900	10.01	0.25	0.500167	0.3905	0.3354
	BNP-26	3.14	0.900	10.02	0.249833	0.500833	0.3909	0.3357
	BNP-27	3.15	0.903	10.00	0.25	0.498167	0.3902	0.3351
	Dosimeter 0-11						0.001131	0.000999
MK-10.4	BNP-11	3.16	0.904	10.01	0.2495	0.500167	0.3905	0.3354
	BNP-18	3.14	0.894	10.02	0.25	0.503333	0.391	0.3358
	BNP-5	3.15	0.900	10.01	0.2495	0.501833	0.3902	0.3351
	Dosimeter 0-8						0.001744	0.001541
MK-10.5	BNP-6	3.14	0.896	10.00	0.25	0.502167	0.3901	0.3351
	BNP-12	3.13	0.895	9.99	0.25	0.503	0.3899	0.3349
	BNP-8	3.13	0.893	10.03	0.25	0.504167	0.3913	0.3361
	Dosimeter 0-9						0.001993	0.001761
MK-10.6	BNP-15	3.14	0.896	10.00	0.2495	0.504333	0.3901	0.3351
	BNP-23	3.14	0.897	10.00	0.25	0.501667	0.3901	0.3351
	BNP-20	3.13	0.894	10.00	0.25	0.503367	0.3903	0.3352
	Dosimeter 0-10						0.001969	0.001739

Table 2.2. Summary of fabrication data for 20 vol % NpO₂ targets

Target number	Pellet number	Pellet density (g/cm ³)	Fraction of theoretical density	NpO ₂ (vol %)	Pellet dimensions		NpO ₂ (g)	Np metal (g)
					Diameter (in.)	Length (in.)		
MK-20.0	BNP-40	3.82	0.886	20.02	0.25	0.50783	0.7815	0.6712
	BNP-47	3.82	0.887	20.00	0.2505	0.50516	0.7801	0.6700
	BNP-58	3.85	0.889	19.99	0.25	0.5065	0.7802	0.6701
	Dosimeter 0-12						0.001264	0.001117
MK-20.1	BNP-41	3.83	0.890	20.03	0.25	0.506	0.7816	0.6713
	BNP-53	3.83	0.890	19.98	0.25	0.50553	0.7794	0.6694
	BNP-59	3.83	0.892	20.00	0.25	0.50483	0.7806	0.6704
	Dosimeter 0-13						0.002198	0.001942
MK-20.2	BNP-43	3.78	0.878	20.01	0.25	0.51266	0.7808	0.6706
	BNP-52	3.82	0.888	19.99	0.25	0.5065	0.7797	0.6697
	BNP-49	3.83	0.892	20.00	0.25	0.50466	0.7804	0.6703
	Dosimeter 0-14						0.00166	0.001466
MK-20.3	BNP-48	3.84	0.890	20.00	0.25	0.50583	0.7807	0.6705
	BNP-42	3.79	0.880	20.00	0.2495	0.51333	0.7806	0.6704
	BNP-60	3.86	0.895	19.99	0.25	0.50283	0.7798	0.6698
	Dosimeter 0-15						0.002073	0.001831
MK-20.4	BNP-50	3.83	0.889	20.01	0.25	0.50666	0.781	0.6708
	BNP-57	3.87	0.898	20.00	0.25	0.50116	0.7807	0.6705
	BNP-44	3.84	0.892	19.99	0.25	0.50466	0.7801	0.6700
	Dosimeter 0-16						0.001633	0.001443
MK-20.5	BNP-45	3.84	0.892	20.00	0.25	0.50483	0.7804	0.6703
	BNP-51	3.84	0.891	20.00	0.2505	0.50316	0.7804	0.6703
	BNP-55	3.80	0.884	19.99	0.2505	0.50716	0.7798	0.6698
	Dosimeter 0-17						0.001411	0.001246
MK-20.6	BNP-54	3.82	0.888	20.01	0.2505	0.50466	0.7806	0.6704
	BNP-61	3.84	0.890	19.99	0.25	0.5055	0.7799	0.6698
	BNP-56	3.80	0.881	20.01	0.2505	0.509	0.781	0.6708
	Dosimeter 0-18						0.001762	0.001557

3. ATR IRRADIATION

The 14 targets were shipped to the Idaho National Engineering and Environmental Laboratory (INEEL), where they were loaded into an aluminum basket (similar to that depicted in Fig. 3.1), thereby forming two arrays as depicted in Fig. 3.2. The seven 10 vol % targets comprised the upper array, while the seven 20 vol % targets formed the lower array. Note that, as shown in Fig. 3.2, the targets were aligned along an axis relative to the center of the reactor. This orientation was selected to aid in the evaluation of self-shielding by the targets. The arrays were irradiated for two cycles in position B-10 of the ATR (Fig. 3.3), which is a 1.5-in.-diam hole near two control drums on the east side of the reactor. The irradiation data for the two cycles are summarized in Table 3.1.

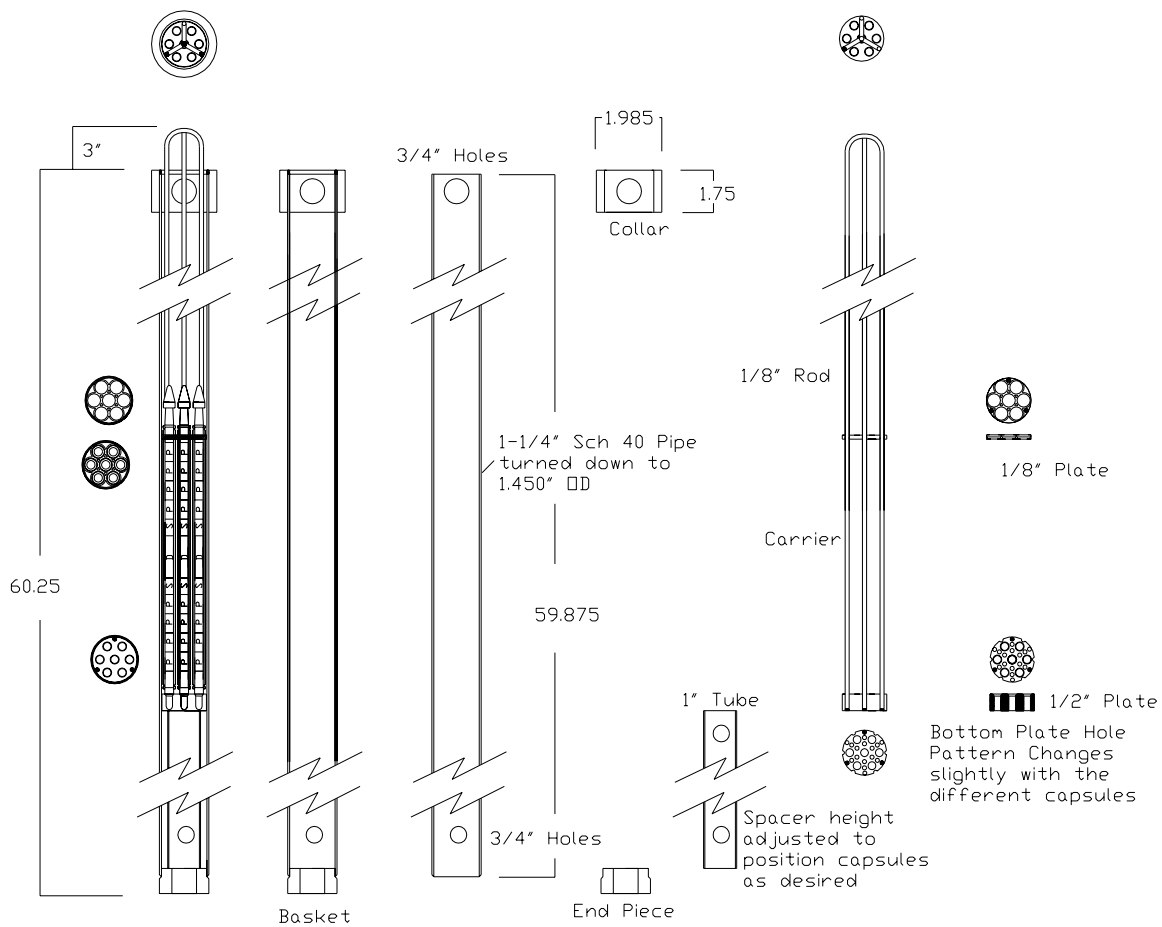


Fig. 3.1. Depiction of aluminum basket similar to that used in the array target irradiations.

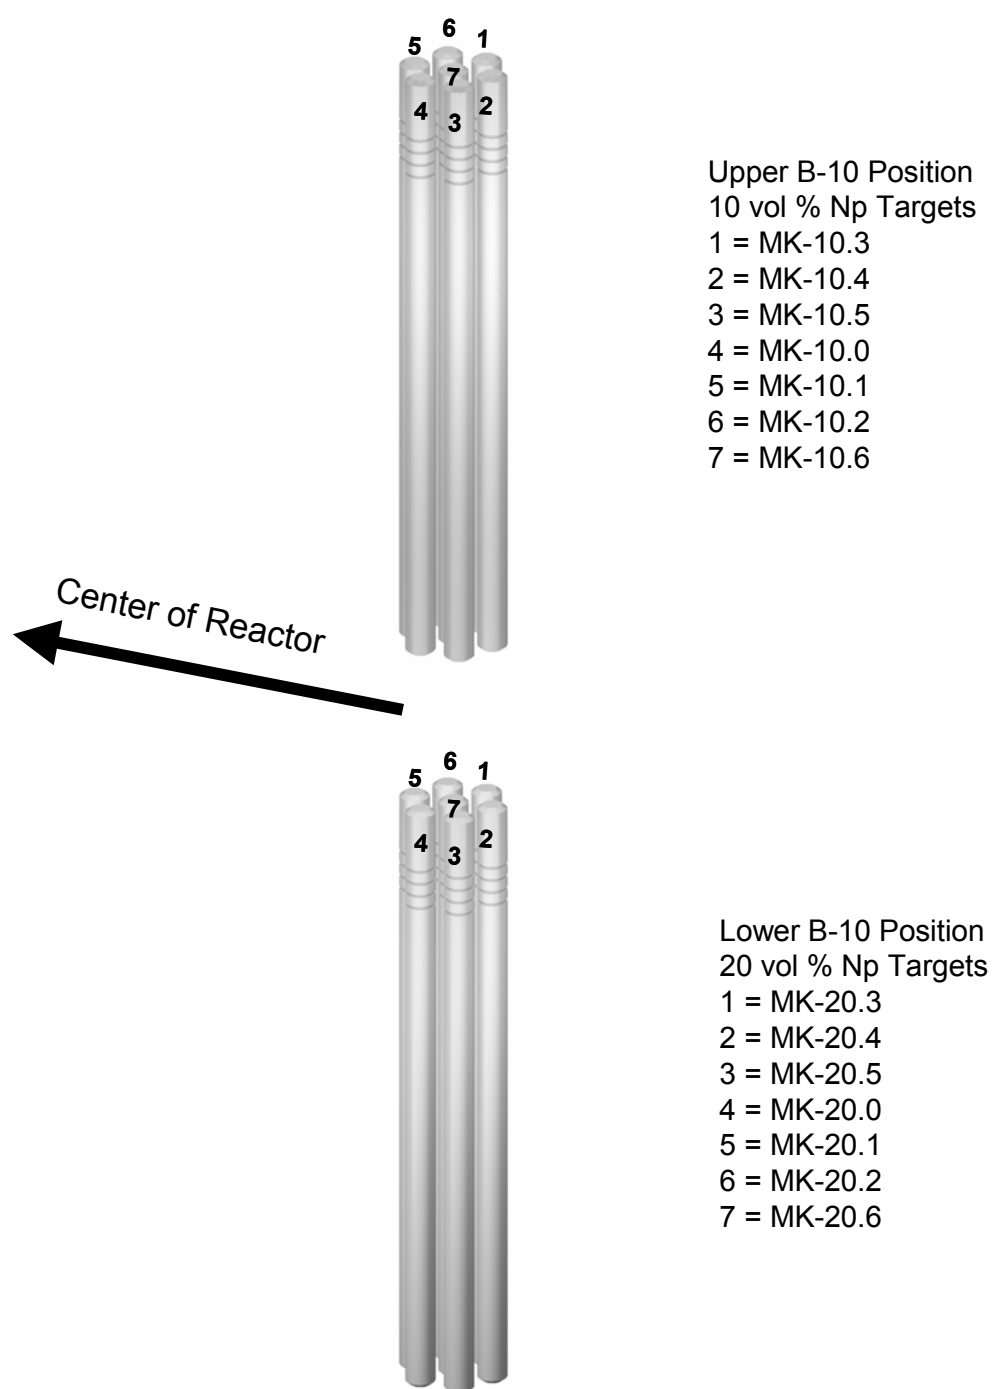


Fig. 3.2. Depiction of configuration of the 10 vol % and 20 vol % NpO_2 arrays relative to the center of the ATR core.

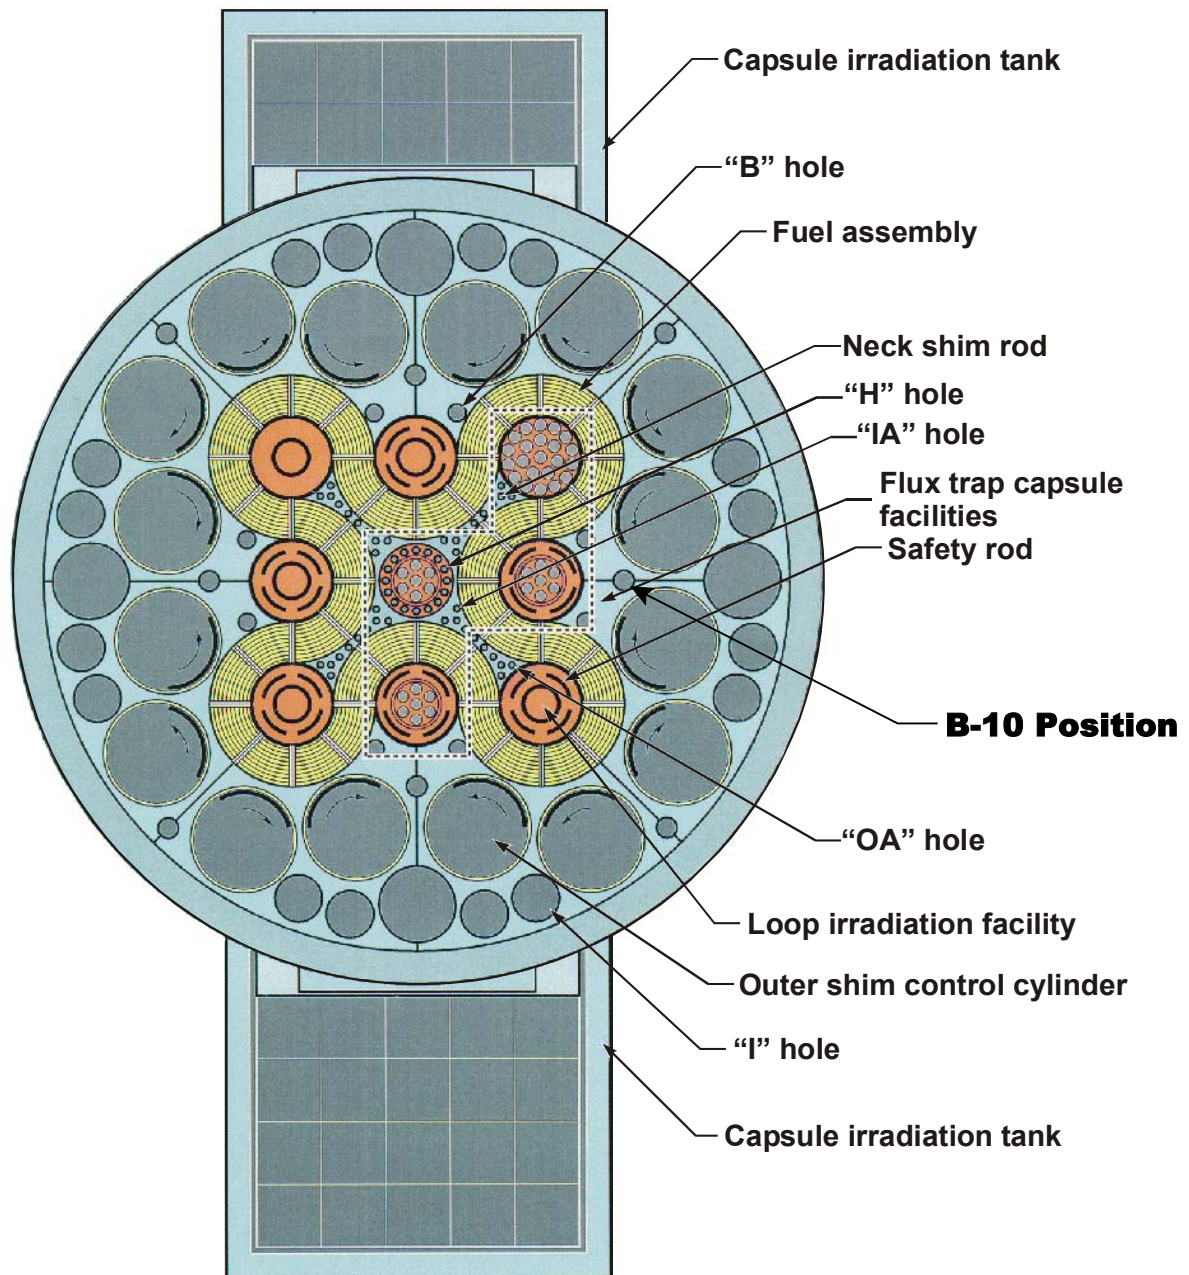


Fig. 3.3. Cross section of the ATR core showing position B-10, which was used in the array target irradiation.

Table 3.1. Summary of data for the two ATR cycles used to irradiate the array targets

	Cycle	
	125B	126A
Start date and time	07:00, 23JUL01	12:00, 24SEP01
Finish date and time	14:00, 11SEP01	15:00, 03NOV01
Cycle length, days	50.292	40.125
Core burnup, MWd	5337.60	4139.80
East quadrant burnup, MWd	1321.02	1044.45
Average core power, MW(t)	106.13	103.17
Average east quadrant power, MW(t)	26.27	26.03

4. TARGET PROCESSING

Nine of the targets (four from the 10 vol % array and five from the 20 vol % array) were processed using a two-stage dissolution process, which consisted of first dissolving the aluminum in a caustic solution and then dissolving the remaining actinides and fission products in an acid solution. The caustic decladding solution and acid product solution were sampled and analyzed by a gamma scan, gross beta scan, gross alpha scan, and inductively coupled plasma (ICP)–mass spectroscopy. Analysis for ^{236}Pu was performed by using a 2-thenoyltrifluoroacetone (TTA) extraction of the acid product solution, which was then followed by a 96-h alpha count. Based on the analytical results, a material balance was performed to determine the amounts of ^{238}Pu , ^{236}Pu , total Pu, ^{237}Np , and fission products that were recovered in the dissolution process. The following subsections describe the equipment and chemical processing steps used in the target processing.

4.1 TARGET-CUTTING JIG

A target-cutting jig, shown in Fig. 4.1, was designed to remove the pellet and dosimeter sections from the target body. The apparatus was constructed as a stainless steel trough, with slots cut into the trough to guide a saw blade through the aluminum spacers in the target. A target was placed in the trough and then held in place by using five push clamps mounted on the side of the jig. A fine-tooth hacksaw, fabricated with manipulator grips, was placed in the cutting slots, and the target was cut into four sections. Each cut was made through a spacer that separated the various sections of the target (see Fig. 2.1).



Fig. 4.1. Photograph of stainless steel saw jig used to section targets.

4.2 DISSOLVER EQUIPMENT

The pellet dissolutions were performed in a hot cell using a Teflon dissolver as shown in Fig. 4.2. The Teflon dissolver was developed after previous dissolutions with a glass dissolver vessel revealed that the silica competed with the actinides for the fluoride ions, which promoted the degradation of the glass and produced a gelatinous material in the bottom of the dissolver.

The Teflon dissolver was designed with three penetrations for a condenser, an input/output tube, and a thermometer. The dissolver was fitted with a reflux condenser that was cooled with chilled water from a constant-temperature recirculation bath. The dissolver solution was effectively refluxed during both the caustic and acid dissolution. The dissolver off-gas was passed through a condensate trap and then scrubbed with about 300 mL of 2 M NaOH to neutralize any acid fumes. The inlet/outlet tube was a 1/4-in. stainless steel tube containing a 2- μ m stainless steel filter.




Fig. 4.2. Photograph of dissolver used for pellet dissolution.

A peristaltic pump was connected to the dissolver inlet/outlet line to transfer solution into and out of the dissolver. Tests indicated that the pump would transfer the caustic solutions through the 2- μ m filter in a reasonable amount of time and that the filter would not allow actinide solids to pass through.

The dissolver was placed on a hot plate that also had a stirrer motor. Mixing during the caustic dissolution was very important in breaking up the pellet as the aluminum matrix was being dissolved. In previous dissolutions carried out in a glass dissolver, it was observed that a hard skeleton of the pellet remained as the aluminum was dissolved from the pellet core. This pellet skeleton was easily broken up when a magnetic stirring bar was used.

4.3 CAUSTIC DISSOLUTION OF TARGET SECTIONS

The caustic dissolution (also referred to as aluminum dejacketing) dissolves the aluminum target tube and aluminum matrix in the pellet core. This dissolution was performed by placing a target section in the dissolver with NaNO_3 solution. (The NaNO_3 reacts with H_2 to produce NH_3 and thereby suppresses the H_2 concentration in the off-gas.) The solution was heated to $\sim 96^\circ\text{C}$ and mixed using a stirring bar with the magnetic stirrer. Sodium hydroxide was then metered into the solution. The overall chemical reaction is shown by the following equation:³



The amount of aluminum in each pellet section was calculated based on the aluminum mass in the target tube, spacers, and three pellets. The pellet sections of the target were estimated to contain ~ 8.5 g of aluminum. An excess of NaOH was used to promote complete dissolution of the aluminum metal.

Figure 4.3 is a typical flowsheet for the caustic dissolution. The caustic dissolved all of the aluminum associated with one pellet section, which contained three pellets. The pellet section was first placed in the dissolver, and 200 mL of 2.2 M NaNO_3 was then added using the pump. The solution was heated to a gentle reflux with temperatures ranging from 90 to 96°C . Approximately 60 mL of 10 M NaOH was then added at a rate of ~ 1 mL/min.* The solution was gently refluxed for 4 h after the NaOH addition at a temperature of $\sim 103^\circ\text{C}$. If the dissolution reaction were instantaneous, then ~ 125 sccm

* At first, the 10 M NaOH solution was added at 5-min intervals, waiting for the reaction to slow before adding additional caustic. However, no problems with overheating or uncontrolled off-gas flow occurred; therefore, the NaOH was added continuously at a 1-mL/min rate without interruption.

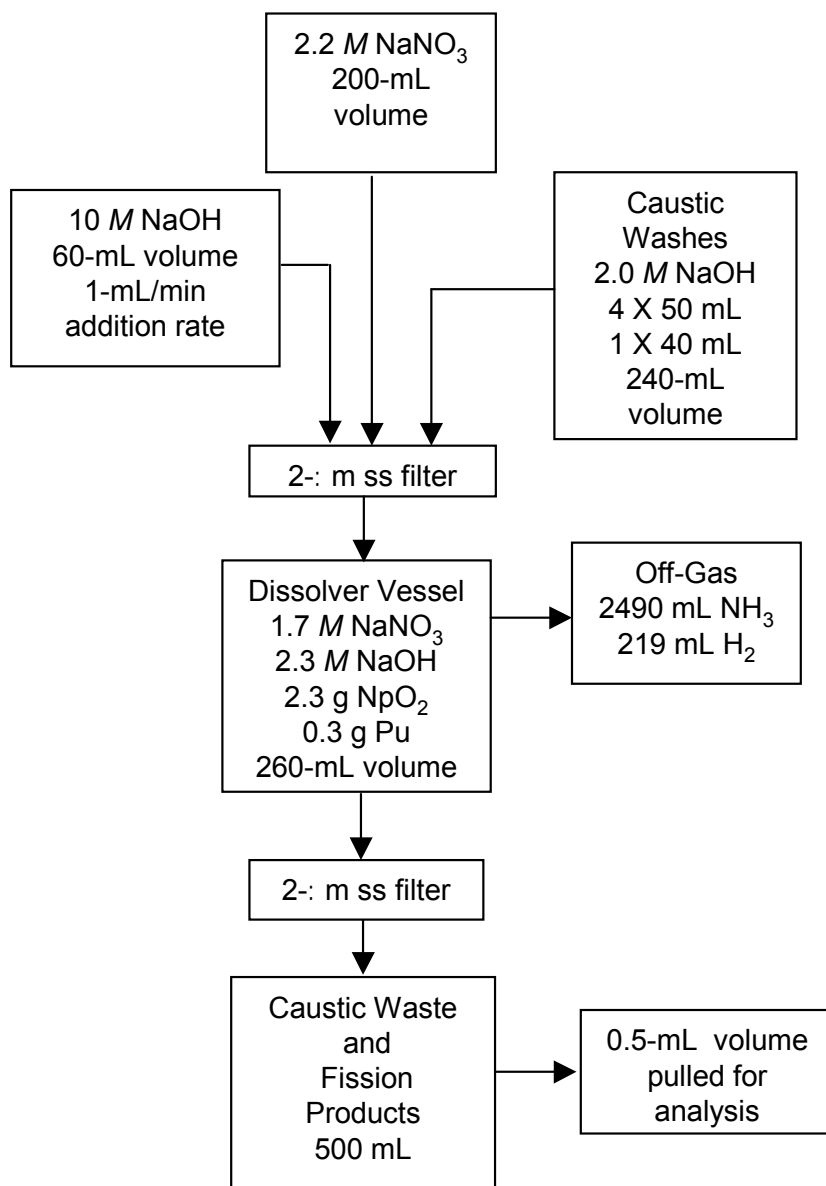


Fig. 4.3. Typical flowsheet for the caustic dissolution.

of gas would evolve during the addition of NaOH. During the dissolution, the pump was left in operation, which continuously purged the dissolver with air from the hot cell.

After a 4-h digestion period, the solution was allowed to settle and cool for 4 h. The solution was then slowly transferred out of the dissolver through the 2- μ m stainless steel filter into a 500-mL volumetric flask. The dissolver and solids were then washed with 2 *M* NaOH solution, which also flushed any solids on the filter back into the dissolver vessel. The dissolver was washed at least twice using ~100 mL of 2 *M* NaOH or until the volumetric flask reached a volume of 500 mL. The 500-mL caustic solution was sampled using a pipette to pull a 0.5-mL sample, which was then submitted for analysis.

4.4 ACID DISSOLUTION

The acid dissolution of the neptunium and plutonium oxides was carried out using HNO₃ with a small amount of added HF. Figure 4.4 depicts a typical flowsheet for the acid dissolution. A 150-mL acid solution containing 8.0 *M* HNO₃ and 0.02 *M* HF was added to the dissolver. It should be noted that Al(NO₃)₃ was not added to the acid solution, since the quantity of fluoride was so small that it was not necessary to bind any possible excess fluoride. The solution was heated to gentle reflux and continuously stirred for 3 h while the temperature was maintained between 106 and 108°C. The solution was usually allowed to cool to <50°C overnight.

The acid product solution was then pumped from the dissolver, through a 2- μ m filter, and into a 500-mL volumetric flask. After the initial product removal, a series of acid flushes using 8 *M* HNO₃–0.02 *M* HF were performed to wash any residual product or solids from the dissolver and filter. The acid flushes were then transferred to the 500-mL volumetric flask. The first acid flush contained about 50 mL of solution. The second, consisting of about 150 mL, was heated to a gentle reflux for ~30 min. This hot acid flush was pulled up into the filter several times. This step was performed to contact the filter surfaces and thus dissolve any residual product present on the surfaces. Three more 50-mL acid flushes of the dissolver were carried out after the hot acid flush. The 500-mL volumetric product flask was then sampled by pipetting a 0.5-mL sample volume, which was submitted for analysis.

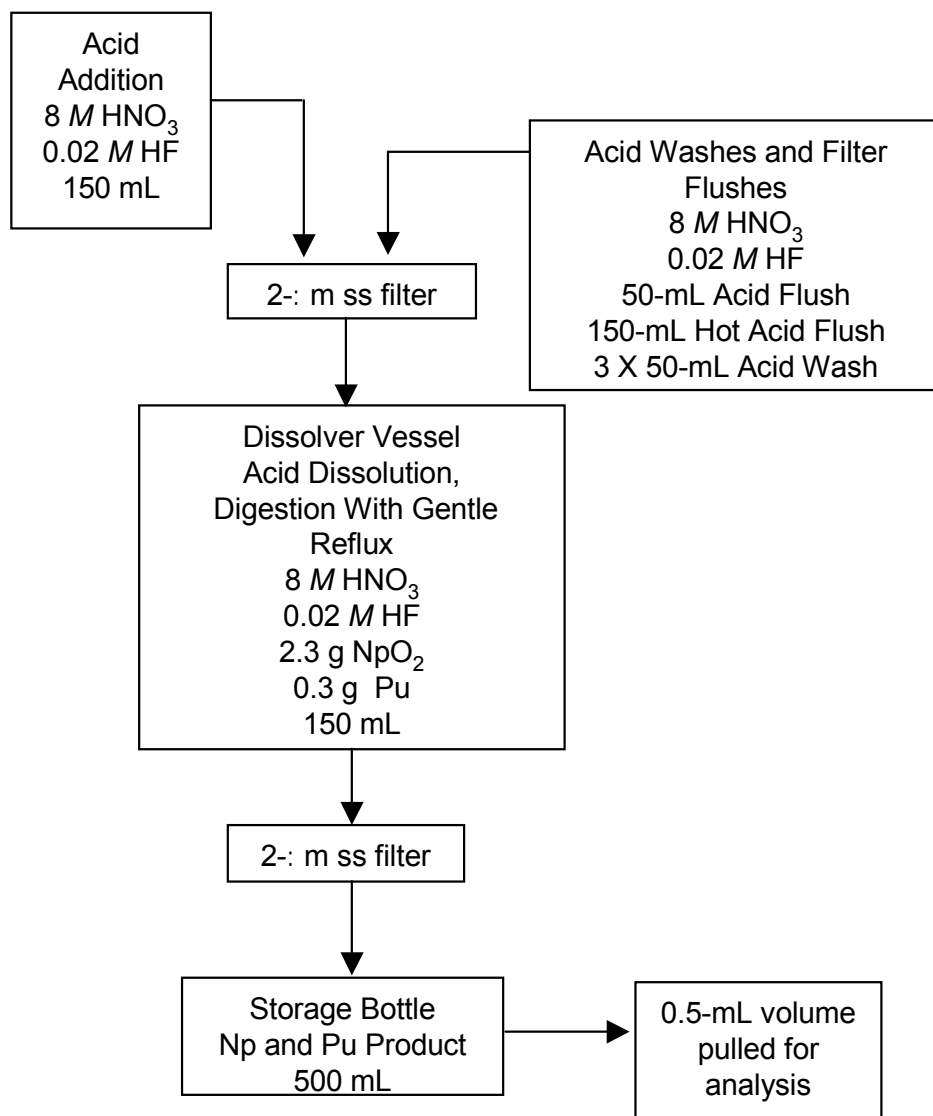


Fig. 4.4. Typical flowsheet for the acid dissolution.

4.5 DOSIMETER DISSOLUTION

The dosimeter within the array target consisted of NpO_2 wire that was placed in a vanadium can and then seal welded. The vanadium can was placed in a zircaloy cylinder, which was then sealed with a press-fit seal. The target section containing the dosimeter packages was precisely cut through the top 0.375 in. of the zircaloy package, a process that usually resulted in the vanadium can sliding out of the target section.

The dissolution process for the dosimeters was carried out using a two-step acid dissolution in a 10-mL Teflon screw-top vial. In order to handle the vials using in-cell manipulators and to heat the vials on a hot plate, an aluminum vial holder was fabricated. The vial holder was slotted to allow the dissolution and liquid level to be visually observed. The receptacle, which was fabricated to hold up to seven vials and holders, was a rectangular-shaped aluminum block into which seven slotted cavities had been machined. Each cavity held a vial and a vial holder, and the slots allowed the vial to be visually inspected during the dissolution process. A thermometer or thermocouple well was drilled into the receptacle to allow the temperature of the dissolution process to be monitored. Figure 4.5 is a photograph of the Teflon vials, vial holders, and receptacle.

The vanadium cans were placed in a 10-mL Teflon vial, where the vanadium was dissolved using ~6–7 mL of 3 *M* HNO_3 during a 12–18-h digestion period. As the vanadium dissolved, the solution became emerald green in color. After the digestion period, the dissolver solution was carefully pipetted out of the vial, while leaving the solids. The solids were washed three times using ~6 mL of 3 *M* HNO_3 .

The solids remaining from the first acid dissolution were then dissolved using ~6 mL of an 8 *M* HNO_3 –0.1 *M* HF acid solution. The temperature of the solution was maintained above 90°C for at least 6 h; however, the dissolution was allowed to digest overnight. The acid product was then carefully pipetted out of the vials, and the vials were washed three times with 6 mL of clean 8 *M* HNO_3 –0.1 *M* HF solution. The acid product and the washes were sampled by pipetting out about 0.4 mL of the solution.



Fig. 4.5. Photographs of vials, vial holders, and receptacle used in the dosimeter dissolution.

5. RESULTS AND DISCUSSION

Table 5.1 provides a list of the targets that were processed. The two target dissolution numbers reflect the two-step dissolution process that was performed. The single dosimeter dissolution number reflects essentially the one-step acid dissolution of the NpO_2 dosimeter. The analytical results from each dissolution sample were used to calculate the amount of neptunium converted to plutonium, the amount of ^{238}Pu recovered, and the amount of ^{236}Pu produced. The results of the analyses are summarized in Table 5.2, while the detailed results for each set of target pellets and dosimeters are presented in Appendix A. To provide some insight into the effect of position and target self-shielding, results are presented in terms of the relative power. The relative power reported for each target was calculated by dividing the neutron flux at a target by the average flux in the region. Note that this calculation was performed for one point in time during the irradiation and is therefore representative of only a particular control drum configuration. Calculations are being performed to establish the relative power based on the total fluence at each target.⁴ However, it is not expected that the relative powers will change significantly. The quantities reported in Table 5.2 are briefly defined in the following paragraph.

The neptunium recovery in both the caustic and acid dissolutions is provided, and the sum of these two quantities divided by the initial quantity of neptunium is reported as the residual neptunium. For the plutonium acid recovery, the plutonium product is reported for both ^{238}Pu and total plutonium. The weight percentage of ^{238}Pu (on the basis of total plutonium) is also shown. The conversion of neptunium to both plutonium and fission products is calculated by dividing the moles of each of these quantities by the initial moles of neptunium. The values for neptunium and plutonium loss to waste are the weight percentages of the recovered neptunium and plutonium in the caustic dissolution stream. The concentration of ^{236}Pu reported is the amount (in parts per million on a total plutonium basis) present at discharge of the target from the reactor. This amount was calculated from the measured concentration of the processed target and the time since discharge.

The isotopic distributions of the fission products are shown for the caustic dissolution and the acid dissolution streams in Tables 5.3 and 5.4, respectively. These amounts are reported in terms of parts per million of the ^{238}Pu produced and can therefore be used to estimate fission product concentrations in waste streams for a particular ^{238}Pu production rate. A summary of the data measured for the dosimeters is presented in Table 5.5. Samples were taken and analyzed for the acid dejacket solution of two dosimeters. The analysis for the MK-10.1 dosimeter revealed that 1.4 and 2.4 wt % of the Np and ^{238}Pu were in the dejacket solution, respectively. For the MK-20.4 dosimeter, these quantities were 0.4 and 0.5 wt %.

Figures 5.1–5.3 provide graphical representations of the data as a function of the relative power. In Fig. 5.1, the percentages of neptunium converted to plutonium are shown. The percentages of total plutonium that consist of ^{238}Pu are shown in Fig. 5.2. Finally, the ^{236}Pu concentration (parts per million on a total plutonium basis) are presented in Fig. 5.3.

Table 5.1. List of the array targets that were processed

Target number	Reactor Position	Target dissolution numbers ^a	NpO _x (vol %)	Dosimeter dissolution number ^b
MK-10.1	U-5	DJ-19/AD-19	10	ADD-25
MK-10.2	U-6	DJ-23/AD-23	10	<i>c</i>
MK-10.4	U-2	DJ-20/AD-20	10	ADD-26
MK-10.6	U-7	DJ-21/AD-21	10	ADD-27
MK-20.1	L-5	DJ-16/AD-16	20	ADD-21
MK-20.2	L-6	DJ-22/AD-22	20	ADD-22
MK-20.4	L-2	DJ-17/AD-17	20	ADD-23
MK-20.5	L-3	DJ-24/AD-24	20	<i>c</i>
MK-20.6	L-7	DJ-18/AD-18	20	ADD-24

^a DJ = dejacket caustic dissolution; AD = acid dissolution.

^b ADD = acid dissolution of dosimeter.

^c Not analyzed.

Table 5.2. Summary of results for array target analysis

Target number	Relative Power	Initial Np (g)	Np recovery (g)		Residual Np (wt %)	Pu acid recovery (g)		²³⁸ Pu/Total Pu (wt %)	Conversion (mol %)		Loss to waste (wt %)		²³⁶ Pu at discharge (ppm) ^b
			Caustic	Acid		²³⁸ Pu	Total Pu		Np to Pu	Np to FP ^a	Np	Pu	
MK-10.4	0.49	1.0063	0.0119	0.965	97.08	0.101	0.112	89.99	11.14	0.06	1.22	0.29	3.26 ± 8.5%
MK-10.6	0.91	1.0054	0.0115	0.870	87.67	0.113	0.129	87.81	12.76	0.09	1.30	0.12	3.86 ± 5.1%
MK-10.2	1.32	1.0054	0.0073	0.855	85.76	0.118	0.137	86.06	13.52	0.09	0.84	0.07	3.30 ± 11.2%
MK-10.1	1.7	1.0062	0.0059	0.890	89.04	0.140	0.165	84.80	16.34	0.18	0.66	0.05	2.96 ± 6.2%
MK-20.4	0.46	2.0113	0.0030	1.825	90.89	0.184	0.204	90.09	10.08	0.05	0.17	0	6.24 ± 2.5%
MK-20.5	0.72	2.0104	0.0026	1.715	85.44	0.215	0.246	87.36	12.18	0.08	0.15	0.0077	4.58 ± 6.3%
MK-20.6	0.81	2.0110	0.0021	1.810	90.11	0.209	0.236	88.51	11.69	0.08	0.12	0	5.36 ± 3.7%
MK-20.2	1.25	2.0106	0.0113	1.780	89.09	0.259	0.297	87.17	14.69	0.10	0.63	0.07	3.58 ± 2.7%
MK-20.1	1.72	2.0111	0.0007	1.675	83.32	0.242	0.285	84.68	14.11	0.15	0.04	0	3.88 ± 5.1%

^a FP = fission products.^b Relative error based on 2 standard deviations as derived from the counting statistics.

Table 5.3. Fission products in caustic dejacket stream (ppm) relative to ^{238}Pu production

Isotope	Target number (Relative power) ^a								
	MK-10.4 (0.49)	MK-10.6 (0.91)	MK-10.2 (1.32)	MK-10.1 (1.7)	MK-20.4 (0.46)	MK-20.5 (0.72)	MK-20.6 (0.81)	MK-20.2 (1.25)	MK-20.1 (1.72)
^{106}Ru	57	76	73	105	40	29	39	46	36
^{134}Cs	11	18	19	33	9	12	14	15	28
^{137}Cs	1430	2199	2379	3328	1270	1517	1709	1743	2766

^a The value for relative power is listed parenthetically following the target number.

Table 5.4. Fission products in acid dissolution stream (ppm) relative to ^{238}Pu production

Isotope	Target number (Relative power) ^a								
	MK-10.4 (0.49)	MK-10.6 (0.91)	MK-10.2 (1.32)	MK-10.1 (1.7)	MK-20.4 (0.46)	MK-20.5 (0.72)	MK-20.6 (0.81)	MK-20.2 (1.25)	MK-20.1 (1.72)
^{95}Zr	2	2	1	4	3	1	4	2	7
^{106}Ru	275	362	348	526	290	323	391	380	711
^{125}Sb	23	< 10	< 10	< 10	23	25	26	24	37
^{134}Cs	7	9	10	14	9	13	10	12	26
^{137}Cs	907	1086	1243	1331	1185	1662	1338	1502	2444
^{144}Ce	353	488	470	698	416	395	508	476	879
^{154}Eu	< 20	< 23	< 25	< 26	< 15	< 16	< 18	< 16	< 23
^{155}Eu	23	33	37	42	21	31	36	25	57

^a The value for relative power is listed parenthetically following the target number.

Table 5.5. Summary of dosimeter data

Target ID for dosimeter	Relative power	Initial Np (g)	Np recovery (g)	Residual Np (wt %)	²³⁸ Pu recovery (g)	Total Pu recovery (g)	²³⁸ Pu/Total Pu (wt %)	Conversion of Np to Pu (mol %)	²³⁶ Pu at discharge (ppm) ^a
MK-10.4	0.49	0.0015	0.0012	79.14	0.00015	0.00017	88.46	11.07	2.76 ± 6.2%
MK-10.6	0.91	0.0017	0.0014	82.21	0.00021	0.00024	86.75	14.11	2.39 ± 5.0%
MK-10.2	1.32	<i>b</i>	<i>b</i>	<i>b</i>	<i>b</i>	<i>b</i>	<i>b</i>	<i>b</i>	<i>b</i>
MK-10.1	1.7	0.0015	0.0009	60.42	0.00016	0.00019	84.12	12.47	3.79 ± 4.2%
MK-20.4	0.46	0.0014	0.0007	51.59	0.00012	0.00014	85.76	9.62	3.55 ± 5.2%
MK-20.5	0.72	<i>b</i>	<i>b</i>	<i>b</i>	<i>b</i>	<i>b</i>	<i>b</i>	<i>b</i>	<i>b</i>
MK-20.6	0.81	0.0016	0.0010	61.09	0.00018	0.00022	83.18	13.75	4.24 ± 4.5%
MK-20.2	1.25	0.0015	0.0011	76.01	0.00021	0.00026	81.56	17.81	3.33 ± 6.2%
MK-20.1	1.72	0.0019	0.0014	72.05	0.00030	0.00038	79.56	19.29	4.20 ± 3.7%

^a Relative error based on 2 standard deviations as derived from the counting statistics.

^b Not analyzed.

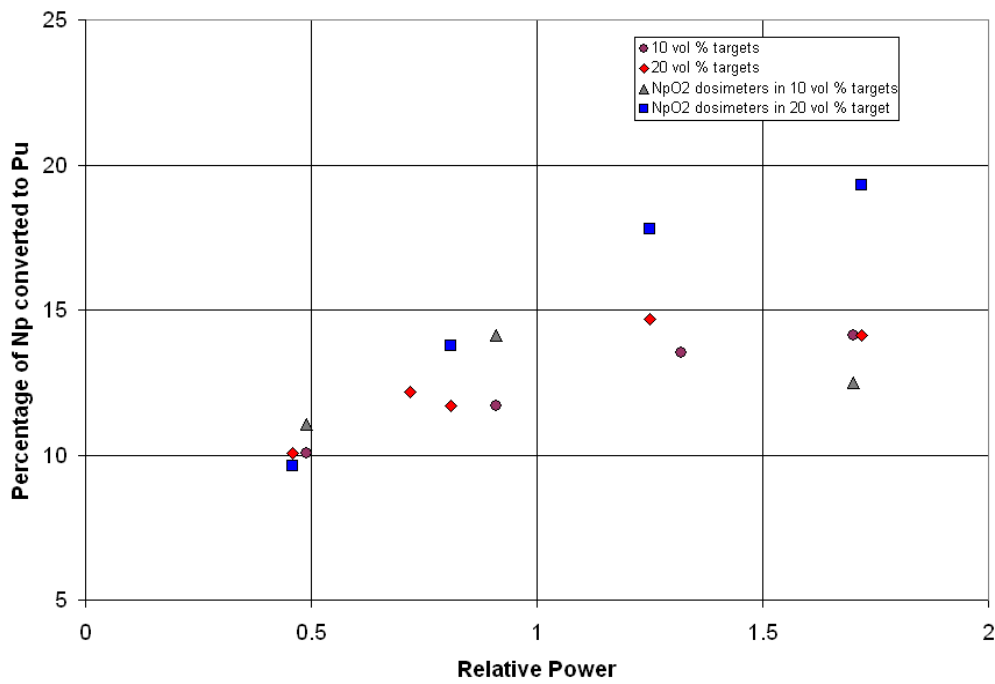


Fig. 5.1. Percentage of neptunium converted to plutonium as a function of relative power for the targets and dosimeters.

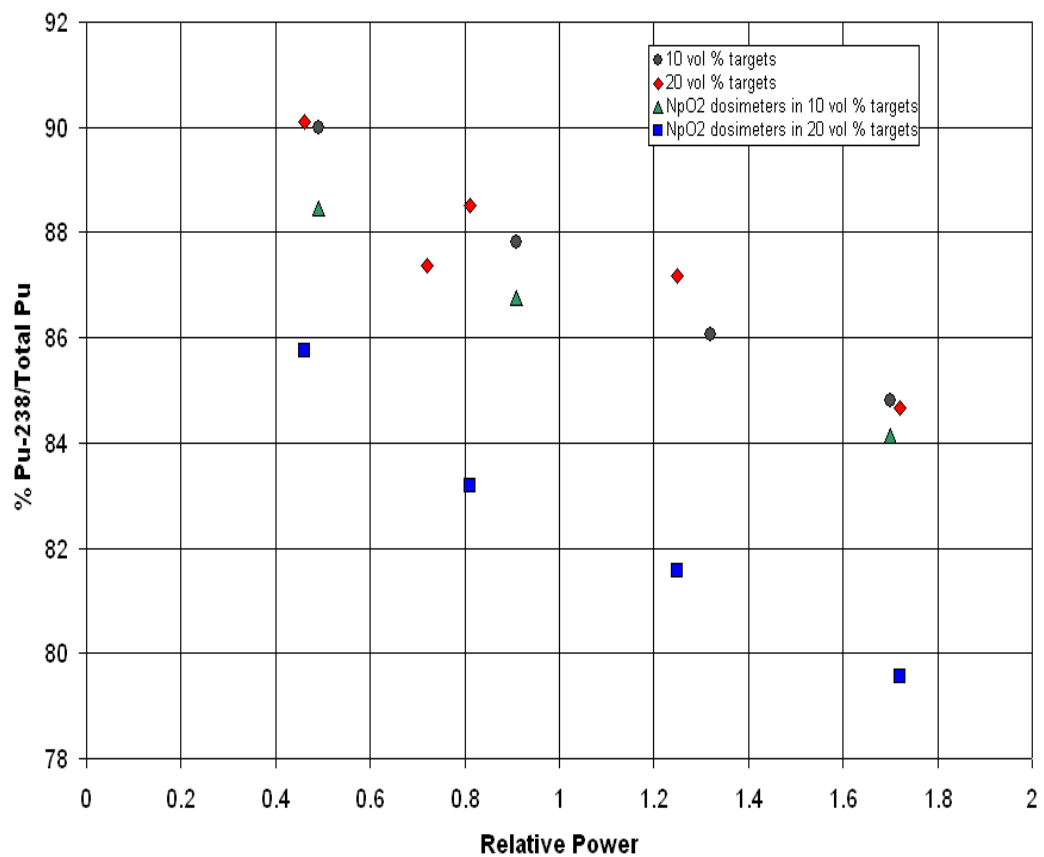


Fig. 5.2. Plutonium-238 production (percentage of total plutonium production) as a function of relative power for the targets and dosimeters.

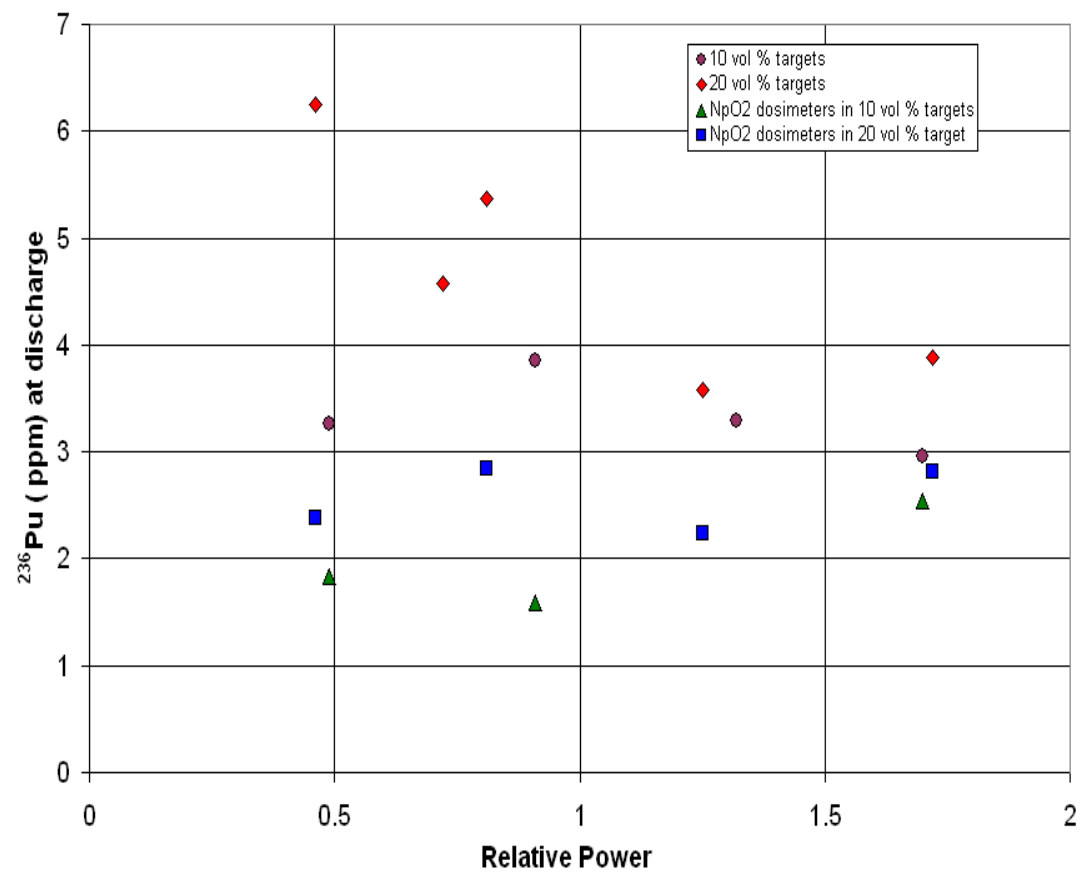


Fig. 5.3. Plutonium-236 content at discharge from the ATR as a function of relative power for the targets and dosimeters.

Several trends that reflect the different flux (and target self-shielding) at the various target positions are evident in the figures. The percentage of neptunium that is converted to plutonium increases with relative power—ranging from about 10 to 16 mol % for the pellets. The results for the 10 and 20 vol % targets are similar. The ^{238}Pu production, as a percentage of total plutonium, generally decreases with increasing relative power. This value ranged from about 85 to 90 wt % for the pellets. The specification for ^{238}Pu production is 82 wt %, as of the date of processing. Again, the 10 and 20 vol % targets provided similar results. In Fig. 5.3, the ^{236}Pu production at discharge tends to decrease with increasing relative power. Additionally, the ^{236}Pu production is higher in the 20 vol % pellets than in the 10 vol % targets. The ^{236}Pu production in the pellets ranged from about 3 to 6 ppm. The specification for ^{236}Pu is 2 ppm, as of the date of processing. Hence, these targets would require a cooling period of 1.7 to 4.5 years.

The processing of the remaining five targets, which will be the subject of a future report, will help to further establish the trends that are observed for the various target positions. Additionally, the preparation of the final calculations for the relative power at each position will provide better insight into the flux depression caused by each of the targets and the role of target self-shielding in the production of ^{238}Pu and ^{236}Pu .

6. SUMMARY

Fourteen targets were irradiated in two arrays during two cycles at the ATR. One array consisted of a set of seven targets that contained 10 vol % NpO_2 pellets, while the other array consisted of seven targets that contained 20 vol % NpO_2 pellets. The pellets consisted of a mixture of NpO_2 and aluminum powder. Each target also contained a dosimeter package, which consisted of a small NpO_2 wire that was inside a vanadium container.


After completion of irradiation and shipment back to ORNL, nine of the targets (four from the 10 vol % array and five from the 20 vol % array) were punctured for pressure measurement and measurement of ^{85}Kr . These nine targets and the associated dosimeters were then chemically processed to measure the residual neptunium, total plutonium production, ^{238}Pu production, and ^{236}Pu concentration at discharge. The amount and isotopic composition of fission products were also measured. These data will be useful in designing the production targets, as well as in planning for the handling of waste streams.

The five remaining targets will be punctured for pressure measurement after additional gas analysis equipment is brought on-line. Finally, calculations on the expected yield are being performed by INEEL personnel. When available, these calculations will be compared with the experimental results to confirm the model used for the ATR and to identify the appropriate cross-section data set for ^{236}Pu production.

REFERENCES

1. *Interim Status of Array Target Fabrication Report for the Advanced Test Reactor (ATR)*, Oak Ridge National Laboratory, Oak Ridge, Tennessee, DRAFT, September 30, 2001.
2. "Results of Np Target Capsule Testing," memo from R. N. Morris, Oak Ridge National Laboratory, to R. M. Wham, Oak Ridge National Laboratory, August 9, 2001.
3. L. J. King, *TRU Operating Manual*, Section 1333, Radiochemical Engineering Development Center, Oak Ridge National Laboratory, January 1975.
4. Personal communication from B. G. Schnitzler, Idaho National Engineering and Environmental Laboratory, Idaho Falls, Idaho, October 2003.

APPENDIX A: Detailed Data Sheets for Targets and Dosimeters

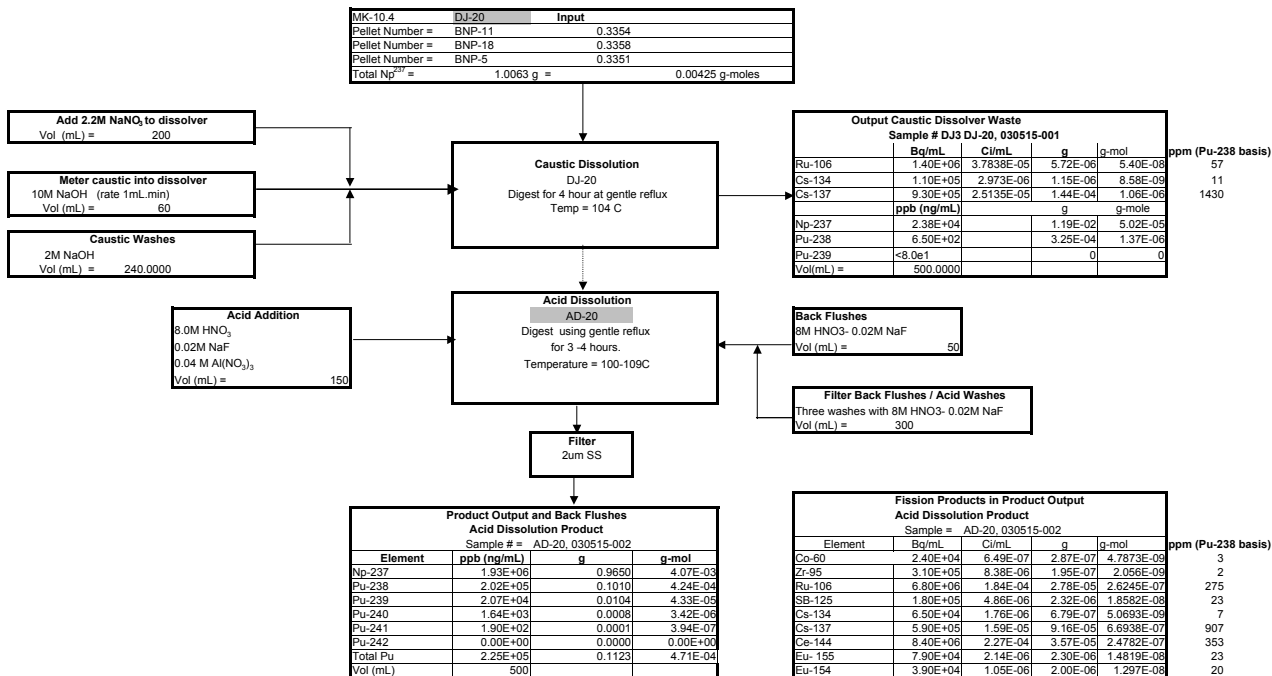

	Target Number	Pellet Number	Dissolution Number	Dissolution Sample Code	% Density	Pellet Vol % NpOX	Pellet Mass Np g	Pellet g-mole Np	Pu-236 ppm	Adjusted Pu-236 ppm
Pellet Input	MK-10.4	BNP-11	20		90.36%	10.01%	0.33540	0.00141	2.21	3.26
Pellet Input	MK-10.4	BNP-18	20		89.43%	10.02%	0.33580	0.00142		
Pellet Input	MK-10.4	BNP-5	20		89.99%	10.01%	0.33510	0.00141		
Total							1.00630	0.00425		
Dejacket Waste	MK-10.4	BNP-11, 18, 5	20	DJ-20, 030515-001			0.01190	0.00005		
Acid Dissol	MK-10.4	BNP-11, 18, 5	20	AD-20, 030515-002			0.96500	0.00407		

	Actual	Predicted (BGS)	Actual/Pred
Np Residual Amount (wt basis) = (Np caustic + Np acid)/ Np input =	0.9708	#DIV/0!	
Pu-238/Total Pu (wt basis) =	0.8999	#DIV/0!	
Conversion of Np to Pu (mol basis) = Pu-238 caustic + Pu-239 caustic + total Pu / Np input =	0.1114	#DIV/0!	
Conversion of Np to FP (mol basis) = (Sum of fission product) in caustic and acid / Np input =	0.0006		
Fractional loss of Np in Liq Waste (wt basis) = Np caustic/ (Np acid + Np dejacket) =	0.0122		
Fractional loss of Pu in Liq Waste (wt basis) = Pu caustic/ (Pu caustic + Pu acid) =	0.0029		

Pu-236 content ppm	Discharge Date	Analysis Date	Time elapsed (t) days	Pu-236 t1/2 years	Pu-236 t1/2 days	Adjusted Pu-236 ppm	Pu-238 t1/2, years	Pu238 t1/2 days	Adjusted Pu-238, g
2.21	11/1/2001	6/6/2003	-582.00	2.85	1040.96	3.26	87.7	32032.425	0.1026

Reference Information	MW	Density g/cc
NpO ₂ ²³⁷ (oxide)	269.047	11.143
Np237	237.0482	20.476
Pu-238	238.0496	19.851
Pu-239	239.0522	19.851
Pu-240	240.0538	19.851
Pu241	241.0568	19.851
Pu-242	242.0587	19.851
Conversion	5.70E+10 Bq/Ci	
	365.25 days/year	

Analysis	Sample	Co-60 Bq/mL	Zr-95 Bq/mL	Ru-106 Bq/mL	SB-125 Bq/mL	Cs-134 Bq/mL	Cs-137 Bq/mL	Ce-144 Bq/mL	Eu-155 Bq/mL	Eu-154 Bq/mL
Gr gamma	DJ-20, 030515-001				1.40E+06		1.10E+05	9.30E+05	8.40E+06	7.90E+04
	AD-20, 030515-002	2.40E+04	3.10E+05	6.80E+06	1.80E+05	6.50E+04	5.90E+05	8.40E+06	7.90E+04	3.90E+04

Alpha & Beta	Sample	Alpha Bq/mL	Beta Bq/mL	total activity Bq/mL
	DJ-20, 030515-001	2.10E+05	4.09E+06	4.30E+06
	AD-20, 030515-002	1.20E+08	4.00E+07	1.60E+08

ICP	Sample	Np-237 ppb (ng/mL)	Pu-238 ppb (ng/mL)	Pu-239 ppb (ng/mL)	Pu-240 ppb (ng/mL)	Pu-241 ppb (ng/mL)	Pu-242 ppb (ng/mL)	Pu-244 ppb (ng/mL)
	DJ-20, 030515-001	2.38E+04	6.50E+02	<8.0e1	<5.0e1	<5.0e1	<5.0e1	<5.0e1
	AD-20, 030515-002	1.93E+06	2.02E+05	2.07E+04	1.64E+03	1.90E+02	<5.0E1	<5.0E1

Pu-Alpha Scan TTA extraction	Sample	Pu-236/Pu-238 ppm (ug/mL)	Relative error %
	AD-20, 030515-002	2.21	8.5


Specific activity Calculation	Factor =	T1/2 s	M g/mol	Specific activity Ci/g
Co-60	1.13E+13	166328640	59.9338222	1130.360
Zr-95		5531328	94.9080427	21489.00
Ru-106		32278176	105.9073269	3306.00
SB-125		87042172.32	124.9052478	1048.00
Cs-134		65160132.48	133.9067134	1294.00
Cs-137		948937032	136.9070835	87.00
Ce-144		24614755.2	143.9136427	3182.80
Eu-155		150248889.4	154.9228894	465.00
Pu-238		2767601520	238.0495534	17.12
Pu-236		89939160	236.0460481	530.00
Eu-154		271174456.8	153.922975	2.64E+02

$$\text{Pu-236/238 ppm} = \frac{(5.80 \text{ MeV Area Counts} \times \text{Pu-236}_{112} \times 236) \times 1 \text{E6}}{(\text{Full Spectrum Counts} \times \text{Pu-238}_{112} \times 238)}$$

$$\text{Relative Error} = \frac{2 \times (5.80 \text{ MeV Area Counts})^{1/2}}{5.80 \text{ Area Counts}}$$

1925.1

4.30E+06

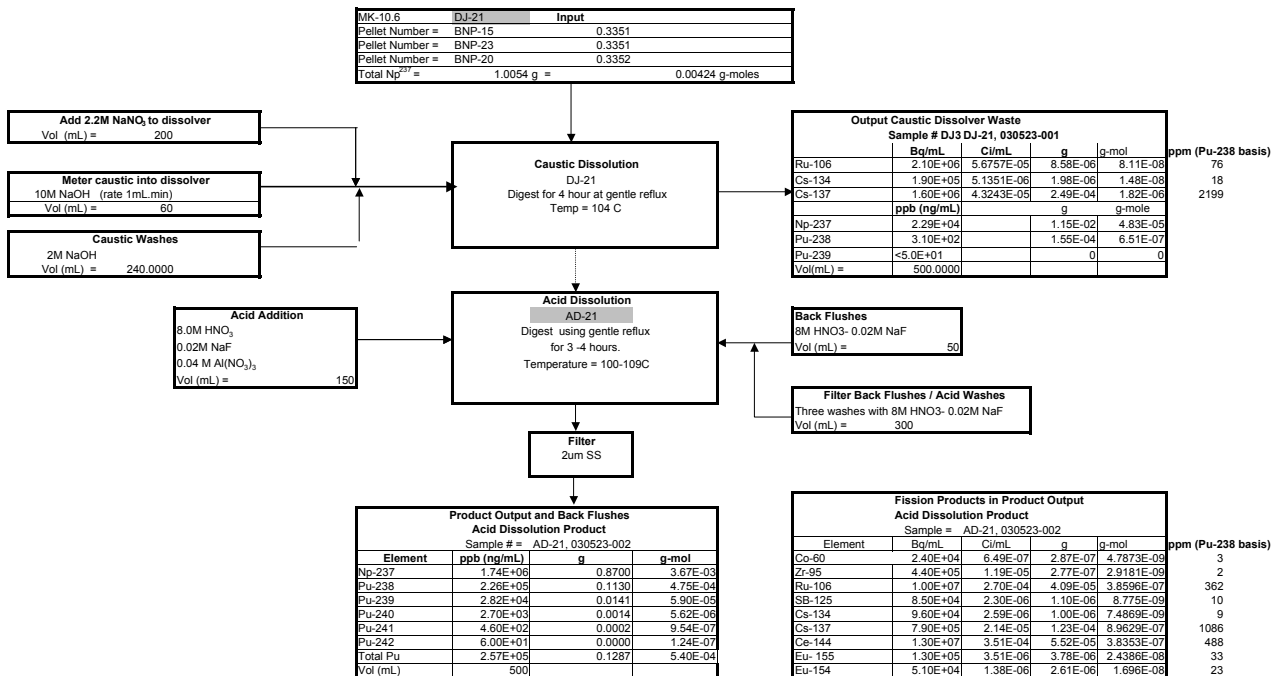

	Target Number	Pellet Number	Dissolution Number	Dissolution Sample Code	% Density	Pellet Vol % NpOX	Pellet Mass Np g	Pellet g-mole Np	Pu-236 ppm	Adjusted Pu-236 ppm
Pellet Input	MK-10.6	BNP-15	21		89.59%	10.00%	0.33510	0.00141	2.62	3.86
Pellet Input	MK-10.6	BNP-23	21		89.71%	10.00%	0.33510	0.00141		
Pellet Input	MK-10.6	BNP-20	21		89.39%	10.00%	0.33520	0.00141		
Total							1.00540	0.00424		
Dejacket Waste	MK-10.6	BNP-15, 23, 20	21	DJ-21, 030523-001			0.01145	0.00005		
Acid Dissol	MK-10.6	BNP-15, 23, 20	21	AD-21, 030523-002			0.87000	0.00367		

	Actual	Predicted (BGS)	Actual/Pred
Np Residual Amount (wt basis) = (Np caustic + Np acid)/ Np input =	0.8767		#DIV/0!
Pu-238/Total Pu (wt basis) =	0.8781		#DIV/0!
Conversion of Np to Pu (mol basis) = Pu-238 caustic + Pu-239 caustic + total Pu / Np input =	0.1276		#DIV/0!
Conversion of Np to FP (mol basis) = (Sum of fission product) in caustic and acid / Np input =	0.0009		
Fractional loss of Np in Liq Waste (wt basis) = Np caustic/ (Np acid + Np dejacket) =	0.0130		
Fractional loss of Pu in Liq Waste (wt basis) = Pu caustic/ (Pu caustic + Pu acid) =	0.0012		

Pu-236 content ppm	Discharge Date	Analysis Date	Time elapsed (t) days	Pu-236 t/2 years	Pu-236 t/1/2 days	Adjusted Pu-236 ppm	Pu-238 t/2, years	Pu238 t/1/2 days	Adjusted Pu-238, g
2.62	11/1/2001	6/6/2003	-582.00	2.85	1040.96	3.86	87.7	32032.425	0.1146

Reference Information		
	MW	Density g/cc
NpO ₂ ²³⁷ (oxide)	269.047	11.143
Np ₂ O ₇	237.0482	20.476
Pu-238	238.0496	19.851
Pu-239	239.0522	19.851
Pu-240	240.0538	19.851
Pu ₂ O ₇	241.0568	19.851
Pu-242	242.0587	19.851
Conversion	3.70E+10 Bq/Ci	
	365.25 days/year	

Analysis	Sample	Co-60 Bq/mL	Zr-95 Bq/mL	Ru-106 Bq/mL	SB-125 Bq/mL	Cs-134 Bq/mL	Cs-137 Bq/mL	Ce-144 Bq/mL	Eu-155 Bq/mL	Eu-154 Bq/mL
Gr gamma	DJ-21, 030523-001			2.10E+06		1.90E+05	1.60E+06			
	AD-21, 030523-002	2.40E+04	4.40E+05	1.00E+07	8.50E+04	9.60E+04	7.90E+05	1.30E+07	1.30E+05	5.10E+04

Alpha & Beta	Alpha Bq/mL	Beta Bq/mL	total activity Bq/mL
DJ-21, 030523-001	1.60E+05	6.34E+06	6.50E+06
AD-21, 030523-002	1.50E+08	5.00E+07	2.00E+08

ICP	Np-237 ppb (ng/mL)	Pu-238 ppb (ng/mL)	Pu-239 ppb (ng/mL)	Pu-240 ppb (ng/mL)	Pu-241 ppb (ng/mL)	Pu-242 ppb (ng/mL)	Pu-244 ppb (ng/mL)
DJ-21, 030523-001	2.29E+04	3.10E+02	<5.0E+01	<5.0E+01	<5.0E+01	<5.0E+01	<5.0E+01
AD-21, 030523-002	1.74E+06	2.26E+05	2.82E+04	2.70E+03	4.60E+02	6.00E+01	<5.0E+01


Pu-Alpha Scan TTA extraction	Pu-236/Pu-238 ppm (ug/mL)	Relative error %
AD-21, 030523-002	2.62	5.1

Specific activity Calculation				
Factor =	1.13E+13	T1/2 s	M g/mol	Specific activity Ci/g
Co-60		166328640	59.9338222	1130.360
Zr-95		5531328	94.9080427	21469.000
Ru-106		32278176	105.9073269	3306.000
SB-125		87042172.32	124.9052478	1048.000
Cs-134		65160132.48	133.9067134	1294.000
Cs-137		948937032	136.9070835	87.000
Ce-144		24614755.2	143.9136427	3182.800
Eu-155		150248889.4	154.9228894	465.000
Pu-238		2767601520	238.0495534	17.12
Pu-239		89939160	238.0460481	530.00
Eu-154		271174456.8	153.922975	2.64E+02

Pu-236/238 ppm =
$$\frac{(5.80 \text{ MeV Area Counts} \times \text{Pu-236}_{1/2} \times \text{X236}) \times 1 \text{E6}}{(\text{Full Spectrum Counts} \times \text{Pu-238}_{1/2} \times \text{X238})}$$

Relative Error =
$$\frac{2 \times (5.80 \text{ MeV Area Counts})^{1/2}}{5.80 \text{ Area Counts}}$$

6.50E+06

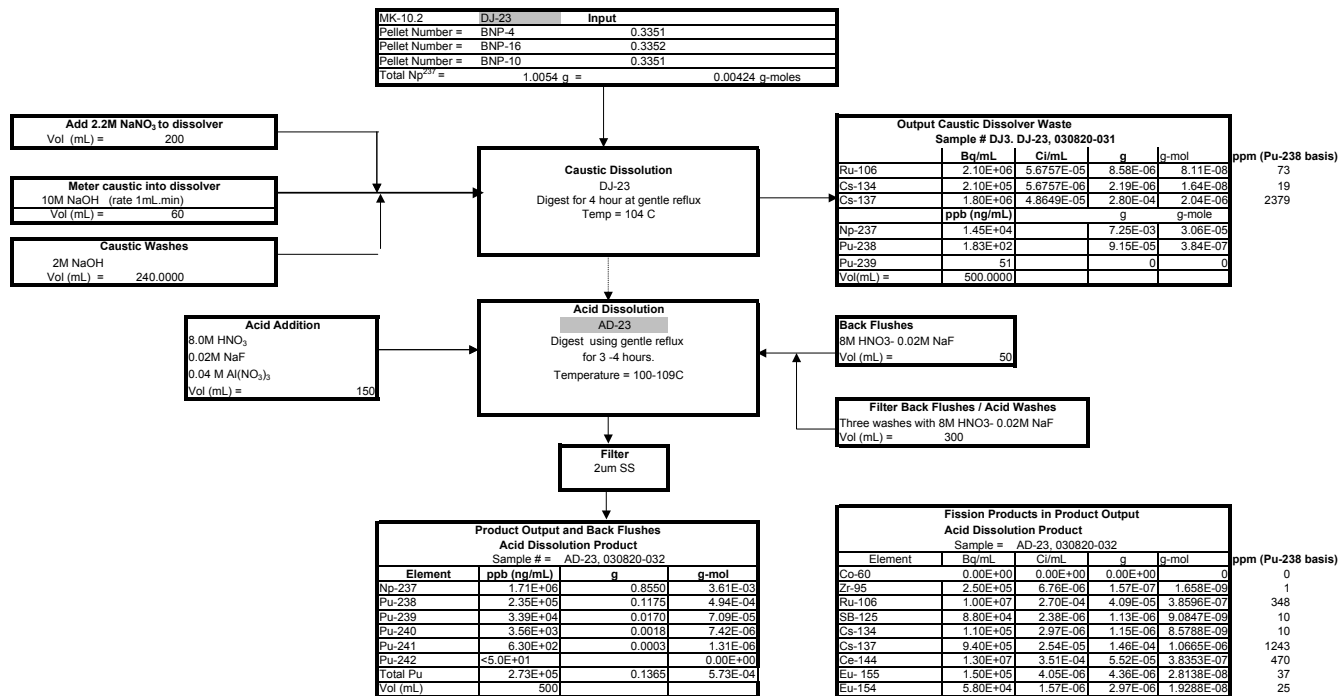

	Target Number	Pellet Number	Dissolution Number	Dissolution Sample Code	% Density	Pellet Vol % NpOX	Pellet Mass Np	Pellet g-mole Np	Pu-236 ppm	Adjusted Pu-236 ppm
Pellet Input	MK-10.2	BNP-4	23		89.73%	10.00%	0.33510	0.00141	2.08	3.30
Pellet Input	MK-10.2	BNP-16	23		89.27%	10.00%	0.33520	0.00141		
Pellet Input	MK-10.2	BNP-10	23		89.94%	10.00%	0.33510	0.00141		
Total							1.00540	0.00424		
Dejacket Waste	MK-10.2	BNP-4, 16, 10	23	DJ-23, 030820-031			0.00725	0.00003		
Acid Dissol	MK-10.2	BNP-4, 16, 10	23	AD-23, 030820-032			0.85500	0.00361		

	Actual	Predicted (BGS)	Actual/Pred
Np Residual Amount (wt basis) = (Np caustic + Np acid) / Np input =	0.8576		#DIV/0!
Pu-238/Total Pu (wt basis) =	0.8606		#DIV/0!
Conversion of Np to Pu (mol basis) = Pu-238 caustic + Pu-239 caustic + total Pu / Np input =	0.1352		#DIV/0!
Conversion of Np to FP (mol basis) = (Sum of fission product) in caustic and acid / Np input =	0.0009		
Fractional loss of Np in Liq Waste (wt basis) = Np caustic / (Np acid + Np dejacket) =	0.0084		
Fractional loss of Pu in Liq Waste (wt basis) = Pu caustic / (Pu caustic + Pu acid) =	0.0007		

Pu-236 content ppm	Discharge Date	Analysis Date	Time elapsed (t) days	Pu-236 t1/2 years	Pu-236 t1/2 days	Adjusted Pu-236 ppm	Pu-238 t1/2, years	Pu238 t1/2 days	Adjusted Pu-238, g
2.08	11/1/2001	9/23/2003	-691.00	2.85	1040.96	3.30	87.7	32032.425	0.1194

	MW	Density g/cc
NpO ₂ ²³⁷ (oxide)	269.047	11.143
Np237	237.0482	20.476
Pu-238	238.0496	19.851
Pu-239	239.0522	19.851
Pu-240	240.0538	19.851
Pu241	241.0568	19.851
Pu-242	242.0587	19.851
Conversion	3.70E+10 Bq/Ci	
365.25 days/year		

Analysis	Sample	Co-60 Bq/mL	Zr-95 Bq/mL	Ru-106 Bq/mL	SB-125 Bq/mL	Cs-134 Bq/mL	Cs-137 Bq/mL	Ce-144 Bq/mL	Eu-155 Bq/mL	Eu-154 Bq/mL
Gr gamma	DJ-23, 030820-031			2.10E+06						
	AD-23, 030820-032		2.50E+05	1.00E+07	8.80E+04	1.10E+05	9.40E+05	1.30E+07	1.50E+05	5.80E+04

Alpha & Beta	Alpha Bq/mL	Beta Bq/mL	Total activity Bq/mL
DJ-23, 030820-031	1.00E+05	6.80E+06	6.90E+06
AD-23, 030820-032	1.50E+08	7.00E+07	2.20E+08

ICP	Np-237 ppb (ng/mL)	Pu-238 ppb (ng/mL)	Pu-239 ppb (ng/mL)	Pu-240 ppb (ng/mL)	Pu-241 ppb (ng/mL)	Pu-242 ppb (ng/mL)	Pu-244 ppb (ng/mL)
DJ-23, 030820-031	1.45E+04	1.83E+02	5.10E+01	<5.0E+0	<5.0E+0	<5.0E+0	<5.0E+0
AD-23, 030820-032	1.71E+06	2.35E+05	3.39E+04	3.56E+03	6.30E+02	<5.0E+01	<5.0E+01


Pu-Alpha Scan TTA extraction	Pu-236/Pu-238 ppm (ug/mL)	Relative error %
AD-23, 030820-032	2.08	11.2

Specific activity Calculation	Factor =	1.13E+13	T1/2 s	M g/mol	Specific activity Ci/g
Co-60			166328640	59.9338222	1130.360
Zr-95			5531328	94.9080427	21469.000
Ru-106			32278176	105.9073269	3306.000
SB-125			87042172.32	124.9052478	1048.000
Cs-134			65160132.48	133.9067134	1294.000
Cs-137			948937032	136.9070835	87.000
Ce-144			24614755.2	143.9136427	3182.800
Eu-155			150248889.4	154.9228894	465.000
Pu-238			2767601520	238.0495534	17.12
Pu-236			895939160	236.0460481	530.00
Eu-154			271174456.8	153.922975	2.64E+02

$$\text{Pu-236/238 ppm} = \frac{(5.80 \text{ MeV Area Counts} \times \text{Pu-236}_{112} \times \text{X236}) \times 1 \text{E6}}{(\text{Full Spectrum Counts} \times \text{Pu-236}_{112} \times \text{X236})}$$

$$\text{Relative Error} = \frac{2 \times (5.80 \text{ MeV Area Counts})^{1/2}}{5.80 \text{ Area Counts}}$$

6.90E+06

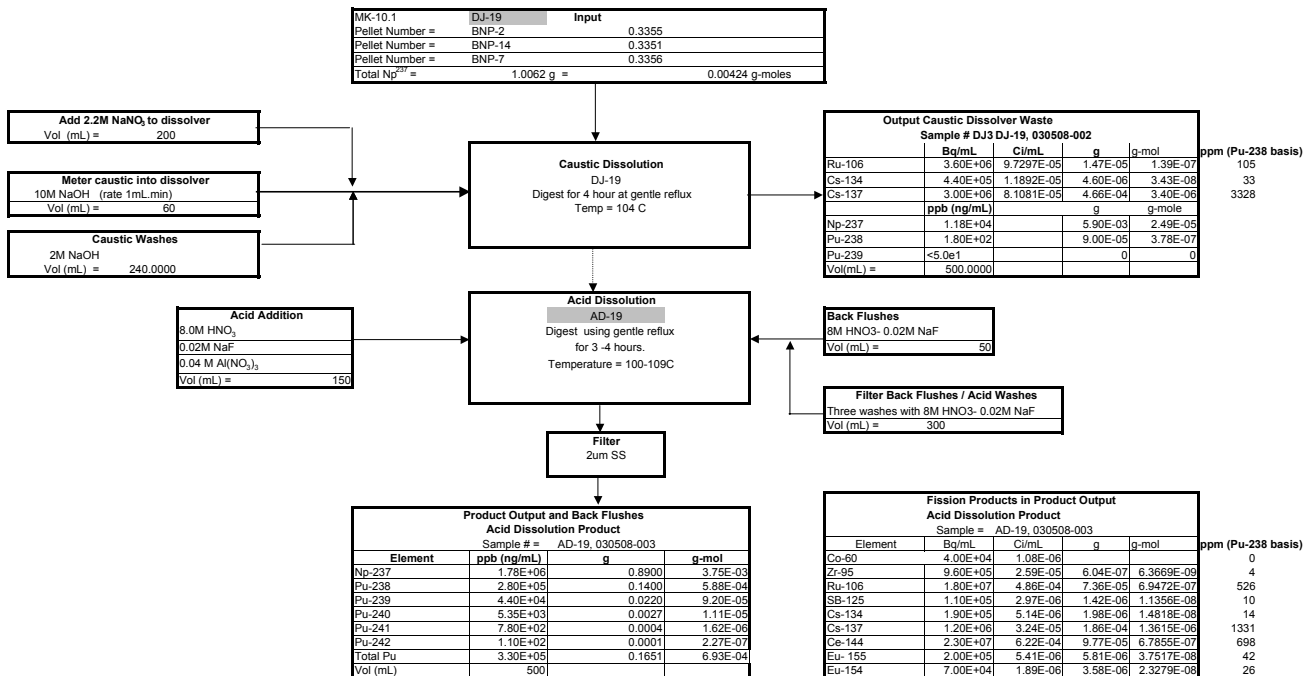

	Target Number	Pellet Number	Dissolution Number	Dissolution Sample Code	% Density	Pellet Vol % NpOX	Pellet Mass Np g	Pellet g-mole Np	Pu-236 ppm	Adjusted Pu-236 ppm
Pellet Input	MK-10.1	BNP-2	19		90.53%	10.01%	0.33550	0.00142	2.01	2.96
Pellet Input	MK-10.1	BNP-14	19		89.54%	10.00%	0.33510	0.00141		
Pellet Input	MK-10.1	BNP-7	19		89.60%	0.10%	0.33560	0.00142		
Total							1.00620	0.00424		
Dejacket Waste	MK-10.1	BNP-2, 14, 7	19	DJ-19, 030508-002			0.00590	0.00002		
Acid Dissol	MK-10.1	BNP-2, 14, 7	19	AD-19, 030508-003			0.89000	0.00375		

	Actual	Predicted (BGS)	Actual/Pred
Np Residual Amount (wt basis) = (Np caustic + Np acid)/ Np input =	0.8904	#DIV/0!	
Pu-238/Total Pu (wt basis) =	0.8480	#DIV/0!	
Conversion of Np to Pu (mol basis) = Pu-238 caustic + Pu-239 caustic + total Pu / Np input =	0.1634	#DIV/0!	
Conversion of Np to FP (mol basis) = (Sum of fission product) in caustic and acid / Np input =	0.0015		
Fractional loss of Np in Liq Waste (wt basis) = Np caustic/ (Np acid + Np dejacket) =	0.0066		
Fractional loss of Pu in Liq Waste (wt basis) = Pu caustic/ (Pu caustic + Pu acid) =	0.0005		

Pu-236 content ppm	Discharge Date	Analysis Date	Time elapsed (t) days	Pu-236 t1/2 years	Pu-236 t1/2 days	Adjusted Pu-236 ppm	Pu-238 t1/2, years	Pu238 t1/2 days	Adjusted Pu-238, g
2.01	11/1/2001	6/6/2003	-582.00	2.85	1040.96	2.96	87.7	32032.425	0.1419

Reference Information	MW	Density g/cc
NpO ₂ ²³⁷ (oxide)	269.047	11.143
Np237	237.0482	20.476
Pu-238	238.0496	19.851
Pu-239	239.0522	19.851
Pu-240	240.0538	19.851
Pu241	241.0568	19.851
Pu-242	242.0587	19.851
Conversion	3.70E+10 Bq/Ci	
	365.25 days/year	

Analysis	Sample	Co-60 Bq/mL	Zr-95 Bq/mL	Ru-106 Bq/mL	SB-125 Bq/mL	Cs-134 Bq/mL	Cs-137 Bq/mL	Ce-144 Bq/mL	Eu-155 Bq/mL	Eu-154 Bq/mL
Gr gamma	DJ-19, 030508-002			3.60E+06						
	AD-19, 030508-003	4.00E+04	9.60E+05	1.80E+07	1.10E+05	1.90E+05	1.20E+06	2.30E+07	2.00E+05	7.00E+04

Alpha & Beta	Alpha Bq/mL	Beta Bq/mL	total activity Bq/mL
DJ-19, 030508-002	5.90E+04	1.19E+07	1.20E+07
AD-19, 030508-003	1.70E+08	1.10E+08	2.80E+08


ICP	Np-237 ppb (ng/mL)	Pu-238 ppb (ng/mL)	Pu-239 ppb (ng/mL)	Pu-240 ppb (ng/mL)	Pu-241 ppb (ng/mL)	Pu-242 ppb (ng/mL)	Pu-244 ppb (ng/mL)
DJ-19, 030508-002	1.18E+04	1.80E+02	<5.0e1	<5.0e1	<5.0e1	<5.0e1	<5.0e1
AD-19, 030508-003	1.78E+06	2.80E+05	4.40E+04	5.35E+03	7.80E+02	1.10E+02	<5.0E1

Pu-Alpha Scan TTA extraction	Pu-236/Pu-238 ppm (ug/mL)	Relative error %
AD-19, 030508-003	2.01	6.2

Specific activity Calculation	Factor =	T1/2 s	M g/mol	Specific activity Ci/g
Co-60	1.13E+13	166328640	59.9338222	1130.360
Zr-95		5531328	94.9080427	21469.00
Ru-106		32278176	105.9073269	3306.00
SB-125		87042172.32	124.9052478	1048.00
Cs-134		65160132.48	133.9067134	1294.00
Cs-137		948937032	136.9070835	87.00
Ce-144		24614755.2	143.9136427	3182.80
Eu-155		150248889.4	154.9228894	465.00
Pu-238		2767601520	238.0495534	17.12
Pu-236		89939160	236.0460481	530.00
Eu-154		271174456.8	153.922975	2.64E+02

Pu-236/238 ppm =	(5.80 MeV Area Counts X Pu-236 ₁₂₂ X 236) X 1E6 (Full Spectrum Counts X Pu-238 ₁₁₂ X 238)
Relative Error =	2 X (5.80 MeV Area Counts) ^{1/2} 5.80 Area Counts

1.20E+07

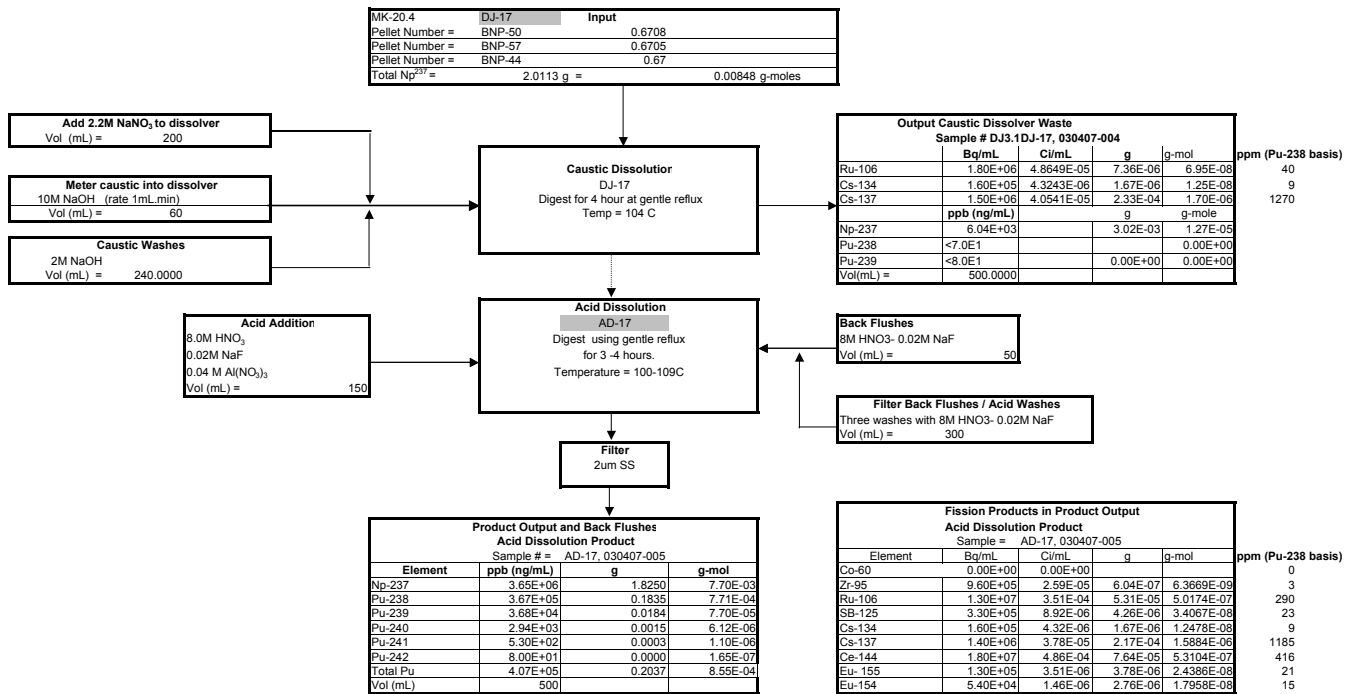

	Target Number	Pellet Number	Dissolution Number	Dissolution Sample Code	% Density	Pellet Vol % NpOX	Pellet Mass Np g	Pellet g-mole Np	Pu-236 ppm	Adjusted Pu-236 ppm
Pellet Input	MK-20.4	BNP-50	17		88.85%	20.01%	0.67080	0.00283	4.19	6.24
Pellet Input	MK-20.4	BNP-57	17		89.82%	20.00%	0.67050	0.00283		
Pellet Input	MK-20.4	BNP-44	17		89.20%	19.99%	0.67000	0.00283		
Total							2.01130	0.00848		
Dejacket Waste	MK-20.4	BNP-50, 57, 44	17	DJ-17, 030407-004			0.00302	0.00079		
Acid Dissol	MK-20.4	BNP-50, 57, 44	17	AD-17, 030407-005			1.82500	0.00770		

	Actual	Predicted (BGS)	Actual/Pred
Np Residual Amount (wt basis) = (Np caustic + Np acid)/ Np input =	0.9089		#DIV/0!
Pu-238/Total Pu (wt basis) =	0.9009		#DIV/0!
Conversion of Np to Pu (mol basis) = Pu-238 caustic + Pu-239 caustic + total Pu / Np input =	0.1008		#DIV/0!
Conversion of Np to FP (mol basis) = (Sum of fission product) in caustic and acid / Np input =	0.0005		
Fractional loss of Np in Liq Waste (wt basis) = Np caustic/ (Np acid + Np dejacket) =	0.0017		
Fractional loss of Pu in Liq Waste (wt basis) = Pu caustic / (Pu caustic + Pu acid) =	0.0000		

Pu-236 content ppm	Discharge Date	Analysis Date	Time elapsed days	Pu-236 t1/2 years	Pu-236 t1/2 days	Adjusted Pu-236 ppm	Pu-238 t1/2, years	Pu238 t1/2 days	Adjusted Pu-238 g
4.19	11/1/2001	6/23/2003	-599.00	2.85	1040.96		87.7	32032.425	0.1859

Reference Information		
	MW	Density
NpO ₂ ²³⁷ (oxide)	269.047	11.143
Np237	237.0482	20.476
Pu-238	238.0496	19.851
Pu-239	239.0522	19.851
Pu-240	240.0538	19.851
Pu241	241.0568	19.851
Pu-242	242.0587	19.851
Conversion	3.70E+10 Bq/Ci	
365.25 days/year		

Analysis	Sample	Co-60 Bq/mL	Zr-95 Bq/mL	Ru-106 Bq/mL	SB-125 Bq/mL	Cs-134 Bq/mL	Cs-137 Bq/mL	Ce-144 Bq/mL	Eu-155 Bq/mL	Eu-154 Bq/mL
Gr gamma	DJ-17, 030407-004			1.80E+06		1.60E+05	1.50E+06			
	AD-17, 030407-005		9.60E+05	1.30E+07	3.30E+05	1.60E+05	1.40E+06	1.80E+07	1.30E+05	5.40E+04

Alpha & Beta	Alpha Bq/mL	Beta Bq/mL	total activity Bq/mL
DJ-17, 030407-004	6.20E+04	2.90E+06	2.96E+06
AD-17, 030407-005	2.40E+06	1.00E+08	3.40E+08

ICP	Np-237 ppb (ng/mL)	Pu-238 ppb (ng/mL)	Pu-239 ppb (ng/mL)	Pu-240 ppb (ng/mL)	Pu-241 ppb (ng/mL)	Pu-242 ppb (ng/mL)	Pu-244 ppb (ng/mL)
DJ-17, 030407-004	6.04E+03	<7.0E1	<8.0E1	<5.0E1	<5.0E1	<5.0E1	<5.0E1
AD-17, 030407-005	3.65E+06	3.67E+05	3.68E+04	2.94E+03	5.30E+02	8.00E+01	<5.0E1


Pu-Alpha Scan TTA extraction	Pu-236/Pu-238 ppm (ug/mL)	Relative error %
AD-17, 030407-005	4.19	2.5

Specific activity Calculation				
Factor =	1.13E+13	T1/2 s	M g/mol	Specific activity Ci/g
Co-60		166328640	59.9338222	1130.360
Zr-95		5531328	94.9080427	21469.00
Ru-106		32278176	105.9073269	3306.00
SB-125		87042172.32	124.9052478	1048.00
Cs-134		65160132.48	133.9067134	1294.00
Cs-137		948937032	136.9070835	87.00
Ce-144		24614755.2	143.9136427	3182.80
Eu-155		150248889.4	154.9228894	465.00
Pu-238		2767601520	238.0495534	17.12
Pu-236		89939160	236.0460481	530.00
Eu-154		271117456.8	153.922975	2.64E+02

Pu-236/238 ppm =
$$\frac{(5.80 \text{ MeV Area Counts} \times \text{Pu-238}_{1/2} \times 236) \times 1E6}{(\text{Full Spectrum Counts} \times \text{Pu-238}_{1/2} \times 238)}$$

Relative Error =
$$\frac{2 \times (5.80 \text{ MeV Area Counts})^{1/2}}{5.80 \text{ Area Counts}}$$

2.96E+06

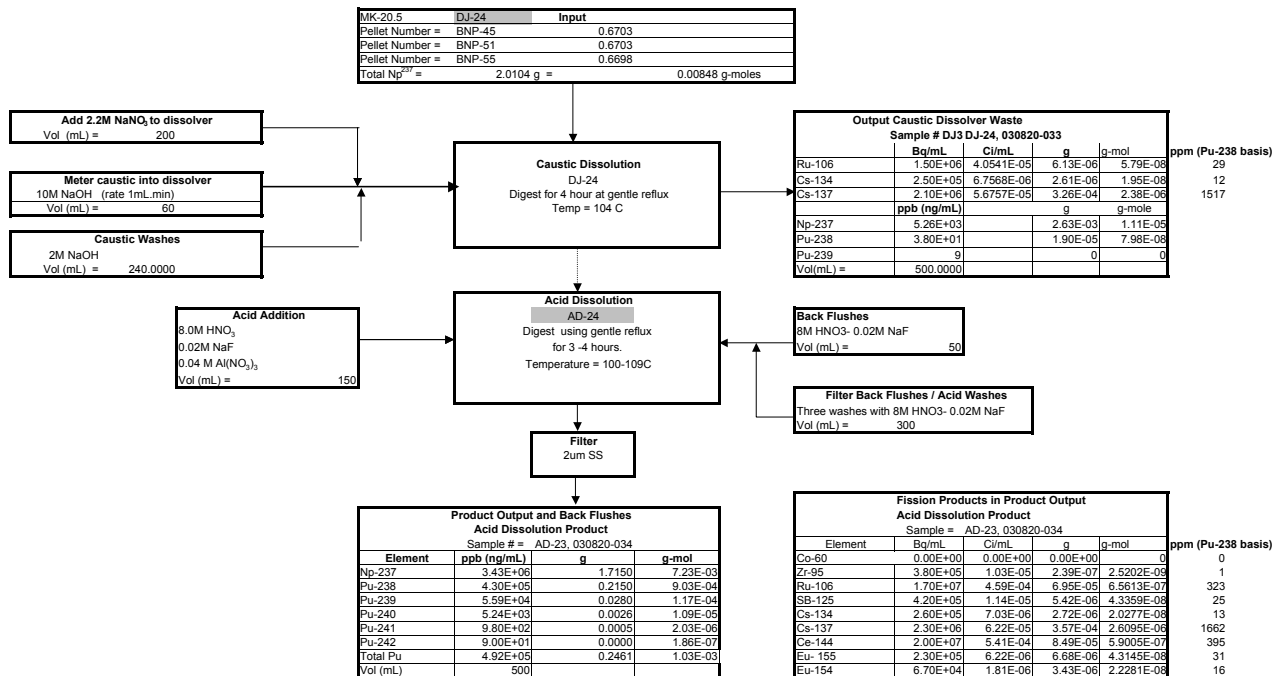

	Target Number	Pellet Number	Dissolution Number	Dissolution Sample Code	% Density	Pellet Vol % NpOX	Pellet Mass Np g	Pellet g-mole Np	Pu-236 ppm	Adjusted Pu-236 ppm
Pellet Input	MK-20.5	BNP-45	24		89.73%	20.00%	0.67030	0.00283	2.89	4.58
Pellet Input	MK-20.5	BNP-51	24		89.08%	20.00%	0.67030	0.00283		
Pellet Input	MK-20.5	BNP-55	24		88.36%	19.99%	0.66980	0.00283		
Total							2.01040	0.00848		
Dejacket Waste	MK-20.5	BNP-45, 51, 55	24	DJ-24, 030820-033			0.00263	0.00001		
Acid Dissol	MK-20.5	BNP-45, 51, 55	24	AD-23, 030820-034			1.71500	0.00723		

	Actual	Predicted (BGS)	Actual/Pred
Np Residual Amount (wt basis) = (Np caustic + Np acid)/Np input =	0.8544		#DIV/0!
Pu-238/Total Pu (wt basis) =	0.8736		#DIV/0!
Conversion of Np to Pu (mol basis) = Pu-238 caustic + Pu-239 caustic + total Pu / Np input =	0.1218		#DIV/0!
Conversion of Np to FP (mol basis) = (Sum of fission product) in caustic and acid / Np input =	0.0008		
Fractional loss of Np in Liq Waste (wt basis) = Np caustic / (Np acid + Np de jacket) =	0.0015		
Fractional loss of Pu in Liq Waste (wt basis) = Pu caustic / (Pu caustic + Pu acid) =	0.0001		

Pu-236 content ppm	Discharge Date	Analysis Date	Time elapsed (t) days	Pu-236 years t1/2	Pu-236 t1/2 days	Adjusted Pu-236 ppm	Pu-238 t1/2, years	Pu238 t1/2 days	Adjusted Pu-238, g
2.89	11/1/2001	9/23/2003	-691.00	2.85	1040.96	4.58	87.7	32032.426	0.2183

Reference Information		
	MW	Density g/cc
NpO ₂ ²³⁷ (oxide)	269.047	11.143
Np237	237.0482	20.476
Pu-238	238.0496	19.851
Pu-239	239.0522	19.851
Pu-240	240.0538	19.851
Pu241	241.0568	19.851
Pu-242	242.0587	19.851
Conversion	3.70E+10 Bq/Ci	
365.25 days/year		

Analysis	Sample	Co-60 Bq/mL	Zr-95 Bq/mL	Ru-106 Bq/mL	SB-125 Bq/mL	Cs-134 Bq/mL	Cs-137 Bq/mL	Ce-144 Bq/mL	Eu-155 Bq/mL	Eu-154 Bq/mL
Gr gamma	DJ-24, 030820-033			1.50E+06		2.50E+05	2.10E+06			
	AD-23, 030820-034		3.80E+05	1.70E+07	4.20E+05	2.60E+05	2.30E+06	2.00E+07	2.30E+05	6.70E+04

Alpha & Beta	Alpha Bq/mL	Beta Bq/mL	total activity Bq/mL
DJ-24, 030820-033	1.90E+04	5.78E+06	5.80E+06
AD-23, 030820-034	2.60E+08	1.20E+08	3.80E+08

ICP	Np-237 ppb (ng/mL)	Pu-238 ppb (ng/mL)	Pu-239 ppb (ng/mL)	Pu-240 ppb (ng/mL)	Pu-241 ppb (ng/mL)	Pu-242 ppb (ng/mL)	Pu-244 ppb (ng/mL)
DJ-24, 030820-033	5.26E+03	3.80E+01	9.00E+00	<5.0E+00	<5.0E+00	<5.0E+00	<5.0E+00
AD-23, 030820-034	3.43E+06	4.30E+05	5.59E+04	5.24E+03	9.80E+02	9.00E+01	<5.0E+01


Pu-Alpha Scan TTA extraction	Pu-236/Pu-238 ppm (ug/mL)	Relative error %
AD-23, 030820-034	2.89	6.3

Specific activity Calculation				
Factor =	1.13E+13	T1/2 s	M g/mol	Specific activity Ci/g
Co-60		166328640	59.9338222	1130.360
Zr-95		5531328	94.9080427	21469.000
Ru-106		32278176	105.9073269	3306.000
SB-125		87042172.32	124.9052478	1048.000
Cs-134		65160132.48	133.9067134	1294.000
Cs-137		948937032	136.9070835	87.000
Ce-144		24614755.2	143.9136427	3182.800
Eu-155		150248889.4	154.9228894	465.000
Pu-238		2767601520	238.049534	17.12
Pu-236		89939160	236.0460481	530.00
Eu-154		271174456.8	153.922975	2.64E+02

Pu-236/238 ppm = $(5.80 \text{ MeV Area Counts} \times \text{Pu-236}_{122} \times 236) \times 1 \text{E6}$
(Full Spectrum Counts X Pu-238₁₂₂ X 238)

Relative Error = $2 \times (5.80 \text{ MeV Area Counts})^{1/2}$
5.80 Area Counts

5.80E+06

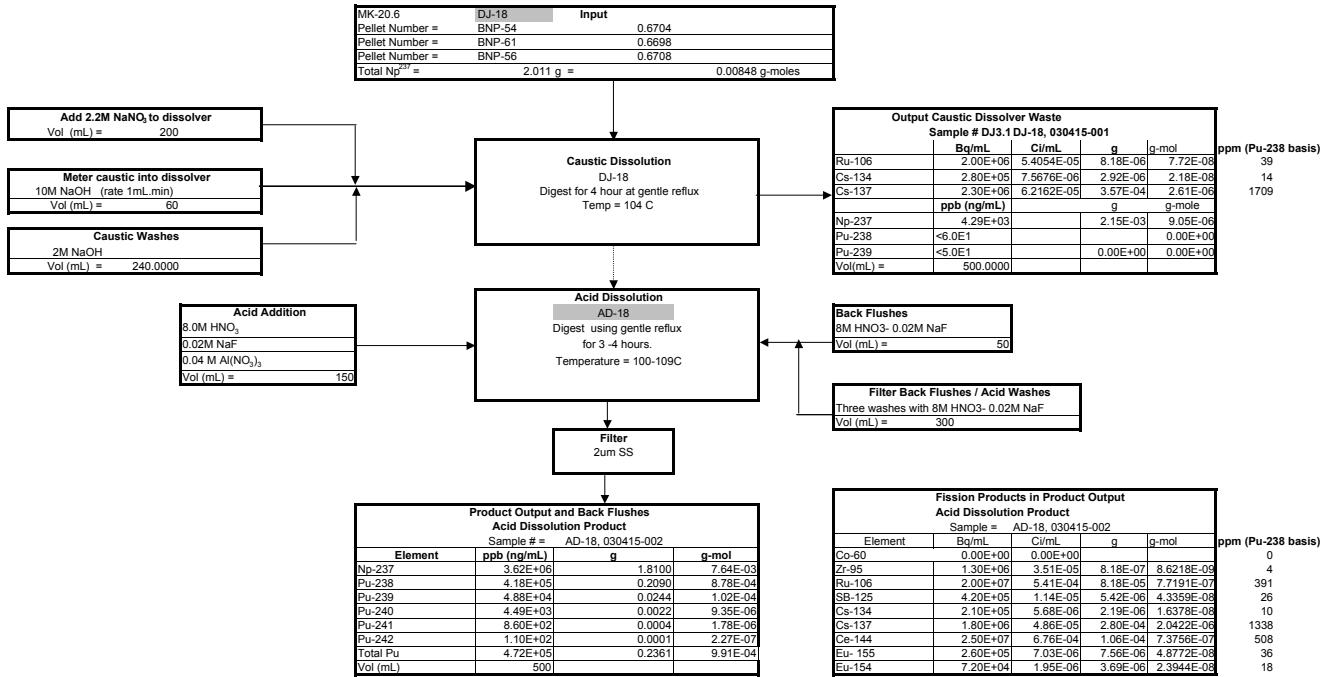

	Target Number	Pellet Number	Dissolution Number	Dissolution Sample Code	% Density	Pellet Vol % NpOX	Pellet Mass Np g	Pellet g-mole Np	Pu-236 ppm	Adjusted Pu-236 ppm
Pellet Input	MK-20.6	BNP-54	18		88.80%	20.01%	0.67040	0.00283	3.6	5.36
Pellet Input	MK-20.6	BNP-61	18		89.02%	19.99%	0.66980	0.00283		
Pellet Input	MK-20.6	BNP-56	18		88.08%	20.01%	0.67080	0.00283		
Total							2.01100	0.00848		
Dejacket Waste	MK-20.6	BNP-54, 61, 56	18	DJ-18, 030415-001			0.00215	0.00085		
Acid Dissol	MK-20.6	BNP-54, 61, 56	18	AD-18, 030415-002			1.81000	0.00764		

	Actual	Predicted (BGS)	Actual/Pred
Np Residual Amount (wt basis) = (Np caustic + Np acid) / Np input =	0.9011		#DIV/0!
Pu-238/Total Pu (wt basis) =	0.8851		#DIV/0!
Conversion of Np to Pu (mol basis) = Pu-238 caustic + Pu-239 caustic + total Pu / Np input =	0.1169		#DIV/0!
Conversion of Np to FP (mol basis) = (Sum of fission product) in caustic and acid / Np input =	0.0008		
Fractional loss of Np in Liq Waste (wt basis) = Np caustic / (Np acid + Np dejacket) =	0.0012		
Fractional loss of Pu in Liq Waste (wt basis) = Pu caustic / (Pu caustic + Pu acid) =	0.0000		

Pu-236 content ppm	Discharge Date	Analysis Date	Time elapsed (t) days	Pu-236 t1/2 years	Pu-236 t1/2 days	Adjusted Pu-236 ppm	Pu-238 t1/2, years	Pu-238 t1/2 days	Adjusted Pu-238, g
3.6	11/1/2001	6/23/2003	-599.00	2.85	1040.96	5.36	87.7	32032.425	0.2117

Reference Information		
	MW	Density g/cc
NpO ₂ ²³⁷ (oxide)	269.047	11.143
Np237	237.0482	20.476
Pu-238	238.0496	19.851
Pu-239	239.0522	19.851
Pu-240	240.0538	19.851
Pu-241	241.0568	19.851
Pu-242	242.0587	19.851
Conversion	3.70E+10 Bq/Ci	
	365.25 days/year	

Analysis	Sample	Co-60 Bq/mL	Zr-95 Bq/mL	Ru-106 Bq/mL	SB-125 Bq/mL	Cs-134 Bq/mL	Cs-137 Bq/mL	Ce-144 Bq/mL	Eu-155 Bq/mL	Eu-154 Bq/mL
Gr gamma	DJ-18, 030415-001			2.00E+06		2.80E+05	2.30E+06			
	AD-18, 030415-002		1.30E+06	2.00E+07	4.20E+05	2.10E+05	1.80E+06	2.50E+07	2.60E+05	7.20E+04

Alpha & Beta	Alpha Bq/mL	Beta Bq/mL	Total activity Bq/mL
DJ-18, 030415-001	2.60E+04	6.77E+06	6.80E+06
AD-18, 030415-002	2.70E+08	1.10E+08	3.80E+08


ICP	Np-237 ppb (ng/mL)	Pu-238 ppb (ng/mL)	Pu-239 ppb (ng/mL)	Pu-240 ppb (ng/mL)	Pu-241 ppb (ng/mL)	Pu-242 ppb (ng/mL)	Pu-244 ppb (ng/mL)
DJ-18, 030415-001	4.29E+03	<6.0E1	<5.0E1	<5.0E1	<5.0E1	<5.0E1	<5.0E1
AD-18, 030415-002	3.62E+06	4.18E+05	4.88E+04	4.49E+03	8.60E+02	1.10E+02	<5.0E1

Pu-Alpha Scan TTA extraction	Pu-236/Pu-238 ppm (ug/mL)	Relative error %
AD-18, 030415-002	3.6	3.7

Specific activity Calculation				
Factor =	1.13E+13	T1/2 s	M g/mol	Specific activity Ci/g
Co-60		166328640	59.9338222	1130.360
Zr-95		5531328	94.9080427	21469.00
Ru-106		32278176	105.9073269	3306.00
SB-125		87042172.32	124.9052478	1048.00
Cs-134		65160132.48	133.9067134	1294.00
Cs-137		948937032	136.9070835	87.00
Ce-144		24614755.2	143.9136427	3182.80
Eu-155		150248889.4	154.9228894	465.00
Pu-238		2767801520	238.0495534	17.12
Pu-239		89939160	239.0460481	530.00
Eu-154		271174456.8	153.922975	2.64E+02

Pu-236/238 ppm =	(5.80 MeV Area Counts X Pu-238 ₁₀₀ X 236) X 1E6 (Full Spectrum Counts X Pu-238 ₁₀₂ X 238)
Relative Error =	2 X (5.80 MeV Area Counts) ^{1/2} 5.80 Area Counts

6.80E+06

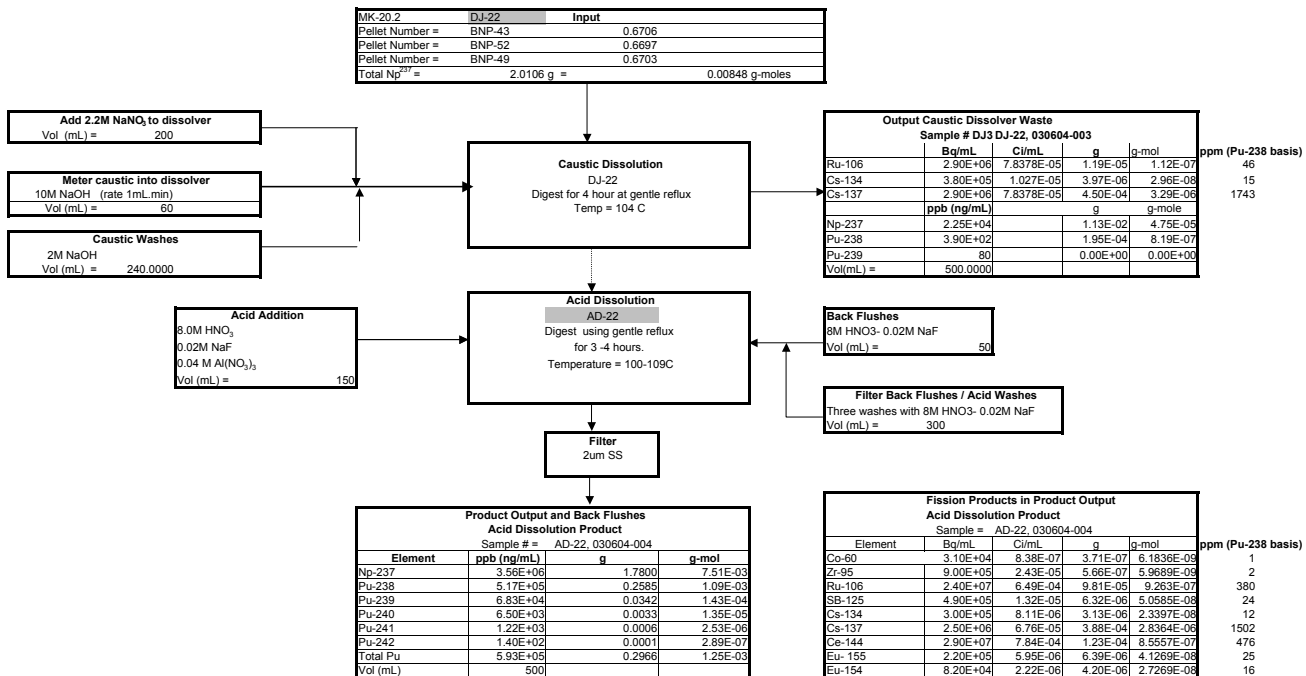

	Target Number	Pellet Number	Dissolution Number	Dissolution Sample Code	% Density	Pellet Vol % NpOX	Pellet Mass Np g	Pellet g-mole Np	Pu-236 ppm	Adjusted Pu-236 ppm
Pellet Input	MK-20.2	BNP-43	22		87.78%	20.01%	0.67060	0.00283	2.38	3.58
Pellet Input	MK-20.2	BNP-52	22		88.83%	19.99%	0.66970	0.00283		
Pellet Input	MK-20.2	BNP-49	22		89.17%	20.00%	0.67030	0.00283		
Total							2.01060	0.00848		
Dejacket Waste	MK-20.2	BNP-15, 23, 20	22	DJ-22, 030604-003			0.01125	0.00005		
Acid Dissol	MK-20.2	BNP-15, 23, 20	22	AD-22, 030604-004			1.78000	0.00751		

	Actual	Predicted (BGS)	Actual/Pred
Np Residual Amount (wt basis) = (Np caustic + Np acid) / Np input =	0.8909		#DIV/0!
Pu-238/Total Pu (wt basis) =	0.8717		#DIV/0!
Conversion of Np to Pu (mol basis) = Pu-238 caustic + Pu-239 caustic + total Pu / Np input =	0.1469		#DIV/0!
Conversion of Np to FP (mol basis) = (Sum of fission product) in caustic and acid / Np input =	0.0010		
Fractional loss of Np in Liq Waste (wt basis) = Np caustic / (Np acid + Np dejacket) =	0.0063		
Fractional loss of Pu in Liq Waste (wt basis) = Pu caustic / (Pu caustic + Pu acid) =	0.0007		

Pu-236 content ppm	Discharge Date	Analysis Date	Time elapsed (t) days	Pu-236 t1/2 years	Pu-236 t1/2 days	Adjusted Pu-236 ppm	Pu-238 t1/2 years	Pu238 t1/2 days	Adjusted Pu-238 g
2.38	11/1/2001	7/7/2003	-613.00	2.85	1040.96	3.58	87.7	32032.425	0.2621

Reference Information	MW	Density g/cc
NpO ₂ ²³⁷ (oxide)	269.047	11.143
Np237	237.0482	20.476
Pu-238	238.0496	19.851
Pu-239	239.0522	19.851
Pu-240	240.0538	19.851
Pu241	241.0568	19.851
Pu-242	242.0587	19.851
Conversion	3.70E+10 Bq/Ci	
	365.25 days/year	

Analysis	Sample	Co-60 Bq/mL	Zr-95 Bq/mL	Ru-106 Bq/mL	SB-125 Bq/mL	Cs-134 Bq/mL	Cs-137 Bq/mL	Ce-144 Bq/mL	Eu-155 Bq/mL	Eu-154 Bq/mL
Gr gamma	DJ-22, 030604-003			2.90E+06		3.80E+05	2.90E+06			
	AD-22, 030604-004	3.10E+04	9.00E+05	2.40E+07	4.90E+05	3.00E+05	2.50E+06	2.90E+07	2.20E+05	8.20E+04

Alpha & Beta	Alpha Bq/mL	Beta Bq/mL	total activity Bq/mL
DJ-22, 030604-003	2.00E+05	9.60E+06	9.80E+06
AD-22, 030604-004	2.90E+08	1.40E+08	4.30E+08


ICP	Np-237 ppb (ng/mL)	Pu-238 ppb (ng/mL)	Pu-239 ppb (ng/mL)	Pu-240 ppb (ng/mL)	Pu-241 ppb (ng/mL)	Pu-242 ppb (ng/mL)	Pu-244 ppb (ng/mL)
DJ-22, 030604-003	2.25E+04	3.90E+02	8.00E+01	<5.0E+01	<5.0E+01	<5.0E+01	<5.0E+01
AD-22, 030604-004	3.56E+06	5.17E+05	6.83E+04	6.50E+03	1.22E+03	1.40E+02	<5.0E+01

Pu-Alpha Scan TTA extraction	Pu-236/Pu-238 ppm (ug/mL)	Relative error %
AD-22, 030604-004	2.38	2.7

Specific activity Calculation	Factor =	T1/2 s	M g/mol	Specific activity Ci/g
Co-60	1.13E+13	166328640	59.9338222	1130.360
Zr-95		5531328	94.9080427	21469.000
Ru-106		32278176	105.9073269	3306.000
SB-125		87042172.32	124.9052478	1048.000
Cs-134		65160132.48	133.9067134	1294.000
Cs-137		948937032	136.9070835	87.000
Ce-144		24614755.2	143.9136427	3182.800
Eu-155		150248889.4	154.9228894	465.000
Pu-238		2767601520	238.0495534	17.12
Pu-239		89939160	238.0460481	530.000
Eu-154		271174456.8	153.922975	2.64E+02

Pu-236/238 ppm = $(5.80 \text{ MeV Area Counts} \times \text{Pu-236}_{112} \times \text{X 1E6}) / (\text{Full Spectrum Counts} \times \text{Pu-238}_{112} \times \text{X 238})$

Relative Error = $2 \times (5.80 \text{ MeV Area Counts})^{1/2} / 5.80 \text{ Area Counts}$

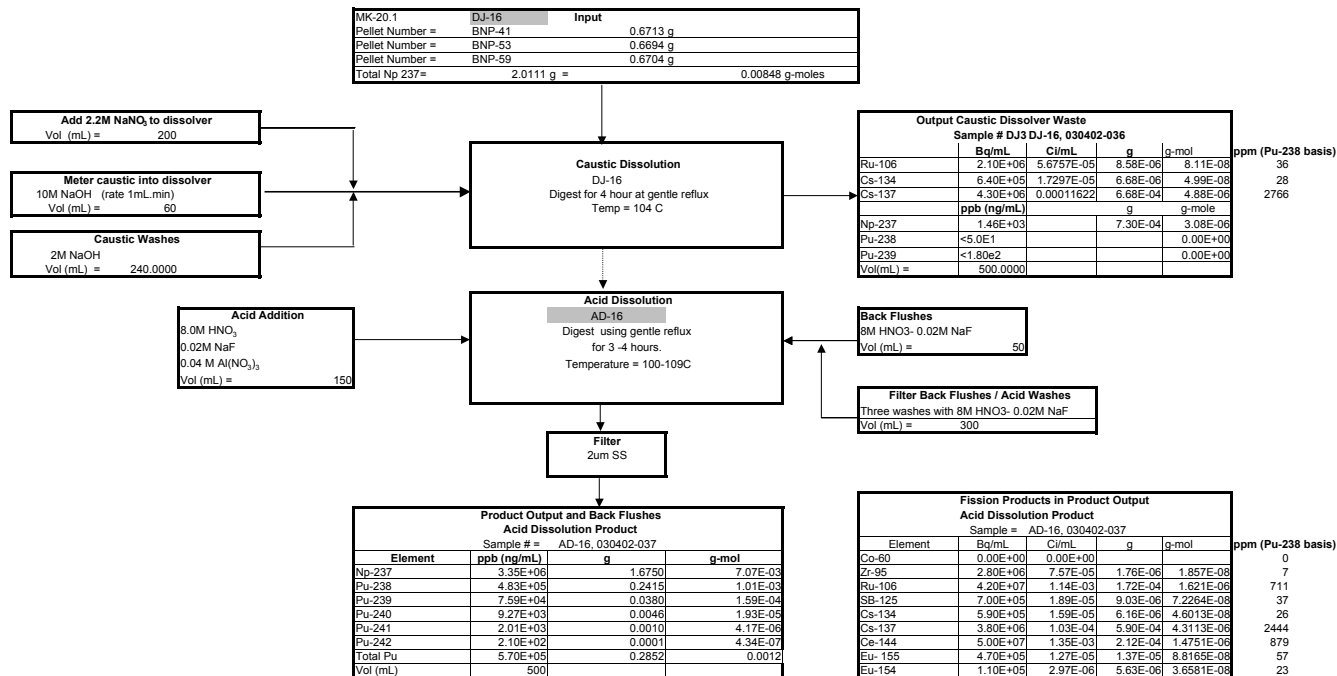

	Target Number	Pellet Number	Dissolution Number	Dissolution Sample Code	% Density	Pellet Vol % NpOX	Pellet Mass Np g	Pellet g-mole Np	Pu-236 ppm	Adjusted Pu-236 ppm
Pellet Input	MK-20.1	BNP-41	16		88.97%	20.03%	0.67130	0.00283	2.75	3.88
Pellet Input	MK-20.1	BNP-53	16		89.00%	19.98%	0.66940	0.00282		
Pellet Input	MK-20.1	BNP-59	16		89.18%	20.00%	0.67040	0.00283		
Total							2.01110	0.00848		
Dejacket Waste	MK-20.1	BNP-41, 53, 59	16	DJ-16, 030402-036			0.00073	0.00000		
Acid Dissol	MK-20.1	BNP-41, 53, 59	16	AD-16, 030402-037			1.67500	0.00707		

	Actual	Predicted (BGS)	Actual/Pred
Np Residual Amount (wt basis) = (Np caustic + Np acid) / Np input =	0.8332		#DIV/0!
Pu-238/Total Pu (wt basis) =	0.8468		#DIV/0!
Conversion of Np to Pu (mol basis) = Pu-238 caustic + Pu-239 caustic + total Pu / Np input =	0.1411		#DIV/0!
Conversion of Np to FP (mol basis) = Sum of fission product in caustic and acid / Np input =	0.0015		
Fractional loss of Np in Liq Waste (wt basis) = Np caustic / (Np acid + Np dejacket) =	0.0004		
Fractional loss of Pu in Liq Waste (wt basis) = Pu caustic / (Pu caustic + Pu acid) =	0.0000		

Pu-236 content ppm	Discharge Date	Analysis Date	Time elapsed (t) days	Pu-236 years	t1/2 years	Pu-236 days	t1/2 days	Adjusted Pu-236 ppm	Pu-238 t1/2, years	Pu-238 days	t1/2 days	Adjusted Pu-238, g
2.75	11/1/2001	4/2/2003	-517.00	2.85	1040.96			3.88	87.7	32032.425		0.2442

Reference Information	MW	Density g/cc
NpO ₂ ²³⁷ (oxide)	269.047	11.143
Np237	237.0482	20.476
Pu-238	238.0496	19.851
Pu-239	239.0522	19.851
Pu-240	240.0538	19.851
Pu241	241.0568	19.851
Pu-242	242.0587	19.851
Conversion	3.70E+10 Bq/Ci	
365.25 days/year		

Analysis	Sample	Co-60 Bq/mL	Zr-95 Bq/mL	Ru-106 Bq/mL	SB-125 Bq/mL	Cs-134 Bq/mL	Cs-137 Bq/mL	Ce-144 Bq/mL	Eu-155 Bq/mL	Eu-154 Bq/mL
Gr gamma	DJ-16, 030402-036			2.10E+06		6.40E+05	4.30E+06			
	AD-16, 030402-037		2.80E+06	4.20E+07	7.00E+05	5.90E+05	3.80E+06	5.00E+07	4.70E+05	1.10E+05


Alpha & Beta	Alpha Bq/mL	Beta Bq/mL	total activity Bq/mL
DJ-16, 030402-036	1.20E+04	9.79E+06	9.80E+06
AD-16, 030402-037	3.40E+08	2.30E+08	5.70E+08

ICP	Np-237 ppb (ng/mL)	Pu-238 ppb (ng/mL)	Pu-239 ppb (ng/mL)	Pu-240 ppb (ng/mL)	Pu-241 ppb (ng/mL)	Pu-242 ppb (ng/mL)	Pu-244 ppb (ng/mL)
DJ-16, 030402-036	1.46E+03	<5.0E1	<1.80E2	<5.0E1	<5.0E1	<5.0E1	<5.0E1
AD-16, 030402-037	3.35E+06	4.83E+05	7.59E+04	9.27E+03	2.01E+03	2.10E+02	<5.0E1

Pu-Alpha Scan TTA extraction	Pu-236/Pu-238 ppm (ug/mL)	Relative error %
AD-16, 030402-037	2.75	5.12

Specific activity Calculation	Factor =	T1/2 s	M g/mol	Specific activity Ci/g
Co-60	1.13E+13	166328640	59.9338222	1130.360
Zr-95		5531328	94.9080427	21469.00
Ru-106		32278176	105.9073269	3306.00
SB-125		87042172.32	124.9052478	1048.00
Cs-134		65160132.48	133.9087134	1294.00
Cs-137		948937032	136.9070835	87.00
Ce-144		24614755.2	143.9136427	3182.80
Eu-155		150248889.4	154.9228894	465.00
Pu-238		2767601520	238.0495534	17.12
Pu-236		89939160	236.0460481	530.00
Eu-154		271174456.8	153.922975	2.64E+02

Pu-236/238 ppm =	(5.80 MeV Area Counts X Pu-236 ₁₂₂ X 236) X 1E6 (Full Spectrum Counts X Pu-238 ₁₂₂ X 238)
Relative Error =	2 X (5.80 MeV Area Counts) ^{1/2} 5.80 Area Counts

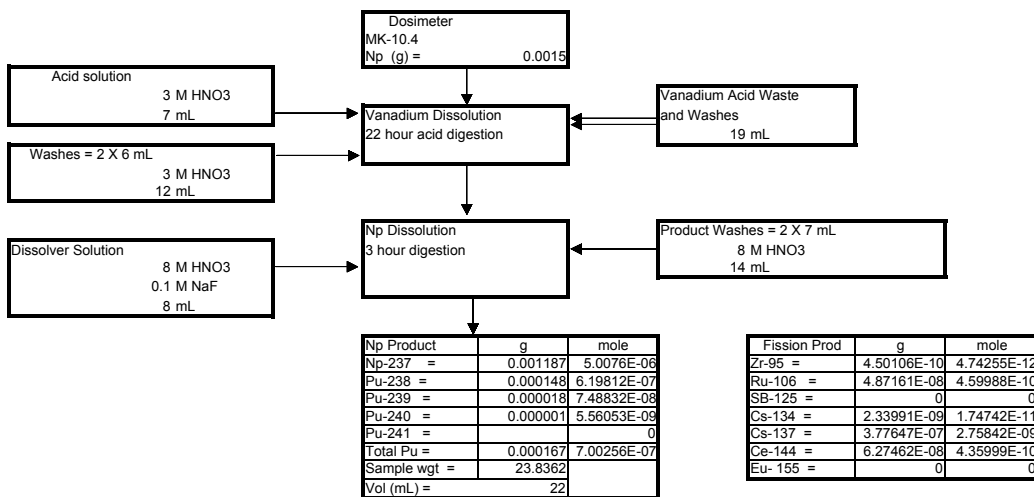

Target	Diss #	Dosimeter Np input g	Np input mole	Vial Tare g	Solution & Vial g	Solution weight g	Np Prod. g	Np Prod. mole	Pu-238 g	Pu-236 ppm	Adjusted Pu-236 ppm	Total Pu g
MK-10.4	ADD-26	0.001500	6.33E-06	27.1444	50.9806	23.836200	0.001187	5.01E-06	0.000148	1.840000	2.764341	0.000167
	DDJ-26			27.1495	45.4386	18.2891						

	Actual	Predicted (BGS)	Actual/Pred
Np Residual Amount (wt basis) Np prod / Np in	=	0.7914	#DIV/0!
Pu-238/Total Pu (wt basis)	=	0.8847	#DIV/0!
Conversion of Np to Pu (mol basis) = Pu total/ Np in	=	0.1107	#DIV/0!
Conversion of Np to FP (mol basis) = Fp prod/Np in	=	0.0006	
Fractional loss of Np in Liq Waste (wt basis)	=	NA	
Fractional loss of Pu in Liq Waste (wt basis)	=	NA	


Pu-236 content ppm	Discharge Date	Analysis Date	Time elapsed (t) days	Pu-236 t1/2 years	t1/2 days	Adjusted Pu-236 ppm
1.84	11/1/2001	7/7/2003	-613.00	2.86	1043.88	2.76

Analysis Date	Time elapsed (t) days	Pu-238 t1/2, years	Pu238, t1/2 days	Adjusted Pu-238, g
5/28/2003	-573.00	87.7	32032.425	0.000149

Analysis	Sample	Co-60 Bq/g	Zr-95 Bq/g	Ru-106 Bq/g	SB-125 Bq/g	Cs-134 Bq/g	Cs-137 Bq/g	Ce-144 Bq/g	Eu-155 Bq/g
Gr gamma	ADD-26, 030429-059		1.50E+04	2.50E+05		4.70E+03	5.10E+04	3.10E+05	
Alpha & Beta	Sample	Alpha Bq/g	Beta Bq/mL	total activity Bq/m	alpha PHA	Pu238, Bq			
	ADD-26, 030429-059	3.80E+06	Beta Bq/g	total activity Bq/g					
ICP	Sample	Np-237 ppb (ng/g)	Pu-238 ppb (ng/g)	Pu-239 ppb (ng/g)	Pu-240 ppb (ng/g)	Pu-241 ppb (ng/g)	Pu-242 ppb (ng/g)	Pu-244 ppb (ng/g)	
	ADD-26, 030429-059	4.98E+04	6.19E+03	7.51E+02	5.60E+01	<4.00E+01	<4.00E+01	<4.00E+01	
Pu-Alpha Scan TTA extraction	Sample	Pu-236/Pu-238 ppm (ug/mL)	Relative error %						
	ADD-26, 030429-059	1.84	6.2						

Reference Information			Reference Information			
	MW	Density g/cc	Specific activity Calculation			
NpO2	269.047	11.143	Factor =	1.13E+13	T1/2 s	M g/mol
Np237	237.0482	20.476				Specific activity Ci/g
Pu238	238.0496	19.851	Co-60		166328640	59.9338222
Pu239	239.0522	19.851	Zr-95		5531328	94.9080427
Pu240	240.0538	19.851	Ru-106		32278176	105.9073269
Pu241	241.0568	19.851	SB-125		87042172.32	124.9052478
Pu242	242.0587	19.851	Cs-134		65160132.48	133.9067134
Conversion	3.70E+10 Bq/Ci		Cs-137		948937032	136.9070835
365.25 days/year			Ce-144		24614755.2	143.9136427
N = N ⁰ *exp -(ln2/t _{1/2} * t)			Eu-155		150248889.4	154.9228894
			Pu-238		2767601520	238.0495534

Pu-236/238 ppm =	(5.80 MeV Area Counts X Pu-236 _{t1/2} X 236) X 1E6 (Full Spectrum Counts X Pu-238 _{t1/2} X 238)
Relative Error =	2 X (5.80 MeV Area Counts) ^{1/2} 5.80 Area Counts

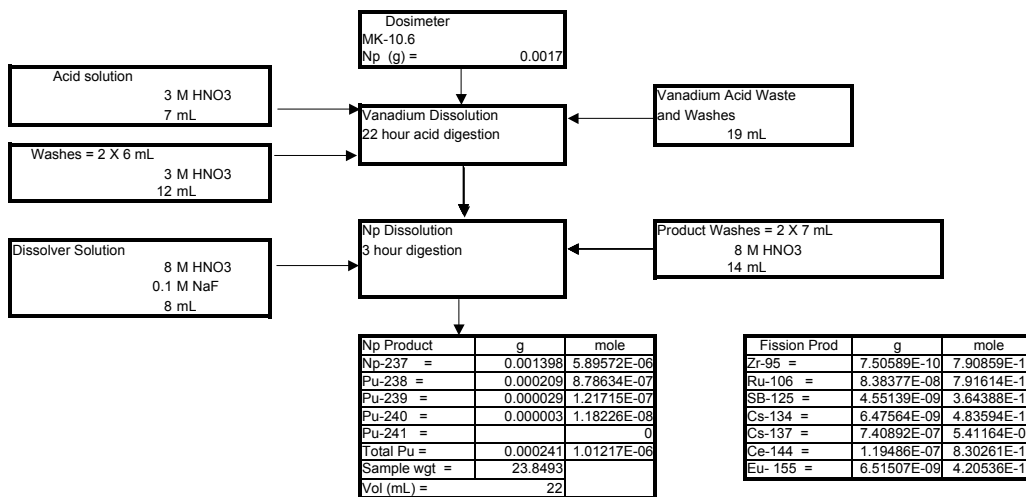

Target	Diss #	Dosimeter Np input g	Np input mole	Vial Tare g	Solution & Vial g	Solution weight g	Np Prod. g	Np Prod. mole	Pu-238 g	Pu-238 ppm	Adjusted Pu-238 ppm	Total Pu g
MK-10.6	ADD-27	0.001700	7.17E-06	26.9450	50.7943	23.849300	0.001398	5.90E-06	0.000209	1.590000	2.388751	0.000241
	DDJ-27			27.2825	46.4323	19.1498						

	Actual	Predicted (BGS)	Actual/Pred
Np Residual Amount (wt basis) Np prod / Np in	= 0.8221		#DIV/0!
Pu-238/Total Pu (wt basis)	= 0.8675		#DIV/0!
Conversion of Np to Pu (mol basis) = Pu total/ Np in	= 0.1411		#DIV/0!
Conversion of Np to FP (mol basis) = Fp prod/Np in	= 0.0010		
Fractional loss of Np in Liq Waste (wt basis)	= NA		
Fractional loss of Pu in Liq Waste (wt basis)	= NA		

Pu-236 content ppm	Discharge Date	Analysis Date	Time elapsed (t) days	Pu-236 t1/2 years	t1/2 days	Adjusted Pu-236 ppm
1.59	11/1/2001	7/7/2003	-613.00	2.86	1043.88	2.39


Analysis Date	Time elapsed (t) days	Pu-238 t1/2, years	Pu238, t1/2 days	Adjusted Pu-238, g
5/28/2003	-573.00	87.7	32032.425	0.000212

Analysis	Sample	Co-60 Bq/g	Zr-95 Bq/g	Ru-106 Bq/g	SB-125 Bq/g	Cs-134 Bq/g	Cs-137 Bq/g	Ce-144 Bq/g	Eu-155 Bq/g
Gr gamma	ADD-27, 030429-060		2.50E+04	4.30E+05	7.40E+03	1.30E+04	1.00E+05	5.90E+05	4.70E+03
Alpha & Beta	Sample	Alpha Bq/g	Beta Bq/g	total activity Bq/g	alpha PHA	Pu238, Bq			
	ADD-27, 030429-060	5.30E+06	2.70E+06	8.00E+06					
ICP	Sample	Np-237 ppb (ng/g)	Pu-238 ppb (ng/g)	Pu-239 ppb (ng/g)	Pu-240 ppb (ng/g)	Pu-241 ppb (ng/g)	Pu-242 ppb (ng/g)	Pu-244 ppb (ng/g)	
	ADD-27, 030429-060	5.86E+04	8.77E+03	1.22E+03	1.19E+02	<3.97E+01	<3.97E+01	<3.97E+01	
Pu-Alpha Scan TTA extraction	Sample	Pu-236/Pu-238 ppm (ug/mL)	Relative error %						
	ADD-27, 030429-060	1.59	5						

Reference Information	MW	Density g/cc
NpO2	269.047	11.143
Np237	237.0482	20.476
Pu238	238.0496	19.851
Pu239	239.0522	19.851
Pu240	240.0538	19.851
Pu241	241.0568	19.851
Pu242	242.0587	19.851
Conversion	3.70E+10 Bq/Ci	
365.25 days/year		
$N = N^0 \cdot \exp(-\ln 2/t_{1/2} \cdot t)$		

Reference Information	Specific activity Calculation	Factor =	T1/2 s	M g/mol	Specific activity Ci/g
Co-60		1.13E+13	166328640	59.9338222	1130.670
Zr-95			5531328	94.9080427	21469.000
Ru-106			32278176	105.9073269	3306.000
SB-125			87042172.32	124.9052478	1048.000
Cs-134			65160132.48	133.9067134	1294.000
Cs-137			948937032	136.9070835	87.000
Ce-144			24614755.2	143.9136427	3182.800
Eu-155			150248889.4	154.9228894	465.000
Pu-238			2767601520	238.0495534	17.119

Pu-236/238 ppm =	(5.80 MeV Area Counts X Pu-236 _{t1/2} X 236) X 1E6 (Full Spectrum Counts X Pu-238 _{t1/2} X 238)
Relative Error =	$2 \times (5.80 \text{ MeV Area Counts})^{1/2}$ 5.80 Area Counts

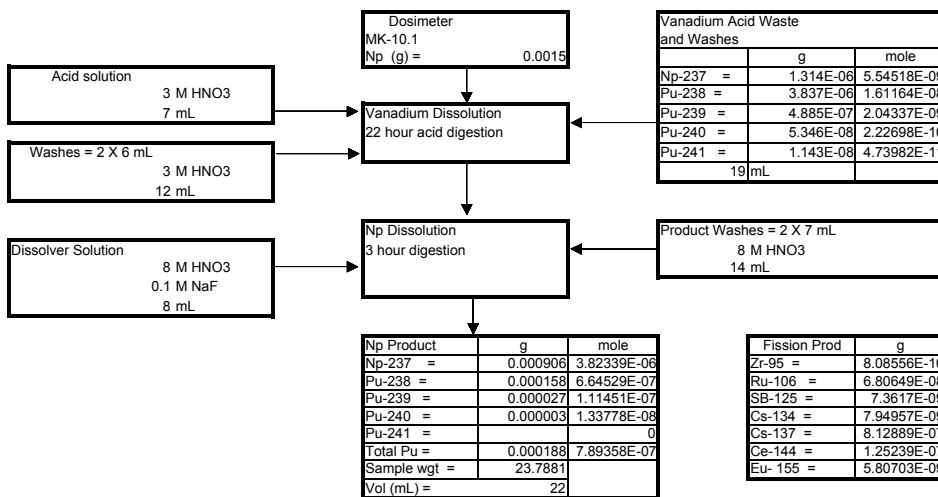

Target	Diss #	Dosimeter Np input g	Np input mole	Vial Tare g	Solution & Vial g	Solution weight g	Np Prod. g	Np Prod. mole	Pu-238 g	Pu-236 ppm	Adjusted Pu-236 ppm	Total Pu g
MK-10.1	ADD-25	0.001500	6.33E-06	27.0241	50.8122	23.788100	0.000906	3.82E-06	0.000158	2.540000	3.790738	0.000188
	DJJ-25			27.1424	48.1069	20.964500	0.0000131					
0.000919												

	Actual	Predicted (BGS)	Actual/Pred
Np Residual Amount (wt basis) Np prod / Np in	= 0.6042		#DIV/0!
Pu-238/Total Pu (wt basis)	= 0.8412		#DIV/0!
Conversion of Np to Pu (mol basis) = Pu total/ Np in	= 0.1247		#DIV/0!
Conversion of Np to FP (mol basis) = Fp prod/Np in	= 0.0012		
Fractional loss of Np in Liq Waste (wt basis)	= NA		
Fractional loss of Pu in Liq Waste (wt basis)	= NA		

Pu-236 content ppm	Discharge Date	Analysis Date	Time elapsed (t) days	Pu-236 t1/2 years	t1/2 days	Adjusted Pu-236 ppm
2.54	11/1/2001	6/27/2003	-603.00	2.86	1043.88	3.79

Analysis Date	Time elapsed (t) days	Pu-238 t1/2, years	Pu238, t1/2 days	Adjusted Pu-238, g
5/28/2003	-573.00	87.7	32032.425	0.000160

Analysis	Sample	Co-60 Bq/g	Zr-95 Bq/g	Ru-106 Bq/g	SB-125 Bq/g	Cs-134 Bq/g	Cs-137 Bq/g	Ce-144 Bq/g	Eu-155 Bq/g
Gr gamma	ADD-25, 030429-058		2.70E+04	3.50E+05	1.20E+04	1.60E+04	1.10E+05	6.20E+05	4.20E+03
	DDJ-25, 030820-037	7.30E+03		3.20E+04		2.00E+03	6.00E+03		
Alpha & Beta	Sample	Alpha Bq/g	Beta Bq/g	total activity Bq/g	alpha PHA	Pu238, Bq			
	ADD-25, 030429-058	4.30E+06	2.50E+06	6.80E+06					
	DDJ-25, 030820-037	1.10E+05	2.00E+04	1.30E+05					
ICP	Sample	Pu-237 ppb (ng/g)	Pu-238 ppb (ng/g)	Pu-239 ppb (ng/g)	Pu-240 ppb (ng/g)	Pu-241 ppb (ng/g)	Pu-242 ppb (ng/g)	Pu-244 ppb (ng/g)	
	ADD-25, 030429-058	3.81E+04	6.65E+03	1.12E+03	1.35E+02	<3.97E+01	<3.97E+01	<3.97E+01	
	DDJ-25, 030820-037	6.27E+02	1.83E+02	2.33E+01	2.55E+00	5.45E-01	<4.55E-01	<4.55E-01	
Pu-Alpha Scan TTA extraction	Sample	Pu-236/Pu-238 ppm (ug/mL)	Relative error %						
	ADD-25, 030429-058	2.54	4.2						


Reference Information	MW	Density g/cc
NpO2	269.047	11.143
Np237	237.0482	20.476
Pu238	238.0496	19.851
Pu239	239.0522	19.851
Pu240	240.0538	19.851
Pu241	241.0568	19.851
Pu242	242.0587	19.851
Conversion	3.70E+10 Bq/Ci	
365.25 days/year		

$$N = N^0 \cdot \exp(-(\ln 2/t_{1/2} \cdot t))$$

Reference Information	Specific activity Calculation	Factor =	T1/2 s	M g/mol	Specific activity Ci/g
Co-60		1.13E+13	166328640	59.9338222	1130.670
Zr-95			5531328	94.9080427	21469.000
Ru-106			32278176	105.9073269	3306.000
SB-125			87042172.32	124.9052478	1048.000
Cs-134			65160132.48	133.9067134	1294.000
Cs-137			948937032	136.9070835	87.000
Ce-144			24614755.2	143.9136427	3182.800
Eu-155			150248889.4	154.9228894	465.000
Pu-238			2767601520	238.0495534	17.119

$$\text{Pu-236/238 ppm} = \frac{(5.80 \text{ MeV Area Counts} \times \text{Pu-236}_{t_{1/2}} \times 236) \times 1E6}{(\text{Full Spectrum Counts} \times \text{Pu-238}_{t_{1/2}} \times 238)}$$

$$\text{Relative Error} = \frac{2 \times (5.80 \text{ MeV Area Counts})^{1/2}}{5.80 \text{ Area Counts}}$$

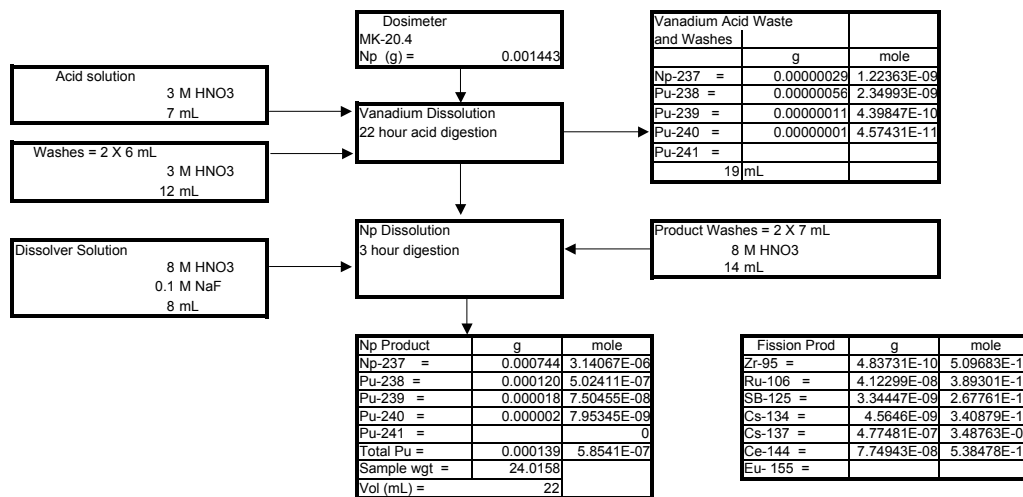

Target	Diss #	Dosimeter Np input g	Np input mole	Vial Tare g	Solution & Vial g	Solution weight g	Np Prod. g	Np Prod. mole	Pu-238 g	Pu-236 ppm	Adjusted Pu- 236 ppm	Total Pu g
MK-20.4	ADD-23	0.001443	6.09E-06	27.0334	51.0492	24.015800	0.000744	3.14E-06	0.000120	2.380000	3.551951	0.000139
	DDJ-23			27.1932	44.4586	17.265400	0.0000029					

	Actual	Predicted (BGS)	Actual/Pred
Np Residual Amount (wt basis) Np prod / Np in	= 0.5159		#DIV/0!
Pu-238/Total Pu (wt basis)	= 0.8577		#DIV/0!
Conversion of Np to Pu (mol basis) = Pu total/ Np in	= 0.0962		#DIV/0!
Conversion of Np to FP (mol basis) = Fp prod/Np in	= 0.0007		
Fractional loss of Np in Liq Waste (wt basis)	= NA		
Fractional loss of Pu in Liq Waste (wt basis)	= NA		

Pu-236 content ppm	Discharge Date	Analysis Date	Time elapsed (t) days	Pu-236 t1/2 years	t1/2 days	Adjusted Pu-236 ppm
2.38	11/1/2001	6/27/2003	-603.00	2.86	1043.88	3.55

Analysis Date	Time elapsed (t) days	Pu-238 t1/2, years	Pu238, t1/2 days	Adjusted Pu-238, g
5/28/2003	-573.00	87.7	32032.425	0.000121


Analysis	Sample	Co-60 Bq/g	Zr-95 Bq/g	Ru-106 Bq/g	SB-125 Bq/g	Cs-134 Bq/g	Cs-137 Bq/g	Ce-144 Bq/g	Eu-155 Bq/g
Gr gamma	ADD-23, 030429-056		1.60E+04	2.10E+05	5.40E+03	9.10E+03	6.40E+04	3.80E+05	3.80E+03
	DDJ-23, 030820-036	7.30E+03		1.80E+04		2.10E+03	4.70E+03		
Alpha & Beta	Sample	Alpha Bq/g	Beta Bq/g	total activity Bq/g	alpha PHA	Pu238, Bq			
	ADD-23, 030429-056	2.90E+06	1.80E+06	4.70E+06					
	DDJ-23, 030820-036	1.90E+04	2.51E+05	2.70E+05					
ICP	Sample	Np-237 ppb (ng/g)	Pu-238 ppb (ng/g)	Pu-239 ppb (ng/g)	Pu-240 ppb (ng/g)	Pu-241 ppb (ng/g)	Pu-242 ppb (ng/g)	Pu-244 ppb (ng/g)	
	ADD-23, 030429-056	3.10E+04	4.98E+03	7.47E+02	7.95E+01	<3.97E+01	<3.97E+01	<3.97E+01	
	DDJ-23, 030820-036	1.68E+02	3.24E+01	6.09E+00	6.36E-01	<4.55E-01	<4.55E-01	<4.55E-01	
Pu-Alpha Scan TTA extraction	Sample	Pu-236/Pu-238 ppm (ug/mL)	Relative error %						
	ADD-23, 030429-056	2.38	5.2						

Reference Information	MW	Density g/cc
NpO2	269.047	11.143
Np237	237.0482	20.476
Pu238	238.0496	19.851
Pu239	239.0522	19.851
Pu240	240.0538	19.851
Pu241	241.0568	19.851
Pu242	242.0587	19.851
Conversion	3.70E+10 Bq/Ci	
365.25 days/year		

$$N = N^0 \cdot \exp(-(\ln 2/t_{1/2} \cdot t))$$

Reference Information	Specific activity Calculation	T1/2 s	M g/mol	Specific activity Ci/g
Factor =	1.13E+13			
Co-60		166328640	59.9338222	1130.670
Zr-95		5531328	94.9080427	21469.000
Ru-106		32278176	105.9073269	3306.000
SB-125		87042172.32	124.9052478	1048.000
Cs-134		65160132.48	133.9067134	1294.000
Cs-137		948937032	136.9070835	87.000
Ce-144		24614755.2	143.9136427	3182.800
Eu-155		150248889.4	154.9228894	465.000
Pu-238		2767601520	238.0495534	17.119

Pu-236/238 ppm =	(5.80 MeV Area Counts X Pu-236 _{t1/2} X 236) X 1E6 (Full Spectrum Counts X Pu-238 _{t1/2} X 238)
Relative Error =	2 X (5.80 MeV Area Counts) ^{1/2} 5.80 Area Counts

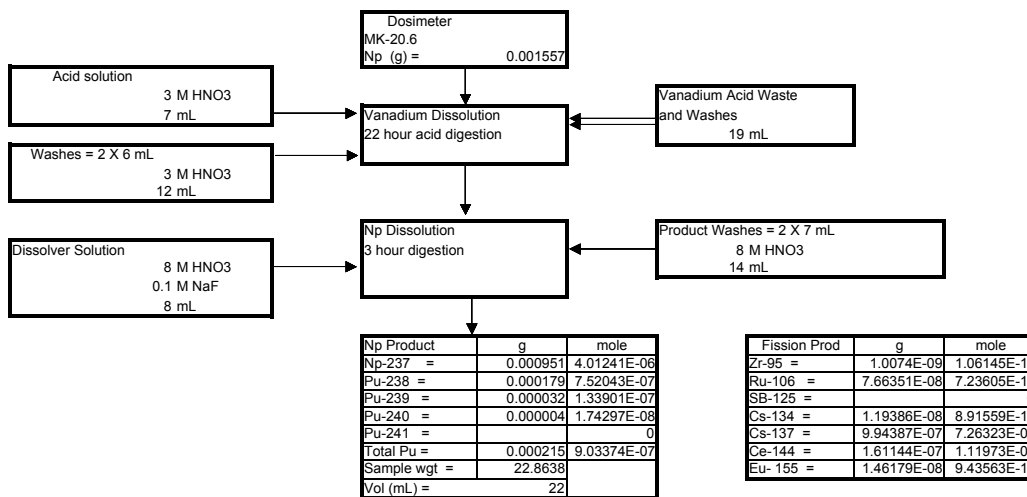

Target	Diss #	Dosimeter Np input g	Np input mole	Vial Tare g	Solution & Vial g	Solution weight g	Np Prod. g	Np Prod. mole	Pu-238 g	Pu-238 ppm	Adjusted Pu-238 ppm	Total Pu g
MK-20.6	ADD-24	0.001557	6.57E-06	27.1896	50.0534	22.863800	0.000951	4.01E-06	0.000179	2.840000	4.238463	0.000215
	DJJ-24			27.1381	46.6526	19.5145						

	Actual	Predicted (BGS)	Actual/Pred
Np Residual Amount (wt basis) Np prod / Np in	=	0.6109	#DIV/0!
Pu-238/Total Pu (wt basis)	=	0.8318	#DIV/0!
Conversion of Np to Pu (mol basis) = Pu total/ Np in	=	0.1375	#DIV/0!
Conversion of Np to FP (mol basis) = Fp prod/Np in	=	0.0014	
Fractional loss of Np in Liq Waste (wt basis)	=	NA	
Fractional loss of Pu in Liq Waste (wt basis)	=	NA	


Pu-236 content ppm	Discharge Date	Analysis Date	Time elapsed (t) days	Pu-236 t1/2 years	t1/2 days	Adjusted Pu-236 ppm
2.84	11/1/2001	6/27/2003	-603.00	2.86	1043.88	4.24

Analysis Date	Time elapsed (t) days	Pu-238 t1/2, years	Pu238, t1/2 days	Adjusted Pu-238, g
5/28/2003	-573.00	87.7	32032.425	0.000181

Analysis	Sample	Co-60 Bq/g	Zr-95 Bq/g	Ru-106 Bq/g	SB-125 Bq/g	Cs-134 Bq/g	Cs-137 Bq/g	Ce-144 Bq/g	Eu-155 Bq/g
Gr gamma	ADD-24, 030429-057		3.50E+04	4.10E+05		2.50E+04	1.40E+05	8.30E+05	1.10E+04
Alpha & Beta	Sample	Alpha Bq/g	Beta Bq/g	total activity Bq/g	alpha PHA	Pu238, Bq			
	ADD-24, 030429-057	4.90E+06	3.60E+06	8.50E+06					
ICP	Sample	Np-237 ppb (ng/g)	Pu-238 ppb (ng/g)	Pu-239 ppb (ng/g)	Pu-240 ppb (ng/g)	Pu-241 ppb (ng/g)	Pu-242 ppb (ng/g)	Pu-244 ppb (ng/g)	
	ADD-24, 030429-057	4.16E+04	7.83E+03	1.40E+03	1.83E+02	<3.98E+01	<3.98E+01	<3.98E+01	
Pu-Alpha Scan TTA extraction	Sample	Pu-236/Pu-238 ppm (ug/mL)	Relative error %						
	ADD-24, 030429-057	2.84	4.5						

Reference Information			Reference Information			
	MW	Density g/cc	Specific activity Calculation			
NpO2	269.047	11.143	Factor =	1.13E+13	T1/2 s	M g/mol
Np237	237.0482	20.476				
Pu238	238.0496	19.851				
Pu239	239.0522	19.851				
Pu240	240.0538	19.851				
Pu241	241.0568	19.851				
Pu242	242.0587	19.851				
Conversion	3.70E+10 Bq/Ci					
	365.25 days/year					
N = N ⁰ *exp -(ln2/t _{1/2} * t)						

Pu-236/238 ppm =	(5.80 MeV Area Counts X Pu-236 _{t1/2} X 236) X 1E6 (Full Spectrum Counts X Pu-238 _{t1/2} X 238)
Relative Error =	2 X (5.80 MeV Area Counts) ^{1/2} 5.80 Area Counts

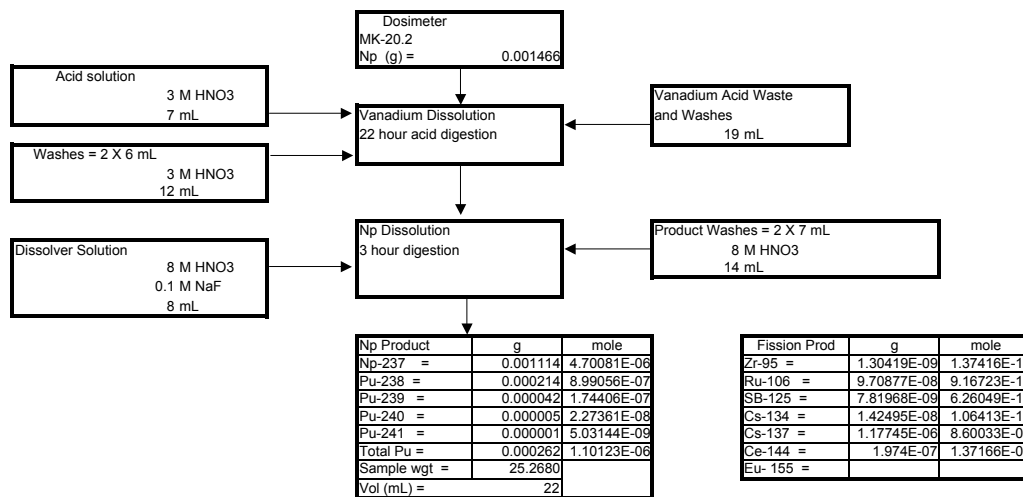

Target	Diss #	Dosimeter Np input g	Np input mole	Vial Tare g	Solution & Vial g	Solution weight g	Np Prod. g	Np Prod. mole	Pu-238 g	Pu-236 ppm	Adjusted Pu- 236 ppm	Total Pu g
MK-20.2	ADD-22	0.001466	6.18E-06	27.1953	52.4633	25.268000	0.001114	4.70E-06	0.000214	2.230000	3.328089	0.000262
	DDJ-22			26.9513	46.8505	19.899200						

	Actual	Predicted (BGS)	Actual/Pred
Np Residual Amount (wt basis) Np prod / Np in	= 0.7601		#DIV/0!
Pu-238/Total Pu (wt basis)	= 0.8157		#DIV/0!
Conversion of Np to Pu (mol basis) = Pu total/ Np in	= 0.1781		#DIV/0!
Conversion of Np to FP (mol basis) = Fp prod/Np in	= 0.0018		
Fractional loss of Np in Liq Waste (wt basis)	= NA		
Fractional loss of Pu in Liq Waste (wt basis)	= NA		

Pu-236 content ppm	Discharge Date	Analysis Date	Time elapsed (t) days	Pu-236 t1/2 years	t1/2 days	Adjusted Pu-236 ppm	Analysis Date	Time elapsed (t) days	Pu-238 t1/2, years	Pu238, t1/2 days	Adjusted Pu-238, g
2.23	11/1/2001	6/27/2003	-603.00	2.86	1043.88	3.33	5/28/2003	-573.00	87.7	32032.425	0.000217

Analysis	Sample	Co-60 Bq/g	Zr-95 Bq/g	Ru-106 Bq/g	SB-125 Bq/g	Cs-134 Bq/g	Cs-137 Bq/g	Ce-144 Bq/g	Eu-155 Bq/g
Gr gamma	ADD-22, 030429-055		4.10E+04	4.70E+05	1.20E+04	2.70E+04	1.50E+05	9.20E+05	


Alpha & Beta	Sample	Alpha Bq/g	Beta Bq/g	total activity Bq/g	alpha PHA	Pu238, Bq
	ADD-22, 030429-055	5.40E+06	3.80E+06	9.20E+06		

ICP	Sample	Np-237 ppb (ng/g)	Pu-238 ppb (ng/g)	Pu-239 ppb (ng/g)	Pu-240 ppb (ng/g)	Pu-241 ppb (ng/g)	Pu-242 ppb (ng/g)	Pu-244 ppb (ng/g)
	ADD-22, 030429-055	4.41E+04	8.47E+03	1.65E+03	2.16E+02	4.80E+01	<4.0 E+01	<4.0 E+01

Pu-Alpha Scan TTA extraction	Sample	Pu-236/Pu-238 ppm (ug/mL)	Relative error %
	ADD-22, 030429-055	2.23	6.2

Reference Information			Reference Information			
	MW	Density g/cc	Specific activity Calculation			
			Factor = 1.13E+13	T1/2 s	M g/mol	Specific activity Ci/g
NpO2	269.047	11.143		166328640	59.9338222	1130.670
Np237	237.0482	20.476		5531328	94.9080427	21469.000
Pu238	238.0496	19.851		32278176	105.9073269	3306.000
Pu239	239.0522	19.851		87042172.32	124.9052478	1048.000
Pu240	240.0538	19.851		65160132.48	133.9067134	1294.000
Pu241	241.0568	19.851		948937032	136.9070835	87.000
Pu242	242.0587	19.851		24614755.2	143.9136427	3182.800
Conversion	3.70E+10 Bq/Ci			150248889.4	154.9228894	465.000
365.25 days/year				2767601520	238.0495534	17.119
N = N ⁰ *exp -(ln2/t _{1/2} * t)						

Pu-236/238 ppm =	(5.80 MeV Area Counts X Pu-236 _{1/2} X 236) X 1E6 (Full Spectrum Counts X Pu-238 _{1/2} X 238)
Relative Error =	2 X (5.80 MeV Area Counts) ^{1/2} 5.80 Area Counts

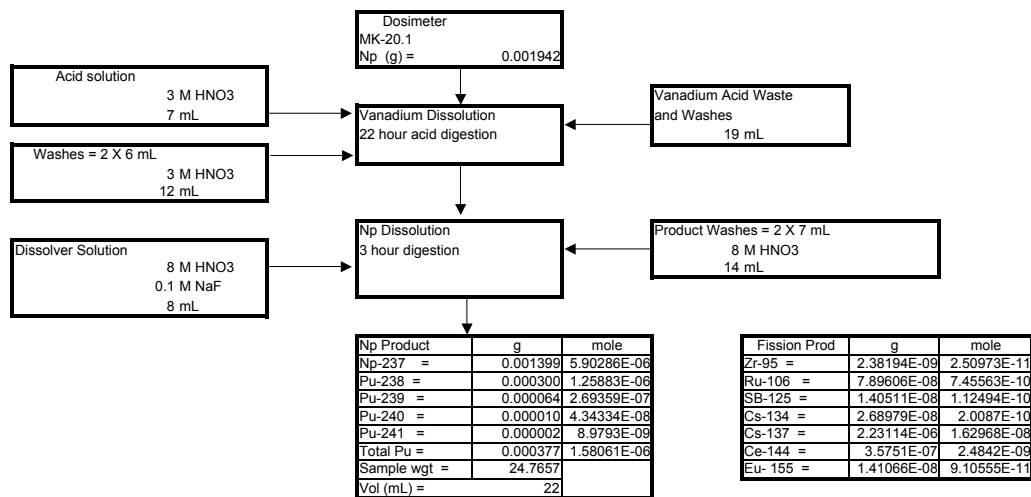

Target	Diss #	Dosimeter Np input g	Np input mole	Vial Tare g	Solution & Vial g	Solution weight g	Np Prod. g	Np Prod. mole	Pu-238 g	Pu-236 ppm	Adjusted Pu- 236 ppm	Total Pu g
MK-20.1	ADD-21	0.001942	8.19E-06	26.9772	51.7429	24.765700	0.001399	5.90E-06	0.000300		4.197451	0.000377
	DDJ-21			27.0216	45.8164	18.7948						

	Actual	Predicted (BGS)	Actual/Pred
Np Residual Amount (wt basis) Np prod / Np in	= 0.7205		#DIV/0!
Pu-238/Total Pu (wt basis)	= 0.7956		#DIV/0!
Conversion of Np to Pu (mol basis) = Pu total/ Np in	= 0.1929		#DIV/0!
Conversion of Np to FP (mol basis) = Fp prod/Np in	= 0.0024		
Fractional loss of Np in Liq Waste (wt basis)	= NA		
Fractional loss of Pu in Liq Waste (wt basis)	= NA		

Pu-236 content ppm	Discharge Date	Analysis Date	Time elapsed (t) days	Pu-236 t1/2 years	t1/2 days	Adjusted Pu-236 ppm	Analysis Date	Time elapsed (t) days	Pu-238 t1/2, years	Pu238, t1/2 days	Adjusted Pu-238, g
2.82	11/1/2001	6/23/2003	-599.00	2.86	1043.88	4.20	5/28/2003	-573.00	87.7	32032.425	0.000303

Analysis	Sample	Co-60 Bq/g	Zr-95 Bq/g	Ru-106 Bq/g	SB-125 Bq/g	Cs-134 Bq/g	Cs-137 Bq/g	Ce-144 Bq/g	Eu-155 Bq/g
Gr gamma	ADD-21, 030429-054		7.64E+04	3.90E+05	2.20E+04	5.20E+04	2.90E+05	1.70E+06	9.80E+03

Alpha & Beta	Sample	Alpha Bq/g	Beta Bq/g	total activity Bq/g	alpha PHA	Pu238, Bq
	ADD-21, 030429-054	7.60E+06	5.40E+06	1.30E+07		

ICP	Sample	Np-237 ppb (ng/g)	Pu-238 ppb (ng/g)	Pu-239 ppb (ng/g)	Pu-240 ppb (ng/g)	Pu-241 ppb (ng/g)	Pu-242 ppb (ng/g)	Pu-244 ppb (ng/g)
	ADD-21, 030429-054	5.65E+04	1.21E+04	2.60E+03	4.21E+02	8.74E+01	<3.97E+01	<3.97E+01

Pu-Alpha Scan TTA extraction	Sample	Pu-236/Pu-238 ppm (ug/mL)	Relative error %
	ADD-21, 030429-054	2.82	3.7

Reference Information			Reference Information			
	MW	Density g/cc	Specific activity Calculation			
			Factor = 1.13E+13	T1/2 s	M g/mol	Specific activity Ci/g
NpO2	269.047	11.143		166328640	59.9338222	1130.670
Np237	237.0482	20.476		5531328	94.9080427	21469.000
Pu238	238.0496	19.851		32278176	105.9073269	3306.000
Pu239	239.0522	19.851		87042172.32	124.9052478	1048.000
Pu240	240.0538	19.851		65160132.48	133.9067134	1294.000
Pu241	241.0568	19.851		948937032	136.9070835	87.000
Pu242	242.0587	19.851		24614755.2	143.9136427	3182.800
Conversion	3.70E+10 Bq/Ci			150248889.4	154.9228894	465.000
365.25 days/year				2767601520	238.0495534	17.119
N = N ⁰ * exp ⁻ (ln2/t _{1/2} * t)						

Pu-236/238 ppm =	(5.80 MeV Area Counts X Pu-236 _{t1/2} X 236) X 1E6 (Full Spectrum Counts X Pu-238 _{t1/2} X 238)
Relative Error =	2 X (5.80 MeV Area Counts) ^{1/2} 5.80 Area Counts

INTERNAL DISTRIBUTION

- | | |
|-----------------------|------------------------|
| 1. C. W. Alexander | 19. B. E. Lewis |
| 2. W. D. Bond | 20. S. C. Marschman |
| 3-4. R. R. Brunson | 21-22. R. R. McMahon |
| 5. R. M. Canon | 23. P. E. Osborne |
| 6. E. D. Collins | 24. J. E. Rushton |
| 7. G. D. Del Cul | 25. C. M. Simmons |
| 8. L. K. Felker | 26. D. W. Simmons |
| 9. S. Goluoglu | 27. L. M. Toth |
| 10. M. A. Green | 28. L. D. Trowbridge |
| 11. J. N. Herndon | 29-33. R. M. Wham |
| 12. D. J. Hill | 34. D. F. Williams |
| 13-17. A. S. Icenhour | 35. NSTD DMC |
| 18. J. M. Keller | 36. OTIC-RC, OSTI, CRL |

EXTERNAL DISTRIBUTION

37. L. W. Boyd, DOE-ORO, U.S. Department of Energy, P.O. Box 2008 MS-6269,
Oak Ridge, TN 37831
38. W. P. Carroll, DOE-HQ, NE-40/Germantown Building, U.S. Department of Energy, 1000
Independence Ave., S.W., Washington, DC 20585-1290
39. S. R. Martin, Jr., DOE-ORO, U.S. Department of Energy, P.O. Box 2008 MS-6269,
Oak Ridge, TN 37831
40. B. G. Schnitzler, Idaho National Engineering and Environmental Laboratory, P. O. Box 1625,
Idaho Falls, ID 83415